

11.12 CONCRETE BATCHING

11.12-1 Process Description ¹⁻⁵

Concrete is composed essentially of water, cement, sand (fine aggregate) and coarse aggregate. Coarse aggregate may consist of gravel, crushed stone or iron blast furnace slag. Some specialty aggregate products could be either heavyweight aggregate (of barite, magnetite, limonite, ilmenite, iron or steel) or lightweight aggregate (with sintered clay, shale, slate, diatomaceous shale, perlite, vermiculite, slag pumice, cinders, or sintered fly ash). Supplementary cementitious materials, also called mineral admixtures or pozzolan minerals may be added to make the concrete mixtures more economical, reduce permeability, increase strength, or influence other concrete properties. Typical examples are natural pozzolans, fly ash, ground granulated blast-furnace slag, and silica fume, which can be used individually with portland or blended cement or in different combinations. Chemical admixtures are usually liquid ingredients that are added to concrete to entrain air, reduce the water required to reach a required slump, retard or accelerate the setting rate, to make the concrete more flowable or other more specialized functions.

Approximately 75 percent of the U.S. concrete manufactured is produced at plants that store, convey, measure and discharge these constituents into trucks for transport to a job site. At most of these plants, sand, aggregate, cement and water are all gravity fed from the weight hopper into the mixer trucks. The concrete is mixed on the way to the site where the concrete is to be poured. At some of these plants, the concrete may also be manufactured in a central mix drum and transferred to a transport truck. Most of the remaining concrete manufactured are products cast in a factory setting. Precast products range from concrete bricks and paving stones to bridge girders, structural components, and panels for cladding. Concrete masonry, another type of manufactured concrete, may be best known for its conventional 8 x 8 x 16-inch block. In a few cases concrete is dry batched or prepared at a building construction site. Figure 11.12-1 is a generalized process diagram for concrete batching.

The raw materials can be delivered to a plant by rail, truck or barge. The cement is transferred to elevated storage silos pneumatically or by bucket elevator. The sand and coarse aggregate are transferred to elevated bins by front end loader, clam shell crane, belt conveyor, or bucket elevator. From these elevated bins, the constituents are fed by gravity or screw conveyor to weigh hoppers, which combine the proper amounts of each material.

11.12-2 Emissions and Controls ⁶⁻⁸

Particulate matter, consisting primarily of cement and pozzolan dust but including some aggregate and sand dust emissions, is the primary pollutant of concern. In addition, there are emissions of metals that are associated with this particulate matter. All but one of the emission points are fugitive in nature. The only point sources are the transfer of cement and pozzolan material to silos, and these are usually vented to a fabric filter or "sock". Fugitive sources include the transfer of sand and aggregate, truck loading, mixer loading, vehicle traffic, and wind erosion from sand and aggregate storage piles. The amount of fugitive emissions generated during the transfer of sand and aggregate depends primarily on the surface moisture content of these materials. The extent of fugitive emission control varies widely from plant to plant. Particulate emission factors for concrete batching are give in Tables 11.12-1 and 11.12-2.

Types of controls used may include water sprays, enclosures, hoods, curtains, shrouds, movable and telescoping chutes, central duct collection systems, and the like. A major source of potential emissions, the movement of heavy trucks over unpaved or dusty surfaces in and around the plant, can be controlled by good maintenance and wetting of the road surface.

Predictive equations that allow for emission factor adjustment based on plant specific conditions are given in the Background Document for Chapter 11.12 and Chapter 13. Whenever plant specific data are available, they should be used with these predictive equations (e.g. Equations 11.12-1 through 11.12-3) in lieu of the general fugitive emission factors presented in Table 11.12-1 through 11.12-5 in order to adjust to site specific conditions, such as moisture levels and localized wind speeds.

11.12-3 Updates since the 5th Edition.

October 2001 – This major revision of the section replaced emissions factors based upon engineering judgment and poorly documented and performed source test reports with emissions tests conducted at modern operating truck mix and central mix facilities. Emissions factors for both total PM and total PM₁₀ were developed from this test data.

June 2006 – This revision of the section supplemented the two source tests with several additional source tests of central mix and truck mix facilities. The measurement of the capture efficiency, local wind speed and fines material moisture level was improved over the previous two source tests. In addition to quantifying total PM and PM₁₀, PM_{2.5} emissions were quantified at all of the facilities. Single value emissions factors for truck mix and central mix operations were revised using all of the data. Additionally, parameterized emissions factor equations using local wind speed and fines material moisture content were developed from the newer data.

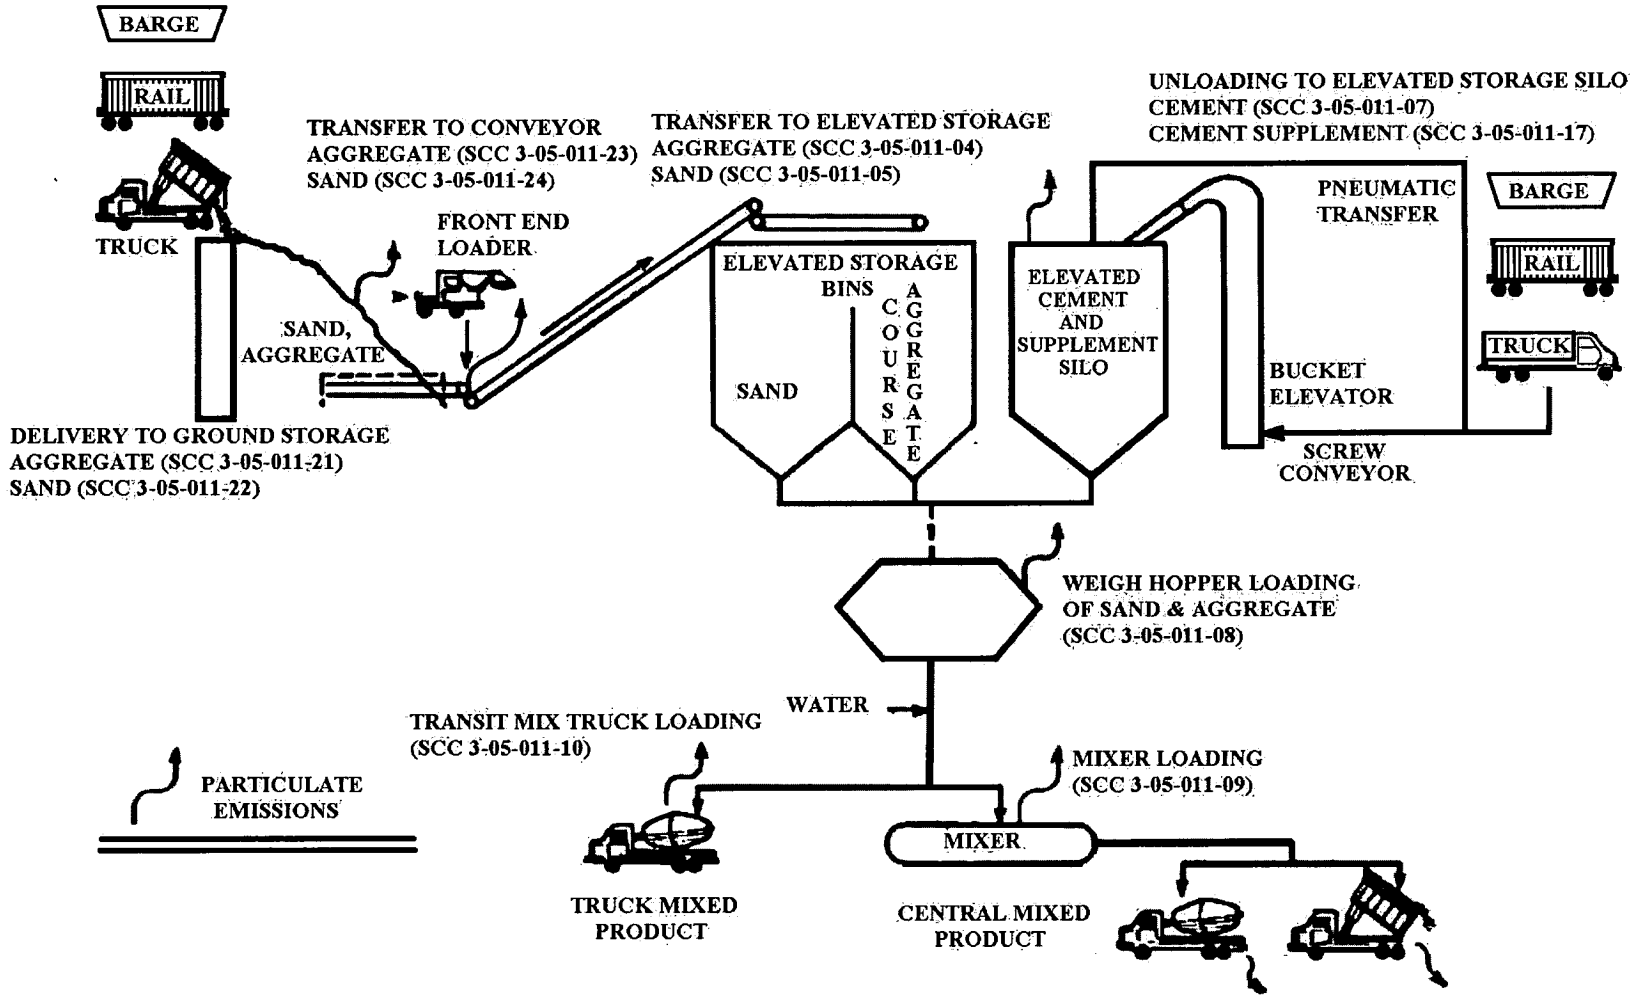


Figure 11.12-1. Typical Concrete Batching Process.

TABLE 11.12-1 (METRIC UNITS)
EMISSION FACTORS FOR CONCRETE BATCHING ^a

Source (SCC)	Uncontrolled				Controlled			
	Total PM	Emission Factor Rating	Total PM ₁₀	Emission Factor Rating	Total PM	Emission Factor Rating	Total PM ₁₀	Emission Factor Rating
Aggregate transfer ^b (3-05-011-04,-21,23)	0.0035	D	0.0017	D	ND		ND	
Sand transfer ^b (3-05-011-05,22,24)	0.0011	D	0.00051	D	ND		ND	
Cement unloading to elevated storage silo (pneumatic) ^c (3-05-011-07)	0.36	E	0.23	E	0.00050	D	0.00017	D
Cement supplement unloading to elevated storage silo (pneumatic) ^d (3-05-011-17)	1.57	E	0.65	E	0.0045	D	0.0024	E
Weigh hopper loading ^e (3-05-011-08)	0.0026	D	0.0013	D	ND		ND	
Mixer loading (central mix) ^f (3-05-011-09)	0.272 or Eqn. 11.12-1	B	0.067 or Eqn. 11.12-1	B	0.0087 or Eqn. 11.12-1	B	0.0024 or Eqn. 11.12-1	B
Truck loading (truck mix) ^g (3-05-011-10)	0.498	B	0.139	B	0.0280 or Eqn. 11.12-1	B	0.0080 or Eqn. 11.12-1	B
Vehicle traffic (paved roads)	See AP-42 Section 13.2.1							
Vehicle traffic (unpaved roads)	See AP-42 Section 13.2.2							
Wind erosion from aggregate and sand storage piles	See AP-42 Section 13.2.5							

ND = No data

^a All emission factors are in kg of pollutant per Mg of material loaded unless noted otherwise. Loaded material includes course aggregate, sand, cement, cement supplement and the surface moisture associated with these materials. The average material composition of concrete batches presented in references 9 and 10 was 846 kg course aggregate, 648 kg sand, 223 kg cement and 33kg cement supplement. Approximately 75 liters of water was added to this solid material to produce 1826 kg of concrete.

^b Reference 9 and 10. Emission factors are based upon an equation from AP-42, Section 13.2.2, with $k_{PM-10} = .35$, $k_{PM} = .74$, $U = 10\text{mph}$, $M_{\text{aggregate}} = 1.77\%$, and $M_{\text{sand}} = 4.17\%$. These moisture contents of the materials ($M_{\text{aggregate}}$ and M_{sand}) are the averages of the values obtained from Reference 9 and Reference 10.

^c The uncontrolled PM & PM-10 emission factors were developed from Reference 9. The controlled emission factor for PM was developed from References 9, 10, 11, and 12. The controlled emission factor for PM-10 was developed from References 9 and 10.

^d The controlled PM emission factor was developed from Reference 10 and Reference 12, whereas the controlled PM-10 emission factor was developed from only Reference 10.

^e Emission factors were developed by using the Aggregate and Sand Transfer Emission Factors in conjunction with the ratio of aggregate and sand used in an average yard³ of concrete. The unit for these emission factors is kg of pollutant per Mg of aggregate and sand.

^f References 9, 10, and 14. The emission factor units are kg of pollutant per Mg of cement and cement supplement. The general factor is the arithmetic mean of all test data.

^g Reference 9, 10, and 14. The emission factor units are kg of pollutant per Mg of cement and cement supplement. The general factor is the arithmetic mean of all test data.

TABLE 11.12-2 (ENGLISH UNITS)
EMISSION FACTORS FOR CONCRETE BATCHING ^a

Source (SCC)	Uncontrolled				Controlled			
	Total PM	Emission Factor Rating	Total PM ₁₀	Emission Factor Rating	Total PM	Emission Factor Rating	Total PM ₁₀	Emission Factor Rating
Aggregate transfer ^b (3-05-011-04,-21,23)	0.0069	D	0.0033	D	ND		ND	
Sand transfer ^b (3-05-011-05,22,24)	0.0021	D	0.00099	D	ND		ND	
Cement unloading to elevated storage silo (pneumatic) ^c (3-05-011-07)	0.72	E	0.46	E	0.00099	D	0.00034	D
Cement supplement unloading to elevated storage silo (pneumatic) ^d (3-05-011-17)	3.14	E	1.10	E	0.0089	D	0.0049	E
Weigh hopper loading ^e (3-05-011-08)	0.0051	D	0.0024	D	ND		ND	
Mixer loading (central mix) ^f (3-05-011-09)	0.544 or Eqn. 11.12-1	B	0.134 or Eqn. 11.12-1	B	0.0173 or Eqn. 11.12-1	B	0.0048 or Eqn. 11.12-1	B
Truck loading (truck mix) ^g (3-05-011-10)	0.995	B	0.278	B	0.0568 or Eqn. 11.12-1	B	0.0160 or Eqn. 11.12-1	B
Vehicle traffic (paved roads)	See AP-42 Section 13.2.1							
Vehicle traffic (unpaved roads)	See AP-42 Section 13.2.2							
Wind erosion from aggregate and sand storage piles	See AP-42 Section 13.2.5							

ND = No data

^a All emission factors are in lb of pollutant per ton of material loaded unless noted otherwise. Loaded material includes course aggregate, sand, cement, cement supplement and the surface moisture associated with these materials. The average material composition of concrete batches presented in references 9 and 10 was 1865 lbs course aggregate, 1428 lbs sand, 491 lbs cement and 73 lbs cement supplement. Approximately 20 gallons of water was added to this solid material to produce 4024 lbs (one cubic yard) of concrete.

^b Reference 9 and 10. Emission factors are based upon an equation from AP-42, Section 13.2.2, with $k_{PM-10} = .35$, $k_{PM} = .74$, $U = 10\text{mph}$, $M_{\text{aggregate}} = 1.77\%$, and $M_{\text{sand}} = 4.17\%$. These moisture contents of the materials ($M_{\text{aggregate}}$ and M_{sand}) are the averages of the values obtained from Reference 9 and Reference 10.

^c The uncontrolled PM & PM-10 emission factors were developed from Reference 9. The controlled emission factor for PM was developed from References 9, 10, 11, and 12. The controlled emission factor for PM-10 was developed from References 9 and 10.

^d The controlled PM emission factor was developed from Reference 10 and Reference 12, whereas the controlled PM-10 emission factor was developed from only Reference 10.

^e Emission factors were developed by using the Aggregate and Sand Transfer Emission Factors in conjunction with the ratio of aggregate and sand used in an average yard³ of concrete. The unit for these emission factors is lb of pollutant per ton of aggregate and sand.

^f References 9, 10, and 14. The emission factor units are lb of pollutant per ton of cement and cement supplement. The general factor is the arithmetic mean of all test data.

^g Reference 9, 10, and 14. The emission factor units are lb of pollutant per ton of cement and cement supplement. The general factor is the arithmetic mean of all test data.

The particulate matter emissions from truck mix and central mix loading operations are calculated in accordance with the values in Tables 11.12-1 or 11.12-2 or by Equation 11.12-1¹⁴ when site specific data are available.

$$E = k (0.0032) \left[\frac{U^a}{M^b} \right] + c \quad \text{Equation 11.12-1}$$

- E = Emission factor in lbs./ton of cement and cement supplement
 k = Particle size multiplier (dimensionless)
 U = Wind speed at the material drop point, miles per hour (mph)
 M = Minimum moisture (% by weight) of cement and cement supplement
 a, b = Exponents
 c = Constant

The parameters for Equation 11.12-1 are summarized in Tables 11.12-3 and 11.12-4.

Table 11.12-3. Equation Parameters for Truck Mix Operations

Condition	Parameter Category	k	a	b	c
Controlled ¹	Total PM	0.8	1.75	0.3	0.013
	PM ₁₀	0.32	1.75	0.3	0.0052
	PM _{10-2.5}	0.288	1.75	0.3	0.00468
	PM _{2.5}	0.048	1.75	0.3	0.00078
Uncontrolled ¹	Total PM	0.995			
	PM ₁₀	0.278			
	PM _{10-2.5}	0.228			
	PM _{2.5}	0.050			

Table 11.12-4. Equation Parameters for Central Mix Operations

Condition	Parameter Category	k	a	b	c
Controlled ¹	Total PM	0.19	0.95	0.9	0.0010
	PM ₁₀	0.13	0.45	0.9	0.0010
	PM _{10-2.5}	0.12	0.45	0.9	0.0009
	PM _{2.5}	0.03	0.45	0.9	0.0002
Uncontrolled ¹	Total PM	5.90	0.6	1.3	0.120
	PM ₁₀	1.92	0.4	1.3	0.040
	PM _{10-2.5}	1.71	0.4	1.3	0.036
	PM _{2.5}	0.38	0.4	1.3	0

1. Emission factors expressed in lbs/tons of cement and cement supplement

To convert from units of lbs/ton to units of kilograms per mega gram, the emissions calculated by Equation 11.12-1 should be divided by 2.0.

Particulate emission factors per yard of concrete for an average batch formulation at a typical facility are given in Tables 11.12-5 and 11.12-6. For truck mix loading and central mix loading, the

emissions of PM, PM-10, PM-10-2.5, and PM-2.5 are calculated by multiplying the emission factor calculated using Equation 11.12-2 by a factor of 0.282 to convert from emissions per ton of cement and cement supplement to emissions per yard of concrete. This equation is based on a typical concrete formulation of 564 pounds of cement and cement supplement in a total of 4,024 pounds of material (including aggregate, sand, and water). This calculation is summarized in Equation 11.12-2.

$$\text{PM, PM10, PM10-2.5, PM2.5 emissions} \left(\frac{\text{pounds}}{\text{yd}^3 \text{ of concrete}} \right) = 0.282 (\text{Equation 11.12-1 factor or Table 11.12-2 Factor})$$

Equation 11.12-2

Metals emission factors for concrete batching are given in Tables 11.12-6 and 11.12-7. Alternatively, the metals emissions from ready mix plants can be calculated based on (1) the weighted average concentration of the metal in the cement and the cement supplement (i.e. flyash) and (2) on the total particulate matter emission factors calculated in accordance with Equation 11.12-3. Emission factors calculated using Equation 11.12-3 are rated D.

$$\text{Metal}_{\text{EF}} = \text{PM}_{\text{EF}} \left(\frac{aC + bS}{C + S} \right) \quad \text{Equation 11.12-3}$$

Where:

Metal _{EF}	=	Metal Emissions, Lbs. As per Ton of Cement and Cement Supplement
PM _{EF}	=	Controlled Particulate Matter Emission Factor (PM, PM10, or PM2.5) Lbs. per Ton of Cement and Cement Supplement
a	=	ppm of Metal in Cement
C	=	Quantity of Cement Used, Lbs. per hour
b	=	ppm of Metal in Cement Supplement
S	=	Quantity of Cement Supplement Used, Lbs. per hour

This equation is based on the assumption that 100% of the particulate matter emissions are material entrained from the cement and cement supplement streams. Equation 11.12-3 over-estimates total metal emissions to the extent that sand and fines from aggregate contribute to the total particulate matter emissions.

**TABLE 11.12-5 (ENGLISH UNITS)
PLANT WIDE EMISSION FACTORS PER YARD OF TRUCK MIX CONCRETE ^a**

	Uncontrolled		Controlled	
	PM (lb/yd ³)	PM-10 (lb/yd ³)	PM (lb/yd ³)	PM-10 (lb/yd ³)
Aggregate delivery to ground storage (3-05-011-21)	0.0064	0.0031	0.0064	0.0031
Sand delivery to ground storage (3-05-011-22)	0.0015	0.0007	0.0015	0.0007
Aggregate transfer to conveyor (3-05-011-23)	0.0064	0.0031	0.0064	0.0031
Sand transfer to conveyor (3-05-011-24)	0.0015	0.0007	0.0015	0.0007
Aggregate transfer to elevated storage (3-05-011-04)	0.0064	0.0031	0.0064	0.0031
Sand transfer to elevated storage (3-05-011-05)	0.0015	0.0007	0.0015	0.0007
Cement delivery to Silo (3-05-011-07 controlled)	0.0002	0.0001	0.0002	0.0001
Cement supplement delivery to Silo (3-05-011-17 controlled)	0.0003	0.0002	0.0003	0.0002
Weigh hopper loading (3-05-011-08)	0.0079	0.0038	0.0079	0.0038
Truck mix loading (3-05-011-10)	See Equation 11.12-2			

**TABLE 11.12-6 (ENGLISH UNITS)
PLANT WIDE EMISSION FACTORS PER YARD OF CENTRAL MIX CONCRETE ^a**

	Uncontrolled		Controlled	
	PM (lb/yd ³)	PM-10 (lb/yd ³)	PM (lb/yd ³)	PM-10 (lb/yd ³)
Aggregate delivery to ground storage (3-05-011-21)	0.0064	0.0031	0.0064	0.0031
Sand delivery to ground storage (3-05-011-22)	0.0015	0.0007	0.0015	0.0007
Aggregate transfer to conveyor (3-05-011-23)	0.0064	0.0031	0.0064	0.0031
Sand transfer to conveyor (3-05-011-24)	0.0015	0.0007	0.0015	0.0007
Aggregate transfer to elevated storage (3-05-011-04)	0.0064	0.0031	0.0064	0.0031
Sand transfer to elevated storage (3-05-011-05)	0.0015	0.0007	0.0015	0.0007
Cement delivery to Silo (3-05-011-07 controlled)	0.0002	0.0001	0.0002	0.0001
Cement supplement delivery to Silo (3-05-011-17 controlled)	0.0003	0.0002	0.0003	0.0002
Weigh hopper loading (3-05-011-08)	0.0079	0.0038	0.0079	0.0038
Central mix loading (3-05-011-09)	See Equation 11.12-2			

^a Total facility emissions are the sum of the emissions calculated in Tables 11.12-4 or 11.12-5. Total facility emissions do not include road dust and wind blown dust. The emission factors in Tables 11.12-4 and 11.12-5 are based upon the following composition of one yard of concrete.

Coarse Aggregate	1865. pounds
Sand	1428. pounds
Cement	491. pounds
Cement Supplement	73. pounds
Water	20. gallons (167 pounds)

TABLE 11.12-7 (METRIC UNITS)
CONCRETE BATCH PLANT METAL EMISSION FACTORS ^a

	Arsenic	Beryllium	Cadmium	Total Chromium	Lead	Manganese	Nickel	Total Phosphorus	Selenium	Emission Factor Rating
Cement Silo Filling ^b (SCC 3-05-011-07) w/ Fabric Filter	8.38e-07 2.12e-09	8.97e-09 2.43e-10	1.17e-07 2.43e-10	1.26e-07 1.45e-08	3.68e-07 5.46e-09	1.01e-04 5.87e-08	8.83e-06 2.09e-08	5.88e-05 ND	ND ND	E E
Cement Supplement Silo Filling ^c (SCC 3-05-011-17) w/ Fabric Filter	ND 5.02e-07	ND 4.52e-08	ND 9.92e-09	ND 6.10e-07	ND 2.60e-07	ND 1.28e-07	ND 1.14e-06	ND 1.77e-06	ND 3.62e-08	E E
Central Mix Batching ^c (SCC 3-05-011-09) w/ Fabric Filter	1.16e-07 9.35e-09	ND ND	5.92e-09 3.55e-10	7.11e-07 6.34e-08	1.91e-07 1.83e-08	3.06e-05 1.89e-06	1.64e-06 1.24e-07	1.01e-05 6.04e-07	ND ND	E E
Truck Loading ^d (SCC 3-05-011-10) w/ Fabric Filter	1.52e-06 5.80e-07	1.22e-07 5.18e-08	1.71e-08 4.53e-09	5.71e-06 2.05e-06	1.81e-06 7.67e-07	3.06e-05 1.04e-05	5.99e-06 2.39e-06	1.92e-05 6.16e-06	1.31e-06 5.64e-08	E E

ND=No data

^a All emission factors are in kg of pollutant per Mg of material loaded unless noted otherwise. Loaded material includes course aggregate, sand, cement, cement supplement and the surface moisture associated with these materials. The average material composition of concrete batches presented in references 9 and 10 was 846 Kg course aggregate, 648 kg sand, 223 kg cement and 33kg cement supplement. Approximately 75 liters of water was added to this solid material to produce 1826 kg of concrete.

^b The uncontrolled emission factors were developed from Reference 8. The controlled emission factors were developed from Reference 9 and 10. Although controlled emissions of phosphorous compounds were below detection, it is reasonable to assume that the effectiveness is comparable to the average effectiveness (98%) for the other metals.

^c Reference 10.

^d Reference 9. The emission factor units are kg of pollutant per Mg of cement and cement supplement. Emission factors were developed from a typical central mix operation. The average estimate of the percent of emissions captured during each run is 94%.

^e Reference 9 and 10. The emission factor units are kg of pollutant per Mg of cement and cement supplement. Emission factors were developed from two typical truck mix loading operations. Based upon visual observations of every loading operation during the two test programs, the average capture efficiency during the testing was 71%.

TABLE 11.12-8 (ENGLISH UNITS)
CONCRETE BATCH PLANT METAL EMISSION FACTORS ^a

	Arsenic	Beryllium	Cadmium	Total Chromium	Lead	Manganese	Nickel	Total Phosphorus	Selenium	Emission Factor Rating
Cement Silo Filling ^b (SCC 3-05-011-07) w/ Fabric Filter	1.68e-06 4.24e-09	1.79e-08 4.86e-10	2.34e-07 4.86e-10	2.52e-07 2.90e-08	7.36e-07 1.09e-08	2.02e-04 1.17e-07	1.76e-05 4.18e-08	1.18e-05 ND	ND ND	E E
Cement Supplement Silo Filling ^c (SCC 3-05-011-17) w/ Fabric Filter	ND 1.00e-06	ND 9.04e-08	ND 1.98e-10	ND 1.22e-06	ND 5.20e-07	ND 2.56e-07	ND 2.28e-06	ND 3.54e-06	ND 7.24e-08	E E
Central Mix Batching ^c (SCC 3-05-011-09) w/ Fabric Filter	2.32e-07 1.87e-08	ND ND	1.18e-08 7.10e-10	1.42e-06 1.27e-07	3.82e-07 3.66e-08	6.12e-05 3.78e-06	3.28e-06 2.48e-07	2.02e-05 1.20e-06	ND ND	E E
Truck Loading ^d (SCC 3-05-011-10) w/ Fabric Filter	3.04e-06 1.16e-06	2.44e-07 1.04e-07	3.42e-08 9.06e-09	1.14e-05 4.10e-06	3.62e-06 1.53e-06	6.12e-05 2.08e-05	1.19e-05 4.78e-06	3.84e-05 1.23e-05	2.62e-06 1.13e-07	E E

ND=No data

^a All emission factors are in lb of pollutant per ton of material loaded unless noted otherwise. Loaded material includes course aggregate, sand, cement, cement supplement and the surface moisture associated with these materials. The average material composition of concrete batches presented in references 9 and 10 was 1865 lbs course aggregate, 1428 lbs sand, 491 lbs cement and 73 lbs cement supplement. Approximately 20 gallons of water was added to this solid material to produce 4024 lbs (one cubic yard) of concrete.

^b The uncontrolled emission factors were developed from Reference 8. The controlled emission factors were developed from Reference 9 and 10. Although controlled emissions of phosphorous compounds were below detection, it is reasonable to assume that the effectiveness is comparable to the average effectiveness (98%) for the other metals.

^c Reference 10.

^d Reference 9. The emission factor units are lb of pollutant per ton of cement and cement supplement. Emission factors were developed from a typical central mix operation. The average estimate of the percent of emissions captured during each test run is 94%.

^e Reference 9 and 10. The emission factor units are lb of pollutant per ton of cement and cement supplement. Emission factors were developed from two typical truck mix loading operations. Based upon visual observations of every loading operation during the two test programs, the average capture efficiency during the testing was 71%.

References for Section 11.12

1. *Air Pollutant Emission Factors*, APTD-0923, U.S. Environmental Protection Agency, Research Triangle Park, NC, April 1970.
2. *Air Pollution Engineering Manual*, 2nd Edition, AP-40, U.S. Environmental Protection Agency, Research Triangle Park, NC, 1974. Out of Print.
3. Telephone and written communication between Edwin A. Pftzing, PEDCo Environmental, Inc., Cincinnati, OH, and Richards Morris and Richard Meininger, National Ready Mix Concrete Association, Silver Spring, MD, May 1984.
4. *Development Document for Effluent Limitations Guidelines and Standards of Performance, The Concrete Products Industries, Draft*, U.S. Environmental Protection Agency, Washington, DC, August 1975.
5. Portland Cement Association. (2001). Concrete Basics. Retrieved August 27, 2001 from the World Wide Web: <http://www.portcement.org/cb/>
6. *Technical Guidance for Control of Industrial Process Fugitive Particulate Emissions*, EPA-450/3-77-010, U.S. Environmental Protection Agency, Research Triangle Park, NC, March 1977.
7. *Fugitive Dust Assessment at Rock and Sand Facilities in the South Coast Air Basin*, Southern California Rock Products Association and Southern California Ready Mix Concrete Association, Santa Monica, CA, November 1979.
8. Telephone communication between T.R. Blackwood, Monsanto Research Corp., Dayton, OH, and John Zoller, PEDCo Environmental, Inc., Cincinnati, OH, October 18, 1976.
9. *Final Test Report for USEPA [sic] Test Program Conducted at Chaney Enterprises Cement Plant*, ETS, Inc., Roanoke, VA April 1994.
10. *Final Test Report for USEPA [sic] Test Program Conducted at Concrete Ready Mixed Corporation*, ETS, Inc., Roanoke, VA April 1994.
11. *Emission Test for Tiberi Engineering Company*, Alar Engineering Corporation, Burbank, IL, October, 1972.
12. *Stack Test "Confidential"* (Test obtained from State of Tennessee), Environmental Consultants, Oklahoma City, OK, February 1976.
13. *Source Sampling Report, Particulate Emissions from Cement Silo Loading*, Specialty Alloys Corporation, Gallaway, Tennessee, Reference number 24-00051-02, State of Tennessee, Department of Health and Environment, Division of Air Pollution Control, June 12, 1984.
14. Richards, J. and T. Brozell. "*Ready Mixed Concrete Emission Factors, Final Report*" Report to the Ready Mixed Concrete Research Foundation, Silver Spring, Maryland. August 2004.



<http://www.epa.gov/ttn/chief/ap42/>

Last updated on Monday, September 10th, 2007. *Date*

Technology Transfer Network Clearinghouse for Inventories & Emissions Factors

You are here: [EPA Home](#) [Technology Transfer Network](#) [Clearinghouse for Inventories & Emissions Factors](#) [Emissions Factors & Policy Applications Center](#) [Emissions Factors & AP 42](#)

Emissions Factors & AP 42

An **emissions factor** is a representative value that attempts to relate the quantity of a pollutant released to the atmosphere with an activity associated with the release of that pollutant. These factors are usually expressed as the weight of pollutant divided by a unit weight, volume, distance, or duration of the activity emitting the pollutant (e.g., kilograms of particulate emitted per megagram of coal burned). Such factors facilitate estimation of emissions from various sources of air pollution. In most cases, these factors are simply averages of all available data of acceptable quality, and are generally assumed to be representative of long-term averages for all facilities in the source category (i.e., a population average).

The general equation for emissions estimation is:

$$E = A \times EF \times (1 - ER/100)$$

where:

- E = emissions;
- A = activity rate;
- EF = emission factor, and
- ER = overall emission reduction efficiency, %

For information about emissions factors from highway vehicles and nonroad mobile sources, visit the **Office of Transportation and Air Quality** web site.

**AP 42, Fifth Edition
Compilation of Air Pollutant Emission Factors, Volume 1:
Stationary Point and Area Sources**

For current information on AP 42 updates and the activities of the Measurement Policy Group, you can subscribe to the CHIEF Listserv.

AP 42 FAQs [Answers to frequently asked questions about AP 42](#)

Drafts [Draft Sections Under Review](#)

AP 42 listing of supplements [Supplements A through F \(1996 - 2000\)](#)

and updates. [Updates 2001 to present](#)

[This information is available for historical purposes](#)

Older Editions of AP-42, Volume 1	<u>only. For the most recent emissions factors, supported by the EPA, please see the table of contents below.</u>
Procedures	The draft version of the document, <i>Detailed Procedures For Preparing Emissions Factors</i> , is now available for review and comment. July 3, 2006. (PDF 1.5M) <i>Procedures for Preparing Emission Factor Documents</i> -- Describes procedures for developing and reporting emission factors in EPA publications -- November 1997 (PDF 477K)
Contents	<u>Cover page, detailed Table of Contents, Publications in Series, Insertion Instructions, and Key Word Index</u> (PDF 128K). This is current through Fifth Edition, Supplement C of AP 42. For sections and chapters added after November 1997, see the chapter web pages below.

AP 42, Volume I, Fifth Edition

Introduction	<u>Introduction to AP 42, Volume I, Fifth Edition</u> - January 1995 (PDF 40K)
Chapter 1	<u>External Combustion Sources</u>
Chapter 2	<u>Solid Waste Disposal</u>
Chapter 3	<u>Stationary Internal Combustion Sources</u>
Chapter 4	<u>Evaporation Loss Sources</u>
Chapter 5	<u>Petroleum Industry</u>
Chapter 6	<u>Organic Chemical Process Industry</u>
Chapter 7	<u>Liquid Storage Tanks</u>
Chapter 8	<u>Inorganic Chemical Industry</u>
Chapter 9	<u>Food and Agricultural Industries</u>
Chapter 10	<u>Wood Products Industry</u>
Chapter 11	<u>Mineral Products Industry</u>
Chapter 12	<u>Metallurgical Industry</u>
Chapter 13	<u>Miscellaneous Sources</u>
Chapter 14	<u>Greenhouse Gas Biogenic Sources</u>
Chapter 15	<u>Ordinance Detonation</u>
Appendix A	<u>Miscellaneous Data & Conversion Factors</u> -- September 1985 (PDF 103K)

Link
↳

- Appendix B.1 **Particle Size Distribution Data and Sized Emission Factors for Selected Sources** -- October 1986 (PDF 2M)
- Appendix B.2 **Generalized Particle Size Distributions** -- September 1996 (PDF 137K)
- Appendix C.1 **Procedures for Sampling Surface/Bulk Dust Loading** -- July 1993 (PDF 65K)
- Appendix C.2 **Procedures for Laboratory Analysis of Surface/Bulk Dust Loading Samples** -- July 1993 (PDF 42K)

Draft Sections Under Review

Chapter & Section	Description	Comments Requested by:
Section 12.2	<u>Coke Production</u>	September 14, 2007
Section 12.5.1	<u>Steel Mini Mills</u>	Extended to April 16, 2007
Chapter 15 - Ordnance Detonation	<u>Sections 15.2, 15.5, 15.8, and 15.9</u>	November 13, 2007

AP 42 Emissions Factors by Chapter