

**Utilization of Lightweight Materials Made
from
Coal Gasification Slags**

Praxis Engineers, Inc.
Milpitas, California 95035

Funding Sources: METC, EPRI, and ICCI

Project Objectives

- ▶ Develop and demonstrate the technology for producing slag-based lightweight aggregates (SLA)
- ▶ Produce 10 tons of SLA Products with different unit weights from two slags
- ▶ Collect operational and emissions data from pilot-scale operations
- ▶ Laboratory- and commercial-scale evaluation of SLA with conventional lightweight and ultra-lightweight aggregates (LWA and ULWA)

Project Objectives (contd)

Characterize SLA products for leachability and conduct applications testing

Evaluate recovered char for recycle to the gasifier, and for use as a fuel during slag expansion or in the boiler

Conduct preliminary economics of SLA production

Slag, LWA, ULWA, & SLA: Definitions


- ▶ Slag is a solid residue by-product of coal gasification combined-cycle process
- ▶ Gasification slag is vitrified ash containing some unconverted carbon
- ▶ Conventional LWA:
 - Produced by pyroprocessing clays and shales at 2100°F
 - Unit weight is 50 lb/ft³
 - Used to make lightweight structural concrete, blocks, and roof tilesMarket price is \$20-30/ton

Definitions (contd)


- ▶ Conventional ULWA:
 - Produced by pyroprocessing perlite ores at 2000°F
 - Unit weight is 4-12 lb/ft³
 - Used for horticultural and insulation applications
 - Market price is over \$200/ton

- ▶ Slag can be expanded under controlled conditions to produce lightweight materials, termed slag-based LWA or SLA:
 - Produced by pyroprocessing at 1600-1800°F
 - Unit weight is 12-50 lb/ft³
 - Blendable with existing raw materials
 - Can be substituted for all or part of the ingredients of some LWA and ULWA applications

MUFFLE BURN TESTS - EXTRUDED MIXTURES

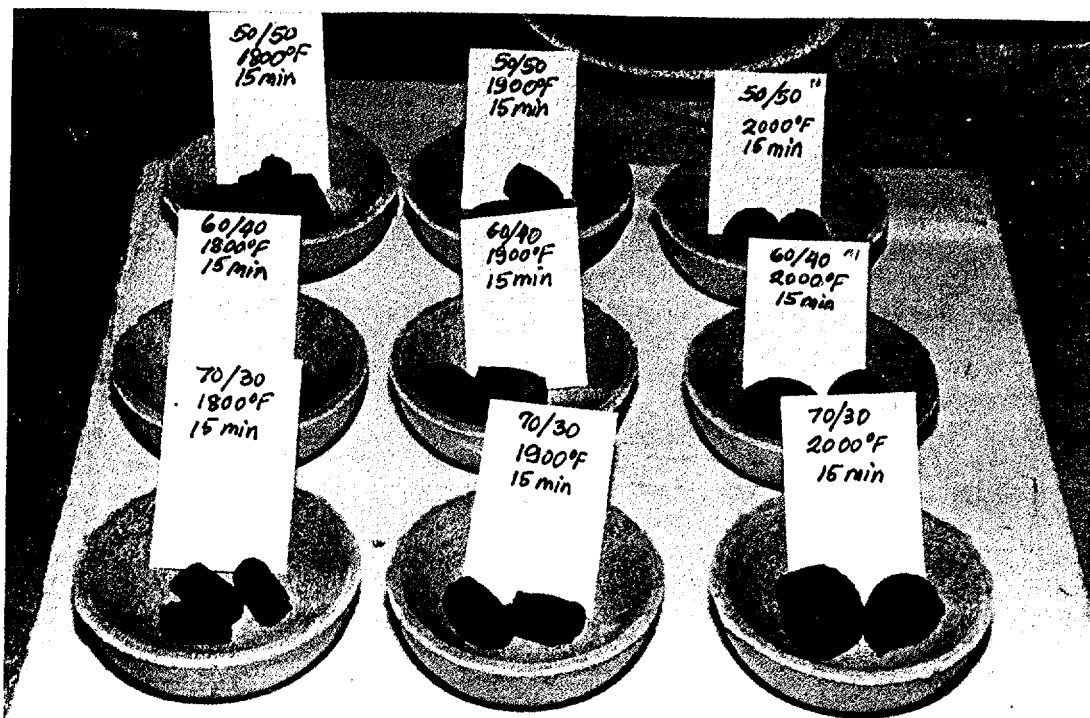

BURN TESTS ALL THREE BLENDS

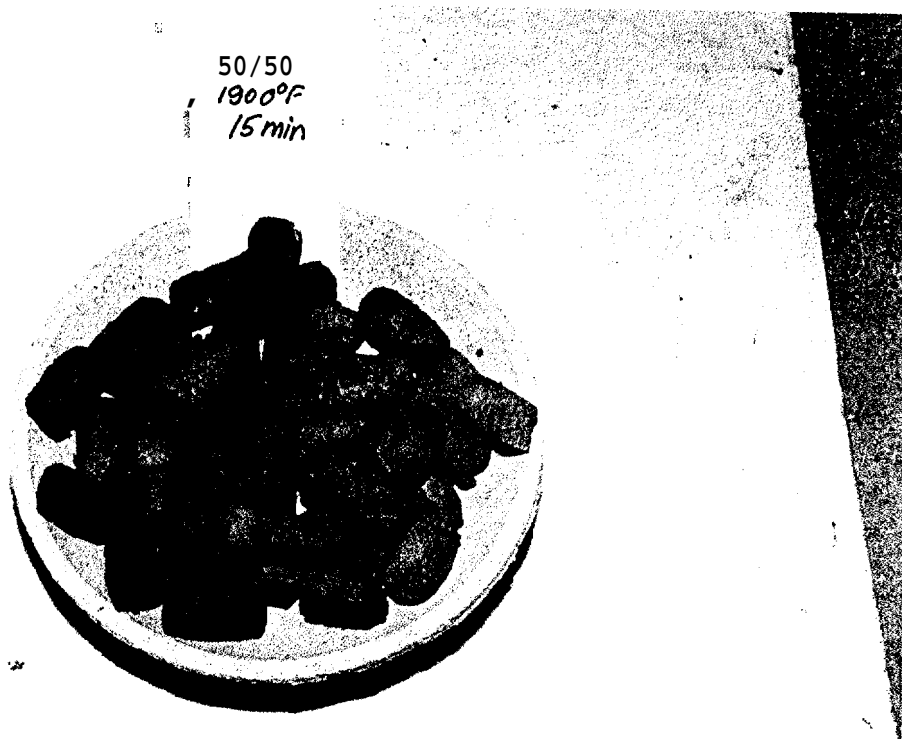


50/50 MIX-COMplete CUP BURN - 1900°F


6" Diameter Bench-Scale Fluid Bed Reactor

Specifications

Bed Height:	3 ft
Feed Height (Above Grid):	2 ft
Inside Diameter:	0.5 ft
Temperature:	+1420°C
Fuel:	Gas/Oil

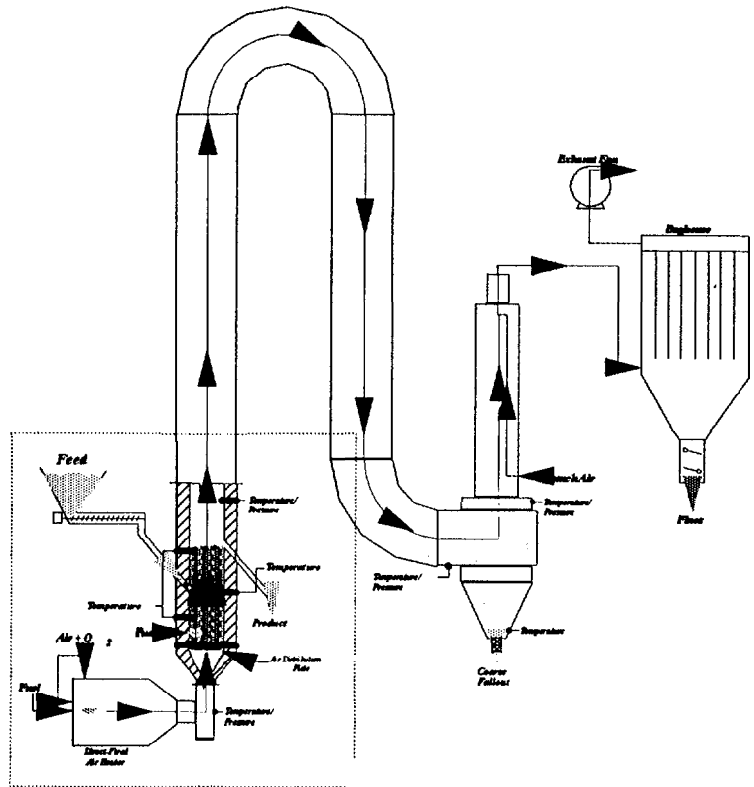


Reactor Section Detail

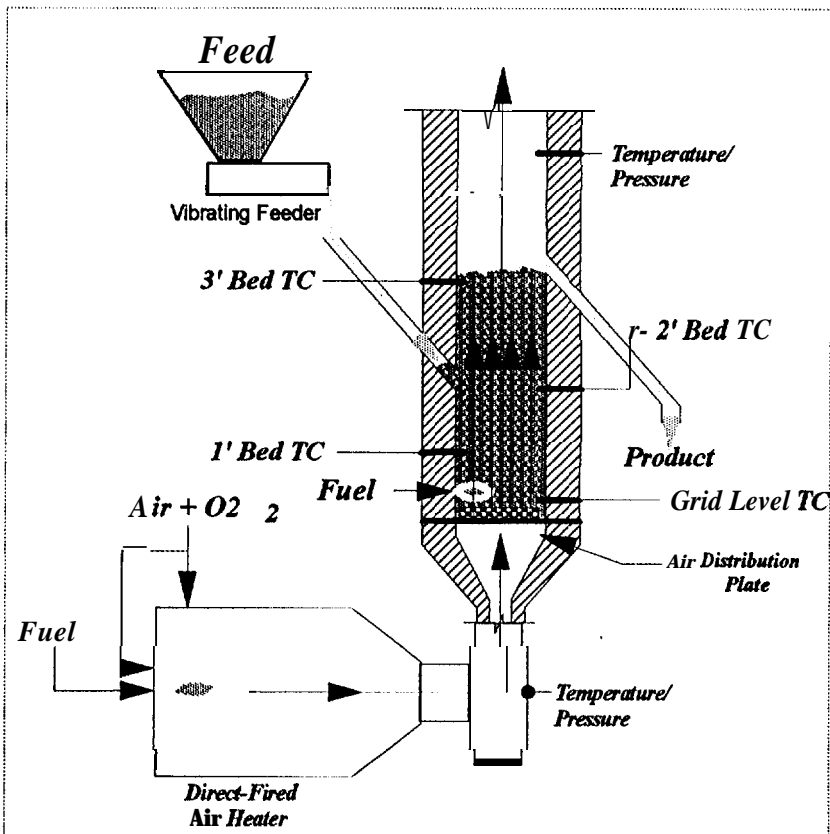


Material Flow

Gas Flow


3'x30' Rotary Kiln Schematic

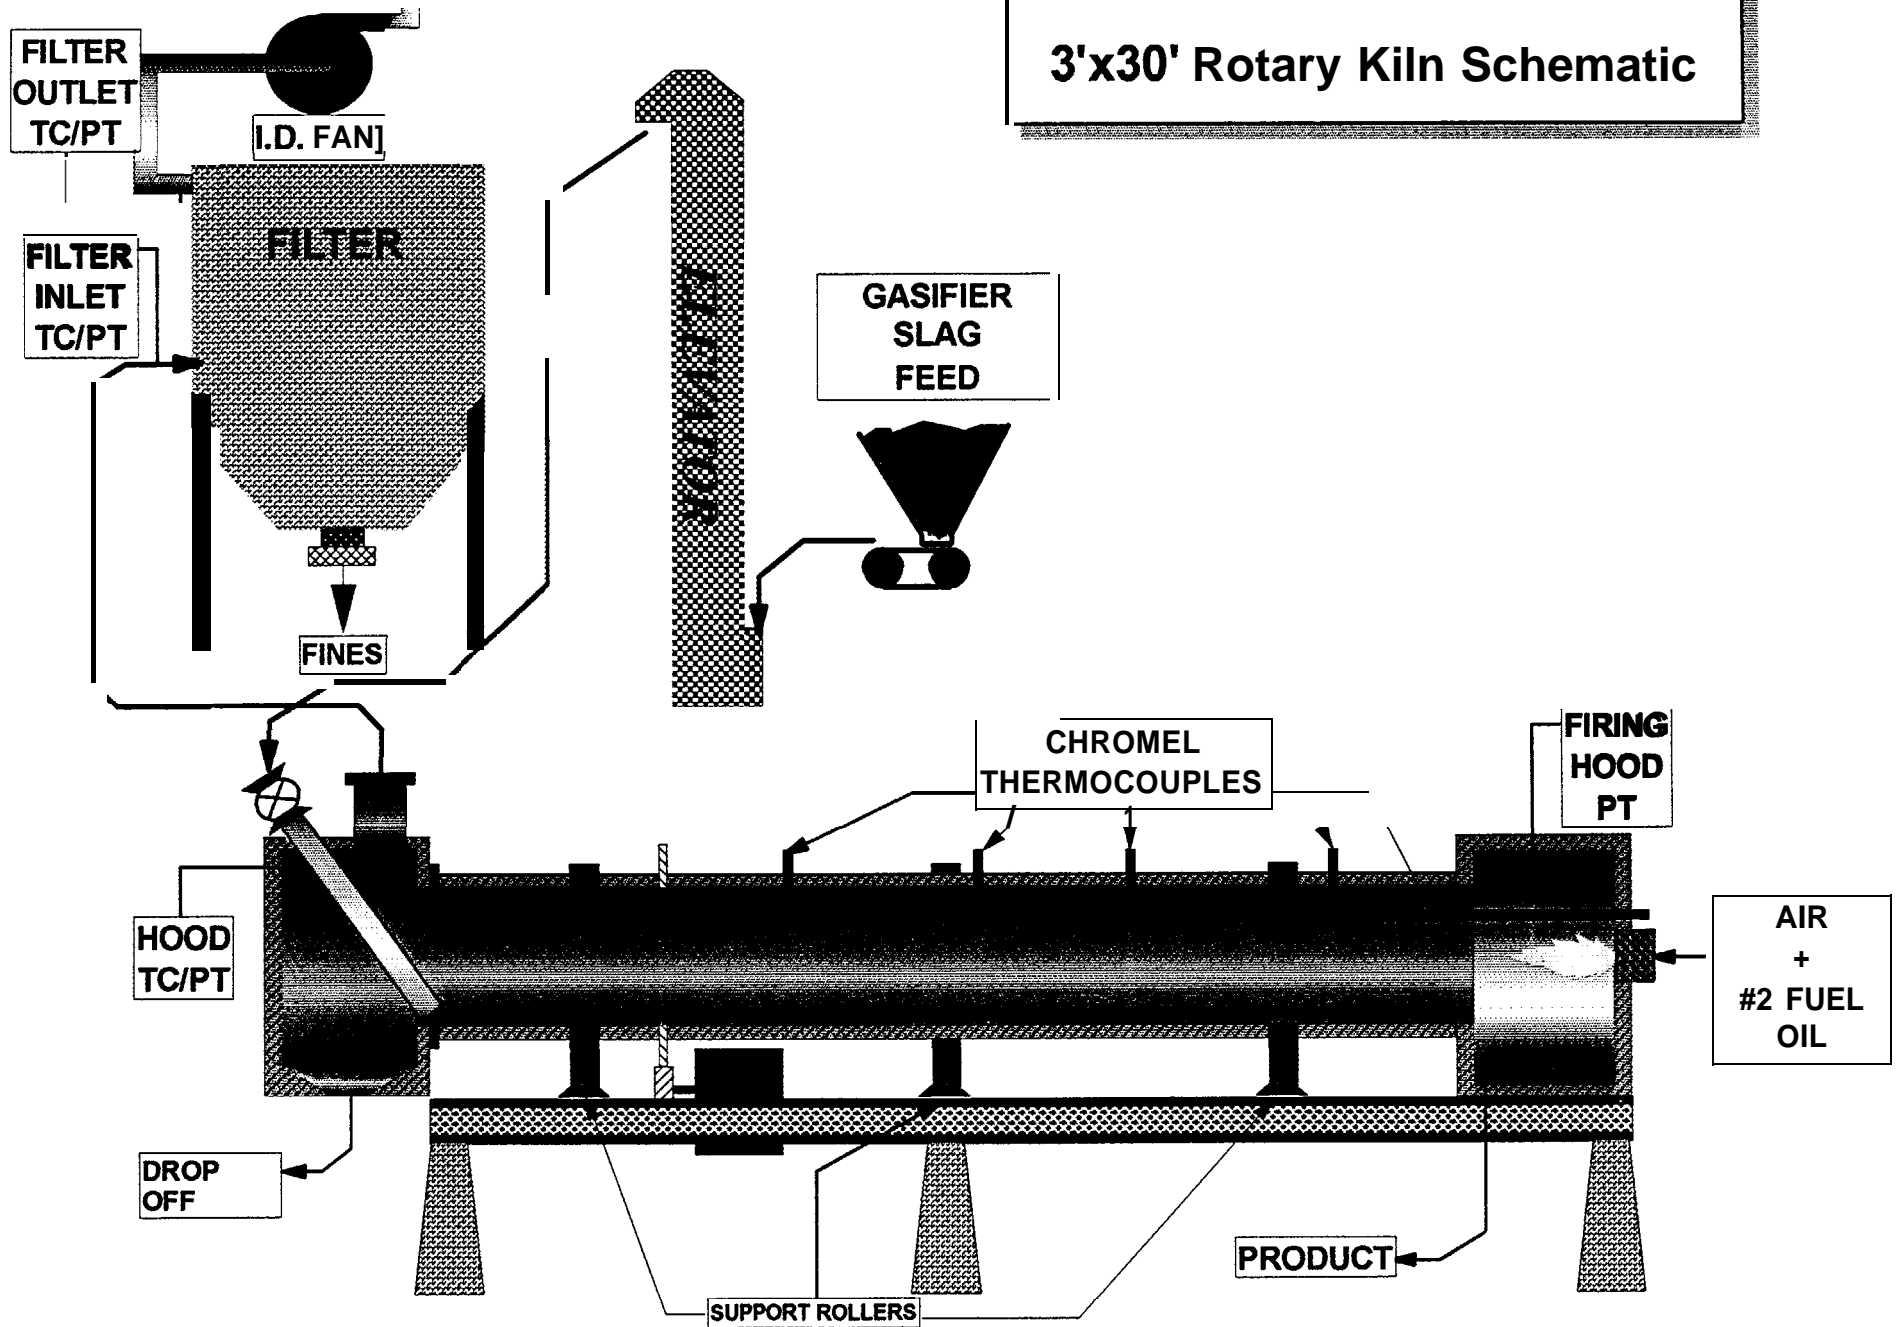

Product Density vs. Fluid Bed Temperature

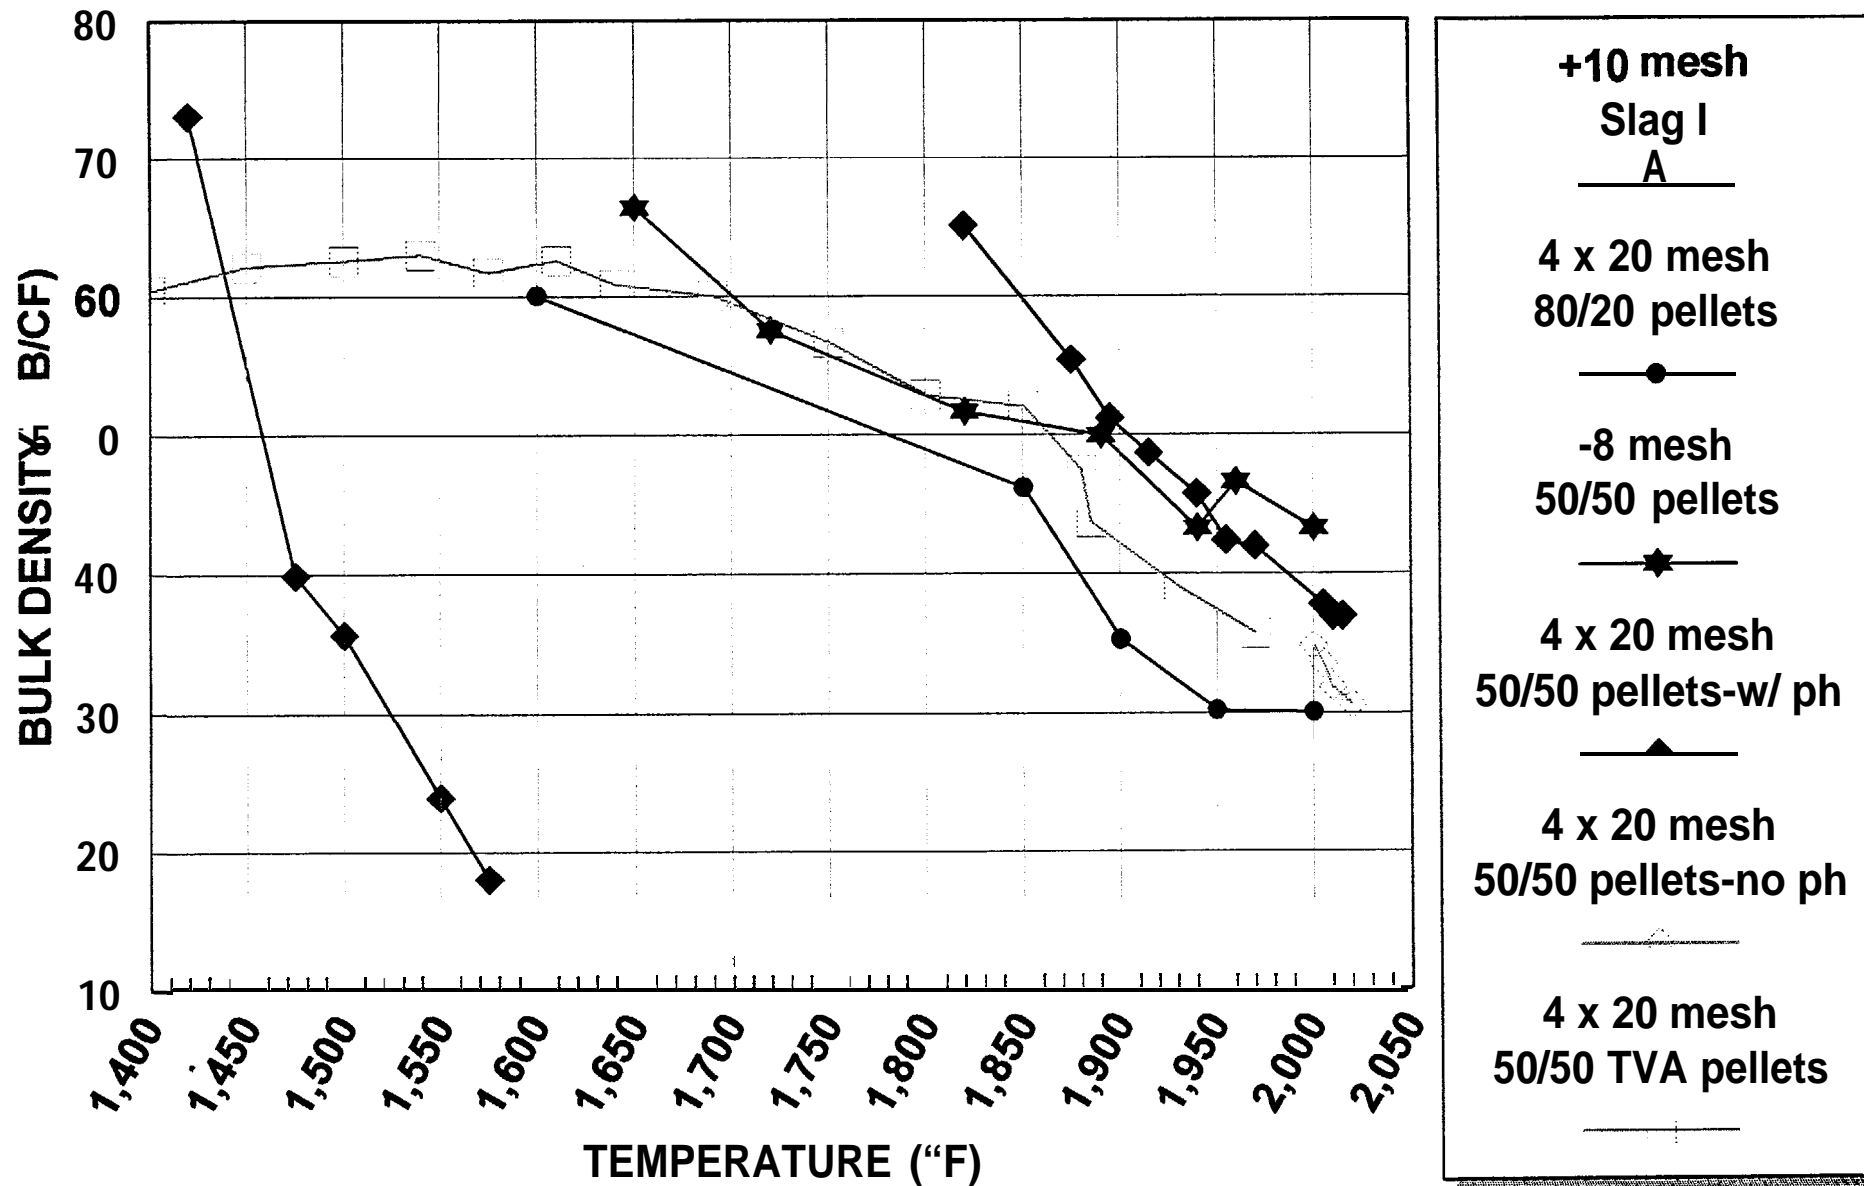


Hot Zone Temperature vs. Product Density Slag I Rotary Kiln Processing

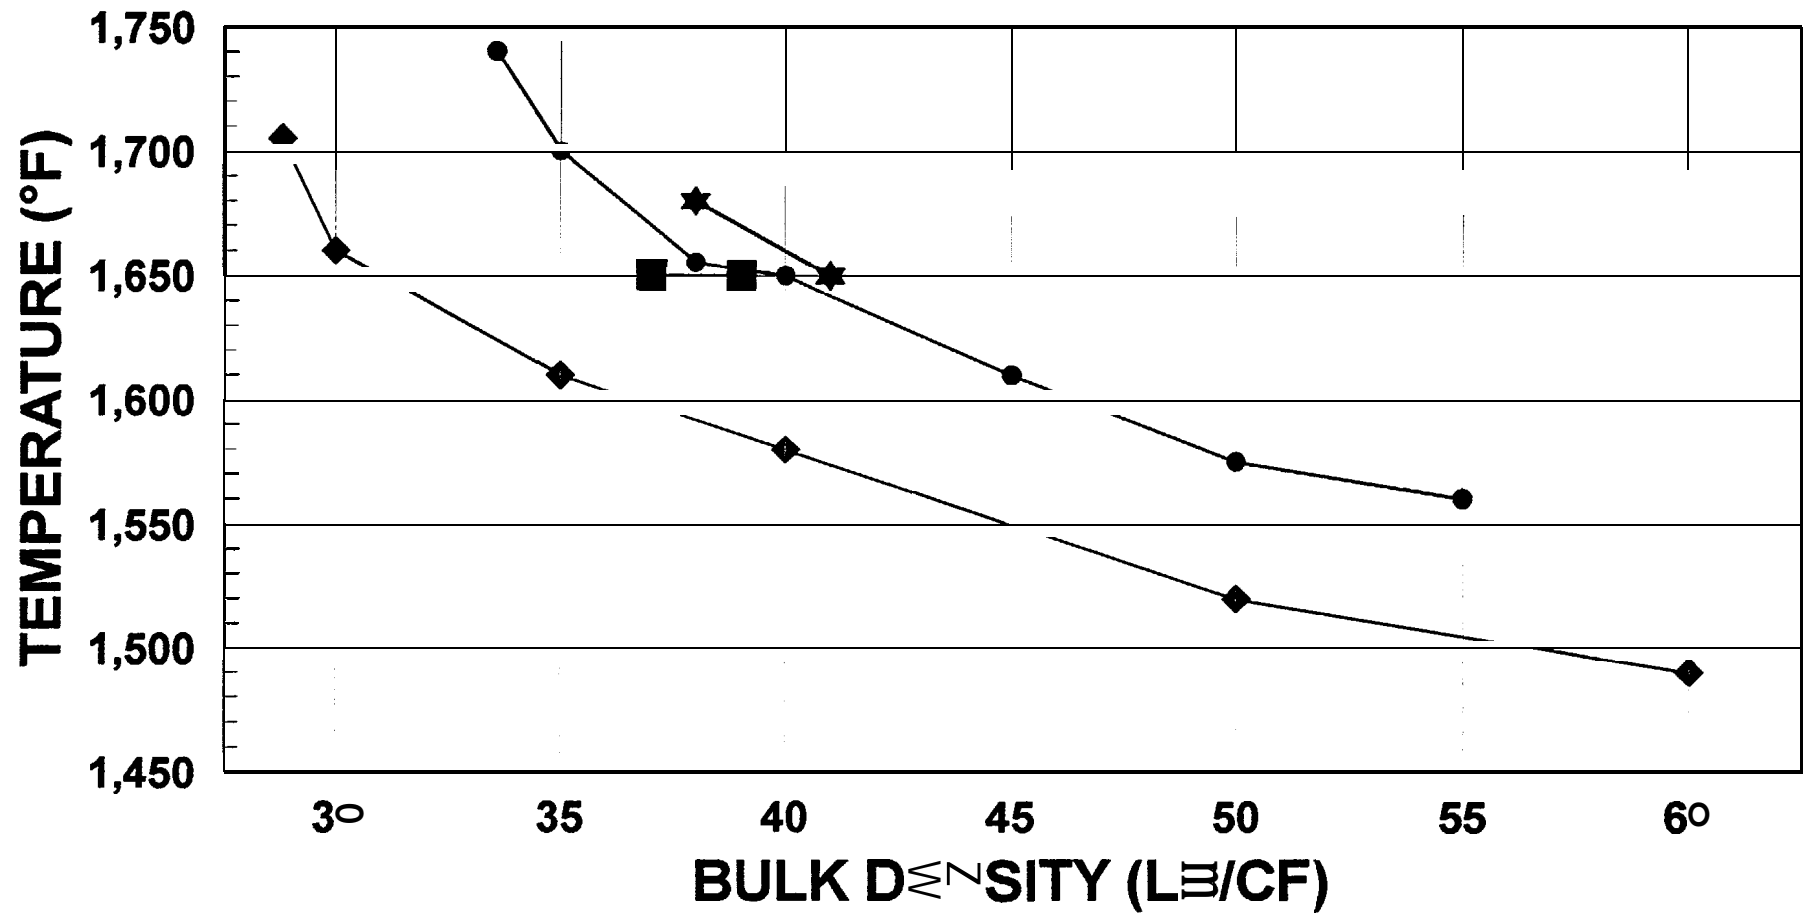



+10 MESH 10x50 MESH 50/50 BLEND DROP OFF



Stack Gas Analysis from Rotary Kiln Testing 14 November 1995

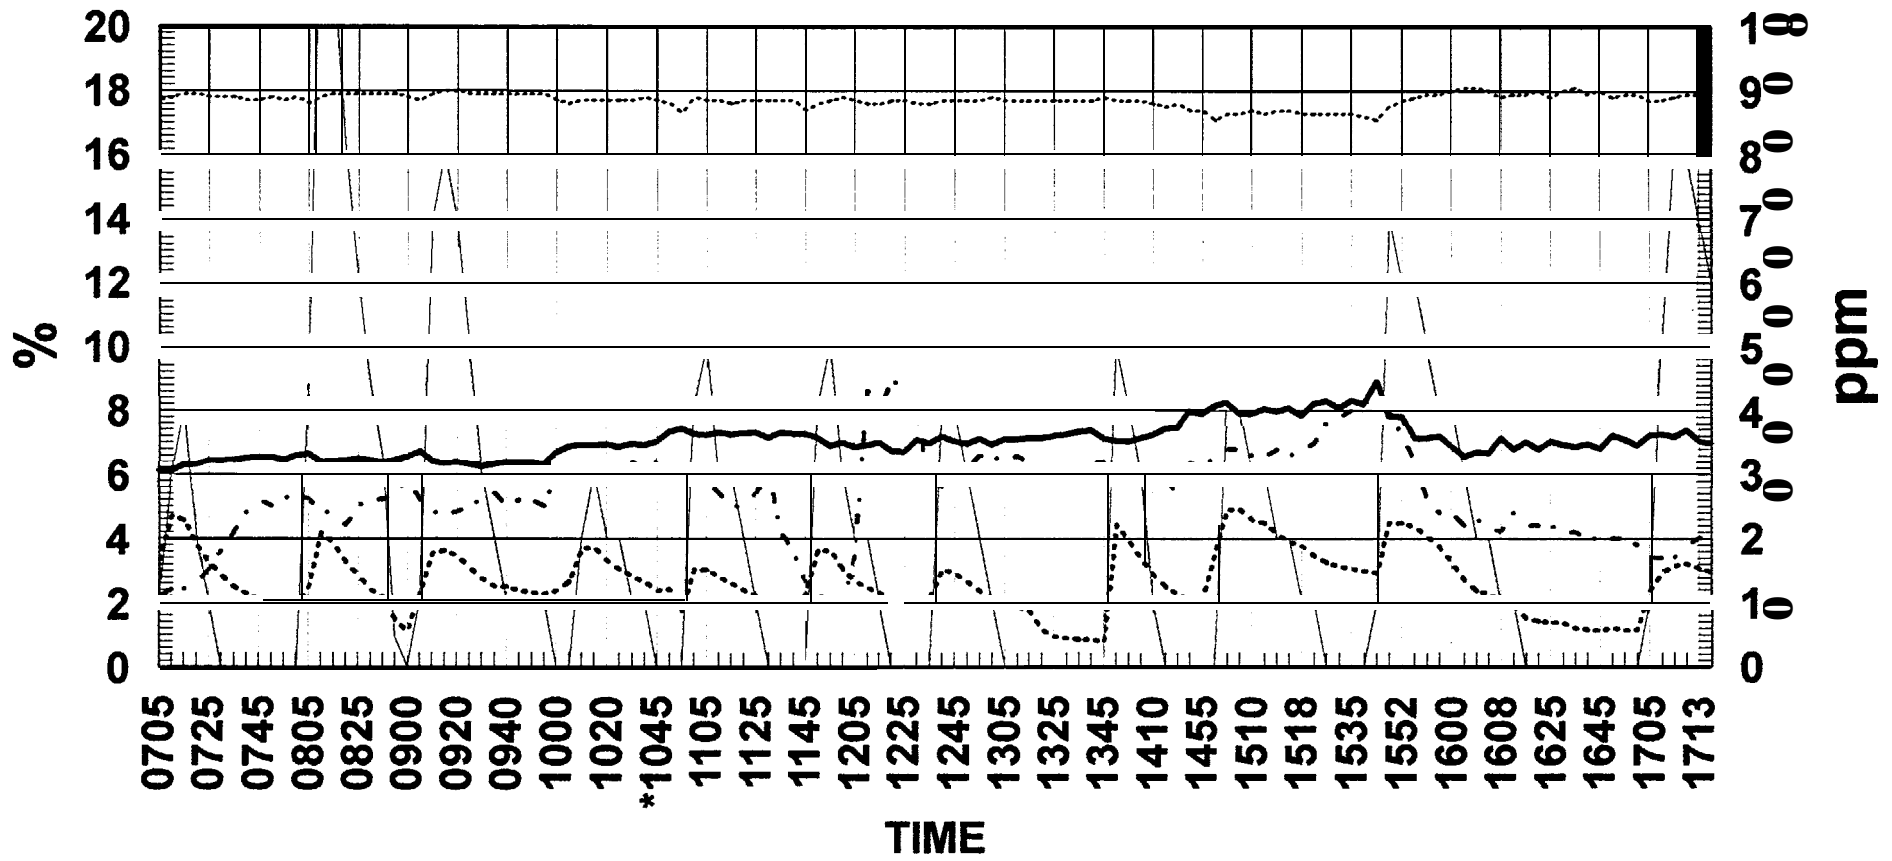


NOx	SO2	O2	CO	CO2
ppm	ppm	%	ppm	%
_____	-----	_____

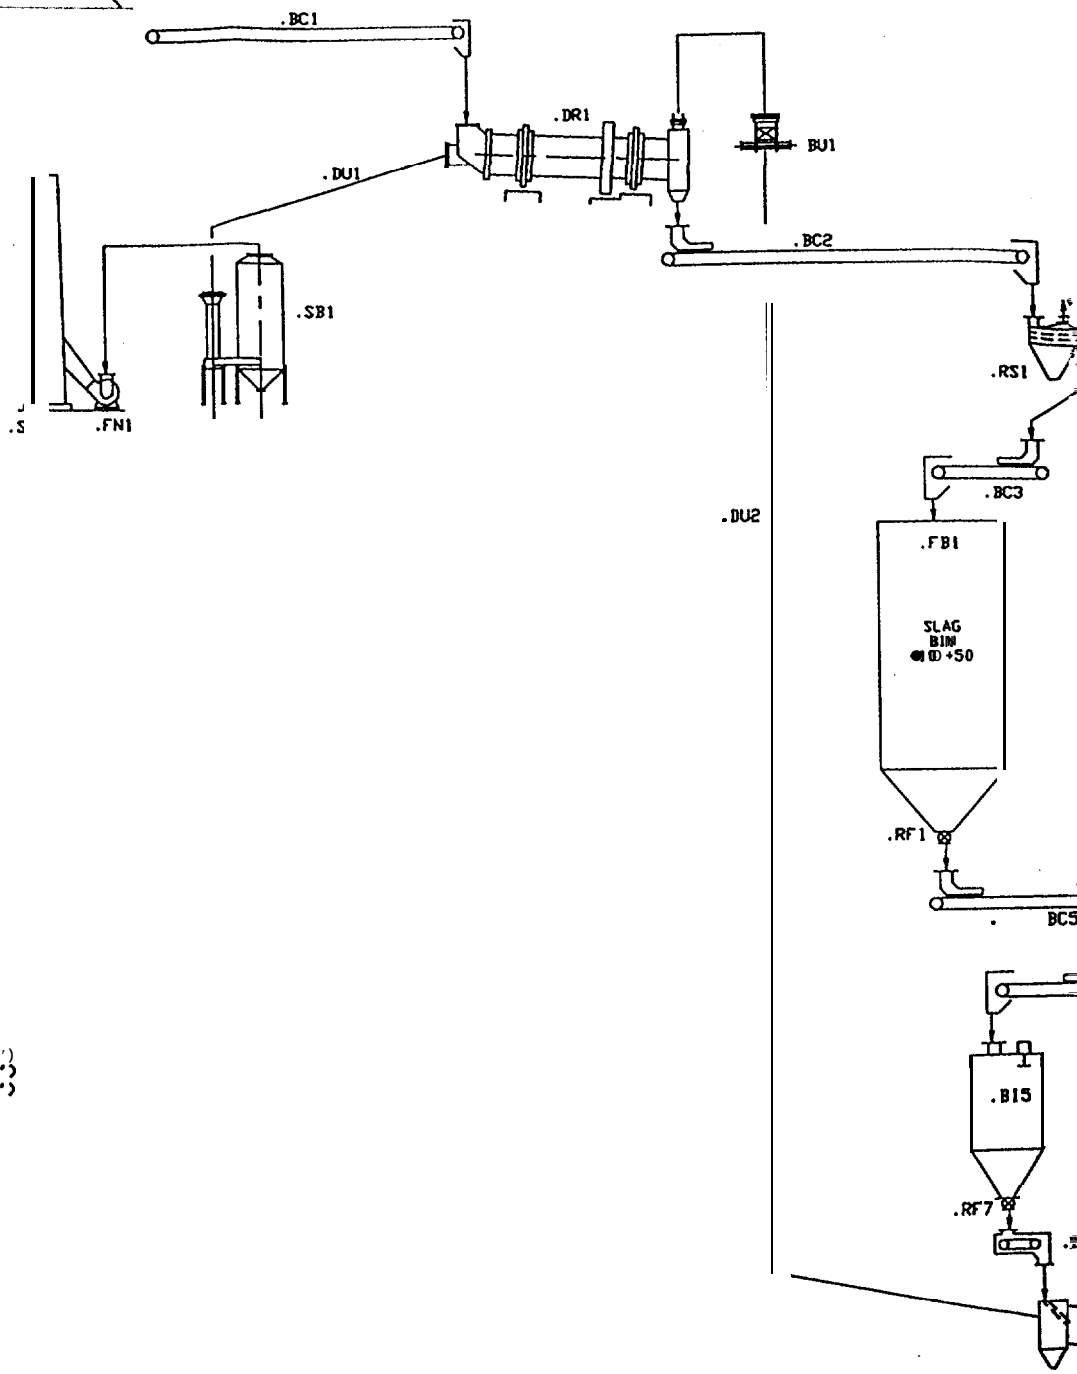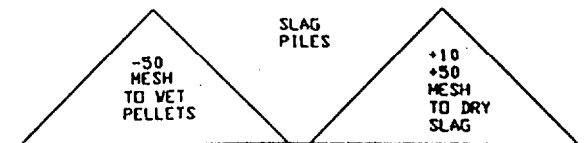

EQUIPMENT LIST

- .BC1 BELT CONVEYOR
- .BC2 BELT CONVEYOR
- .BC3 BELT CONVEYOR
- .BC4 BELT CONVEYOR
- .BC5 BELT CONVEYOR
- .BC6 BELT CONVEYOR
- .BC7 BELT CONVEYOR
- .BE1 BUCKET ELEVATOR
- .BF1 DUST COLLECTOR
- .B11 PRODUCT BIN
- .B12 PRODUCT BIN
- .B13 PRODUCT BIN
- .B14 PRODUCT BIN
- .B15 PRODUCT BIN
- .BU1 BURNER
- .BU2 BURNER
- .BV1 BELT SCALE
- .BV2 BELT SCALE
- .CC1 AGGREGATE COOLER
- .CR1 CONE CRUSHER
- .DR1 DRYER (5' X 55')
- .DU1 DUCTING
- .DU2 DUCTING
- .DU3 DUCTING
- .DU4 DUCTING
- .DV1 DIVERTER VALVE
- .DV2 DIVERTER VALVE
- .DV3 DIVERTER VALVE
- .DV4 DIVERTER VALVE
- .EX1 EXTRUDER
- .FB1 SLAG BIN +10 TO +50 (30'DIA. X 60')
- .FB2 SLAG BIN -50 (20'DIA. X 30')
- .FB3 CLAY BIN (20'DIA. X 30')
- .FN1 FAN
- .FN2 FAN
- .FN3 FAN
- .FN4 FAN
- .FN5 FAN
- .KL1 KILN (9' X 120')
- .PU1 PUG MILL
- .RF1 ROTARY FEEDER
- .RF2 ROTARY FEEDER
- .RF3 ROTARY FEEDER
- .RF4 ROTARY FEEDER
- .RF5 ROTARY FEEDER
- .RF6 ROTARY FEEDER
- .RF7 ROTARY FEEDER
- .RF8 ROTARY FEEDER
- .RS1 ROTARY SCREEN
- .SB1 SCRUBBER
- .SC1 SCREW CONVEYOR
- .SF1 CLAY FEEDER
- .SK1 STACK
- .SK2 STACK

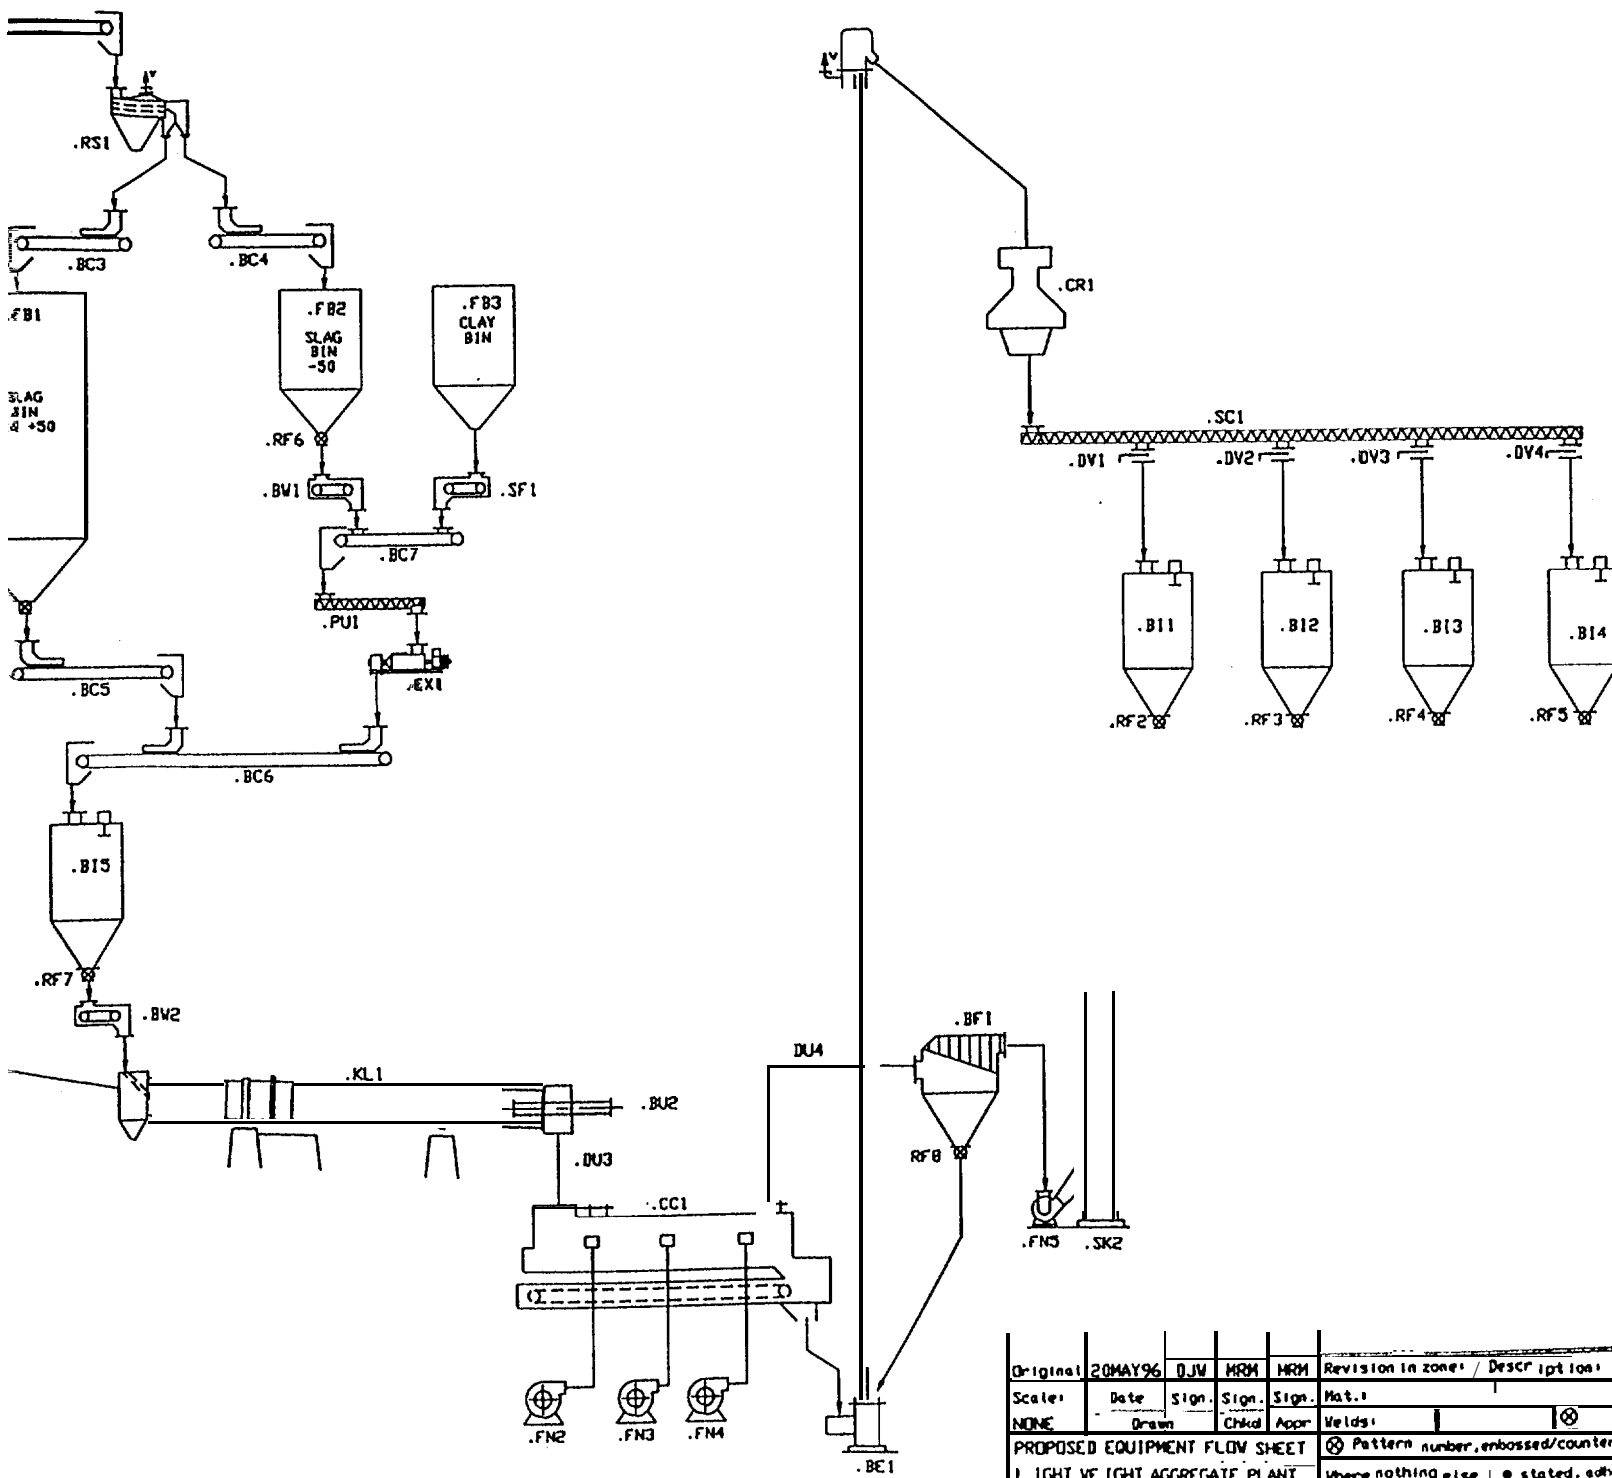

Original	20MAY96	DJW	HRM	HRM	Revision in zone / Description
Scale	Date	Sign.	Sign.	Sign.	Mat.
NONE	Drawn	Checked	Appr.	Welds	
PROPOSED EQUIPMENT FLOW SHEET					⊗ Pattern number, embossed/counter
LIGHT WEIGHT AGGREGATE PLANT					where nothing else is stated, refer to general instructions No. 52053
235 TPD WET PELETS					
200 TPD DRY SLAG					PC-143
FULLER PROPOSAL					Drawing Number
					1.725762

SLA Products Made at Pilot Scale

Slag/Size/ Mix Type	Direct- Fired Kiln lb/ft³	Fluidized Bed Expander lb/ft³
Slag I: +10M	28-67	24-73
Char injection	--	16-26
Slag I: 10x 50M	34-58	--
Slag I: +50M	38	16-58
Extruded Slag I/Clay		
80/20	27-62	--
50/50	21-42	--
0/100	18-41	--
Slag I/Clay Granules		
80/20 4 x 20M	.-	30-60
80/20 4 x 30M	--	37-42
50/50 4 x 20M	--	31-65
50/50 -8M	--	43-66
Slag II: +10M	22-82	--
Slag 11/Clay Granules		
50/50 4 x 20M	--	33-63

Production Costs of SLA vs. LWA and ULWA (\$/Ton)

Cost Item	Shale/Clay LWA ⁽¹⁾	Perlite ULWA ⁽²⁾	SLA ⁽³⁾
System	Rotary Kiln	Vert.Shaft Furnace	Rotary Kiln
Fuel	011	Natl gas	Coal/char
Mining/prep	6.00	40.00	-
Transport	0.50	40.00	
Clay binder			1.45
Labor	6.23	12.00	6.25
Fuel	5.09	8.00	1.64
Power	1.37	4.50	1.35
M&S	1.85	3.00	1.48
Other	1.11	2.00	1.10
Overhead	2.24	10.00	-
Depreciate	5.71	4.75	4.28
Interest	excluded	excluded	6.85
Total	30.10	124.25	24.40

Estimated by(1) Fuller Co., (2) Silbrico, (3) Praxis/Fuller

Conclusions: Slag Processing

- Slag I was expanded to unit weights of 30-50 lb/ft³ and Slag II to 20-50 lb/ft³ by means of temperature control. Attempts to lower these further resulted in fusion which is a function of slag chemistry.
- The entire 1/4" x 50M fraction can be processed in the kiln as a single feed.
- Minus 50M fines must be extruded prior to kiln processing. Extruded pellets using 20-50% expansive clay binder yielded product unit weights of 27-33 lb/ft³ at 1800 -1900°F.

Conclusions: Char Utilization

- ▶ Char can be recovered from slag easily and used as a fuel
- ▶ A char product containing 45-54% ash was upgraded successfully to 70% carbon
- ▶ Char can be utilized as a substitute for 50% of the fuel in a rotary kiln and 80% of the fuel in a fluidized bed system

Conclusions: SLA Economics

- ▶ Expansion temperature for slag is 300-400 °F lower than that typically required for expansible clays and shales and represents significant energy savings
- ▶ SLA production costs from a large (440 t/d) facility were estimated at \$24.40/ton using rotary kiln and \$21.87/ton using fluidized bed vs. \$30.10/ton for conventional LWA plant
- ▶ Preliminary analyses also indicate that small SLA plants can be economically attractive if the avoided costs of slag disposal (\$10-\$20/ton) are factored in.

Planned Product Evaluation (Phase II)

Commercial-scale testing of SLA as a substitute for LWA and ULWA in the following applications:

- ▶ Structural concrete using 3/4" coarse and 3/8" LWA
- ▶ Lightweight blocks (2-3 blends)
- ▶ Insulating concrete (ASTM C 332 Group II concrete, 45-90 lb/ft³)
- ▶ Lightweight roof tile aggregate
- ▶ Loose fill insulation (ASTM C 549)
- ▶ Horticultural applications