

**Paper Number:**

DOE/ER/81964-97/C0732

**Title:**

Decomposition of Ammonia in IGCC Fuel Gas Streams

**Authors:**

S.A. Qadar

Q.A. Qadar

L.J. Muzio

**Contractor:**

Energy and Environmental Technology Corporation

11609 Treviso Way

Rancho Cucamonga, CA 91701

**Contract Number:**

DE-FG03-95ER81964

**Conference:**

Advanced Coal-Fired Power Systems '96 Review Meeting

**Conference Location:**

Morgantown, West Virginia

**Conference Dates:**

July 16-18, 1996

**Conference Sponsor:**

U.S. DOE, Morgantown Energy Technology Center

## **Disclaimer**

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

# Decomposition of Ammonia in IGCC Fuel Gas Streams

Shaik A. Qader (909) 466-6266  
Qusro A. Qader (909) 466-6266  
Energy and Environmental Technology Corporation  
11609 Treviso Way  
Rancho Cucamonga, California 91701

Lawrence J. Muzio (714) 859-4466  
Fossil Energy Research Corporation  
22342C South Pointe  
Laguna Hills, California 92653

## Introduction

Integrated Coal Gasification Combined Cycle (IGCC) technology has the potential to emerge as an efficient and environmentally clean technology for generation of power from coal. Development of processes to clean coal gas at high temperatures prior to its combustion in gas turbines improves efficiency and economics of IGCC technology. Particulate,  $\text{NH}_3$ , and  $\text{H}_2\text{S}$  comprise the main impurities of coal gas.

During combustion,  $\text{NH}_3$  present in coal gas is oxidized to  $\text{NO}_x$  which necessitates  $\text{NO}_x$  removal from gas turbine exhaust using the expensive Selective Catalytic Reduction (SCR) process (Refs. 1-3). Decomposition of  $\text{NH}_3$  present in coal gas at high temperatures prior to combustion results in higher IGCC efficiency and lower costs.

Ammonia can be removed from coal gas by scrubbing the gas with water or  $\text{H}_2\text{SO}_4$  at a low temperature of 1500F (Ref. 4). Ammonia present in the flue gas of a large incinerator operating in Switzerland was reduced by injection of methanol at high temperatures in the range 1300-20000F (Ref. 5). Research on catalytic decomposition of  $\text{NH}_3$  at high temperatures is also being carried out at Research Triangle Institute under DOE sponsorship (Ref. 6).


The Energy and Environmental Technology Corporation (EETC) is developing processes to decompose  $\text{NH}_3$  at high temperatures, Bench-scale tubular flow reactors operating isothermally have been used to test two new approaches,

## Objective

The main objective of the research work is to develop technically feasible and potentially low cost processes to decompose  $\text{NH}_3$  present in coal gases at high temperatures upstream of the gas turbine. Specific objectives of the work include development of  $\text{NH}_3$  decomposition processes applicable to both air-blown and oxygen-blown coal gasification-based combined cycle power plants,

## Technical Approach

Ammonia decomposition tests were carried out in a bench-scale tubular flow reactor shown in Figure 1. The flow system includes feed gas supply with flow control and pressure regulation, preheater and reactor, heaters, monitoring and control of system temperature and pressure, and feed and product analysis instrumentation. Non-catalytic  $\text{NH}_3$  decomposition tests were carried out in both Alloy RA-330 and quartz reactors. Catalytic tests were conducted only in the quartz reactor.

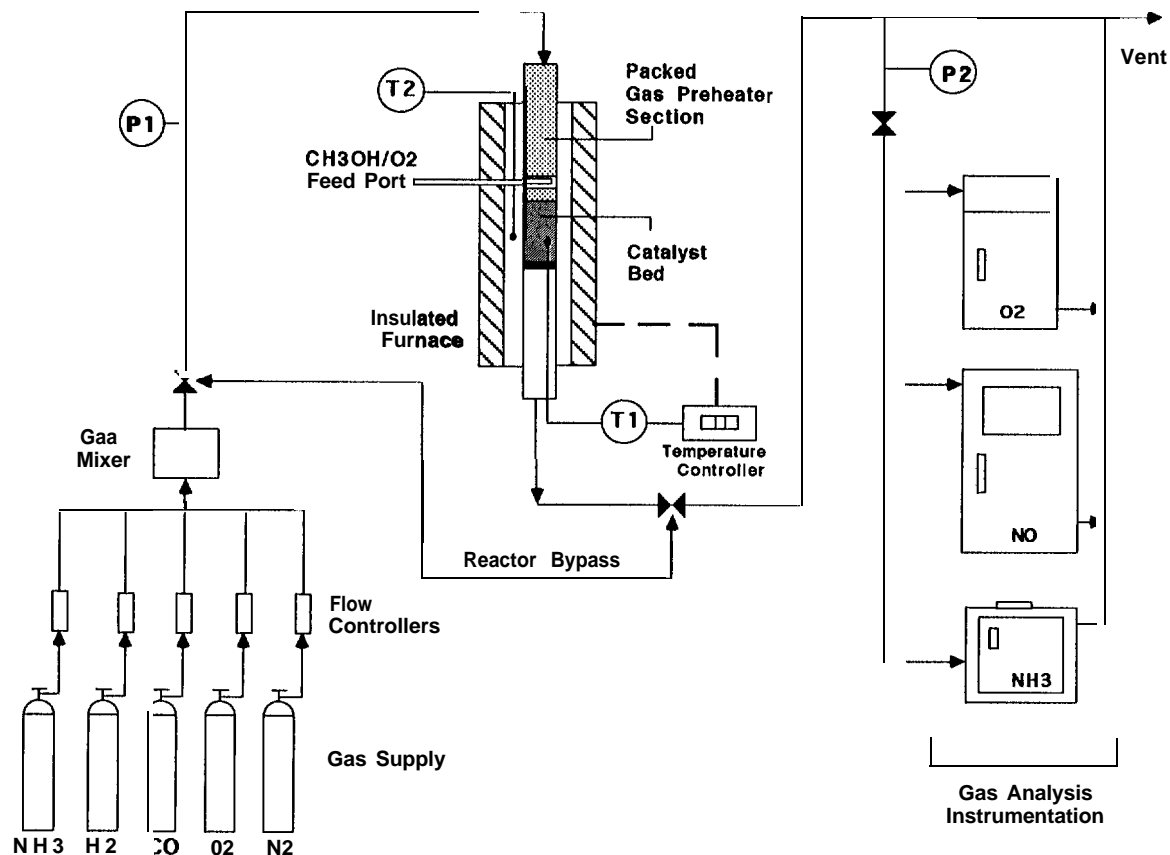

**Figure 1. Schematic of Bench-Scale Flow System**

Alloy RA-330 and quartz reactors of 0.25 in. -0.35 in. I.D. and 24 in. -36 in. length were used. The alloy and quartz reactors employed for non-catalytic  $\text{NH}_3$  decomposition tests were packed with alloy and quartz packing, respectively, having an average diameter of 3 mm. For the catalytic tests, the quartz reactor was packed with alumino-silicate catalyst particles of 3-4 mm diameter.

Tests were carried out in three temperature ranges: 800- 10000F, 1200- 13000F, 1600"- 18000F. The non-catalytic tests were performed in the two higher temperature ranges, and the catalytic tests were carried out in the lower temperature range. Ammonia decomposition tests were also carried out in the presence of H<sub>2</sub> and CO. Oxygen was used in the catalytic decomposition tests. Tests were designed to obtain data applicable to air-blown as well as oxygen-blown coal gasification-based IGCC systems. Gas analyses were done by standard methods.

### Project Description

Two processes have been developed for decomposition of ammonia present in coal gases. In the first process, NH<sub>3</sub> undergoes decomposition on the surface of Alloy RA-330 in the temperature ranges of 1200- 13000F and 1500- 16000F. In the second process, NH<sub>3</sub> undergoes decomposition on the surface of an aluminosilicate catalyst in the temperature range of 800- 10000F.

### RA-330 Promoted Decomposition (RAPD) Process

Figure 2 shows the basic RAPD process concept. In this concept, coal gas containing NH<sub>3</sub> enters a reactor packed with RA-330 honeycombs in the temperature ranges of 1200- 13000F and 1500- 16000F. Ammonia is decomposed on the surface of RA-330 honeycomb. Some NH<sub>3</sub> may decompose in the gas phase. The technical feasibility of the concept was established by tests performed in the flow system using a RA-330 tubular reactor packed with RA-330 packing of 3-4 mm diameter pieces. The packing was used to provide surface for NH<sub>3</sub> decomposition, Tests were carried out in the presence and absence of methanol.

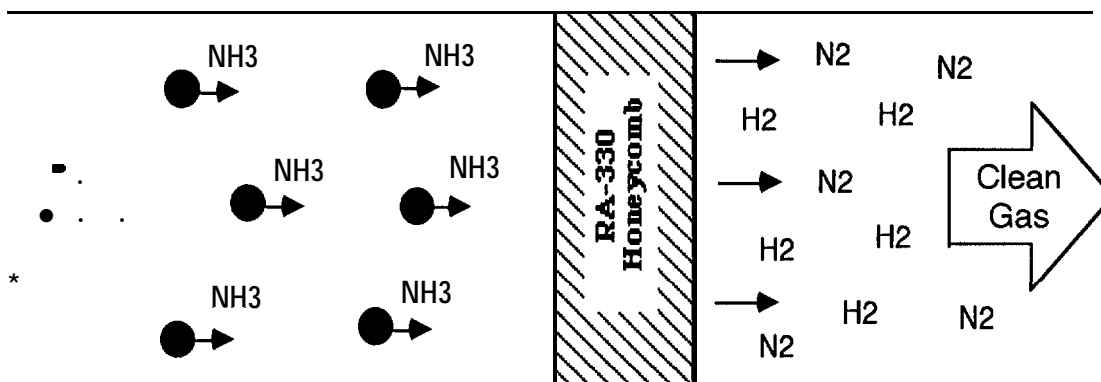


Figure 2. Basic RAPD Process Concept

Table 1 contains data which were obtained with methanol injection in the RA-330 reactor. The data show that total NH<sub>3</sub> conversion increases from 95% at 10000F to greater than 99% at 13000F and above. However, 76% and 65% of the NH<sub>3</sub> was converted to amine as an intermediate product at 10000 and 12000F respectively. But at 13000F and above, all the NH<sub>3</sub> was ultimately decomposed to N<sub>2</sub> and H<sub>2</sub>. If any amine was formed as an intermediate product, it may have decomposed at the higher temperatures. The data of Table 1 led to the conclusion that most of the NH<sub>3</sub> is converted to amine at temperatures in the range 1000- 12000F. At temperatures of 13000F and higher, NH<sub>3</sub> and any possible amine undergoes decomposition to nearly 1000/O.

**Table 1: Effect of Temperature on Ammonia Decomposition in RA-330 Reactor**

**CH<sub>3</sub>OH/NH<sub>3</sub> moles = 1.0**  
**Residence Time = 0.6- 0.8 sec.**

<b>Temperature (°)F</b>	<b>Total NH<sub>3</sub> Conversion (%)</b>	<b>NH<sub>3</sub> Conversion to Amine (%)</b>
1000	95	76
1200	97	65
1300	>99	Trace
1600	>99	--
1800	>99	--

Table 2 contains data which were obtained with methanol injection in the quartz reactor. The total NH<sub>3</sub> conversions obtained at 1300 and 16000F are lower than the corresponding conversions obtained in the RA-330 reactor. Even at these high temperatures, most of the NH<sub>3</sub> is converted to amine which did not undergo decomposition.

**Table 2: Effect of Temperature on Ammonia Decomposition in Quartz Reactor**

**CH<sub>3</sub>OH/NH<sub>3</sub> moles = 1.0**  
**Residence Time = 0.5- 0.6 sec.**

<b>Temperature (oF)</b>	<b>Total NH<sub>3</sub> Conversion (%)</b>	<b>NH<sub>3</sub> Conversion to Amine (%)</b>
1300	80	70
1600	91	82
1800	>99	41

Table 3 contains data which were obtained in the RA-330 reactor without methanol injection. NH<sub>3</sub> decomposition of close to 100% was obtained at 13000F, 16000F and 18000F, which indicates that NH<sub>3</sub> decomposes directly to N<sub>2</sub> and H<sub>2</sub> on the surface of RA-330 which promotes the decomposition reaction.

**Table 3: Effect of Temperature on NH<sub>3</sub> Decomposition**

**Reactor = RA-330 Alloy**

**Residence Time = 0.8 -1.0 sec.**

<b>Temperature (°F)</b>	<b>NH<sub>3</sub> Decomposition (%)</b>
1000	27
1200	44
1300	>99
1600	>99
1800	>99

The data of Tables 1-3 led to the conclusion that NH<sub>3</sub> decomposition by reaction with CH<sub>3</sub>OH is not technically feasible due to the formation of amine as an intermediate product. The data also led to the conclusion that NH<sub>3</sub> can be completely decomposed on the surface of RA-330 without addition of CH<sub>3</sub>OH.

Table 4 contains data which were obtained in the RA-330 alloy reactor at 1300 and 16000F in the presence of H<sub>2</sub> and CO. Hydrogen present in the gas reduces NH<sub>3</sub> decomposition. At 13000F, NH<sub>3</sub> decomposition decreases from greater than 99% at 0% H<sub>2</sub> to 85% at 19% H<sub>2</sub> and to 76% at 34% H<sub>2</sub>. At 1600°F, NH<sub>3</sub> decomposition decreases from >99% at 0% H<sub>2</sub> to 92% at 20% H<sub>2</sub> and to 84% at 35% H<sub>2</sub>. Carbon monoxide does not seem to have any significant effect on NH<sub>3</sub> decomposition.

**Table 4: Effect of H<sub>2</sub> and CO on Ammonia Decomposition**

**Reactor = RA-330 Alloy**

**Residence Time = 0.8 -0.9 sec.**

<b>Temperature (°F)</b>	<b>H<sub>2</sub> Concentration (%)</b>	<b>CO Concentration (%)</b>	<b>NH<sub>3</sub> Decomposition (%)</b>
1300	19	0.0	85
1300	34	0.0	76
1600	20	0.0	92
1600	35	0.0	84
1300	20	30	86
1600	30	32	88

## Application of RAPD Ammonia Decomposition Process

The test data of Tables 1-4 were evaluated to determine applicability of the RAPD concept for decomposition of  $\text{NH}_3$  present in coal gas at high temperatures before the gas is fed to the gas turbine. The evaluation showed that the RAPD process is technically feasible and is applicable for decomposition of  $\text{NH}_3$  present in coal gas at high temperatures upstream of the gas turbine. Figures 3 and 4 contain conceptualized schematics of the RAPD process.

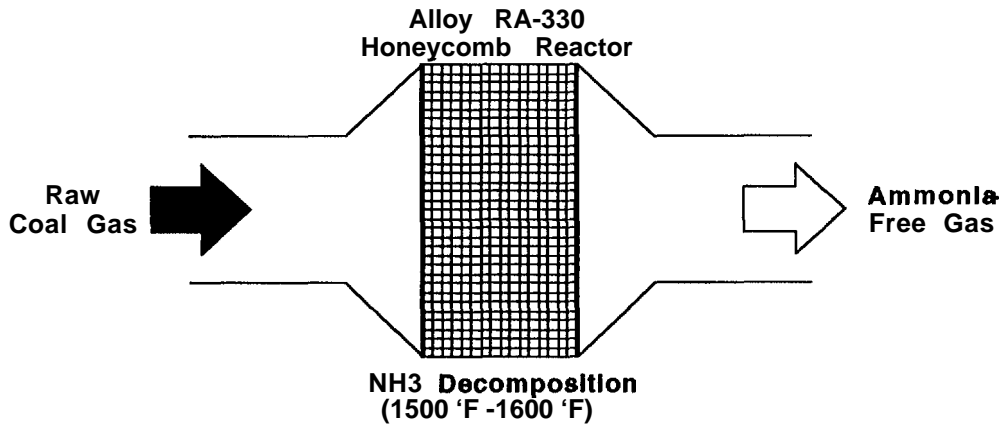


Figure 3. Schematic of High Temperature RAPD Process for  $\text{NH}_3$  Decomposition

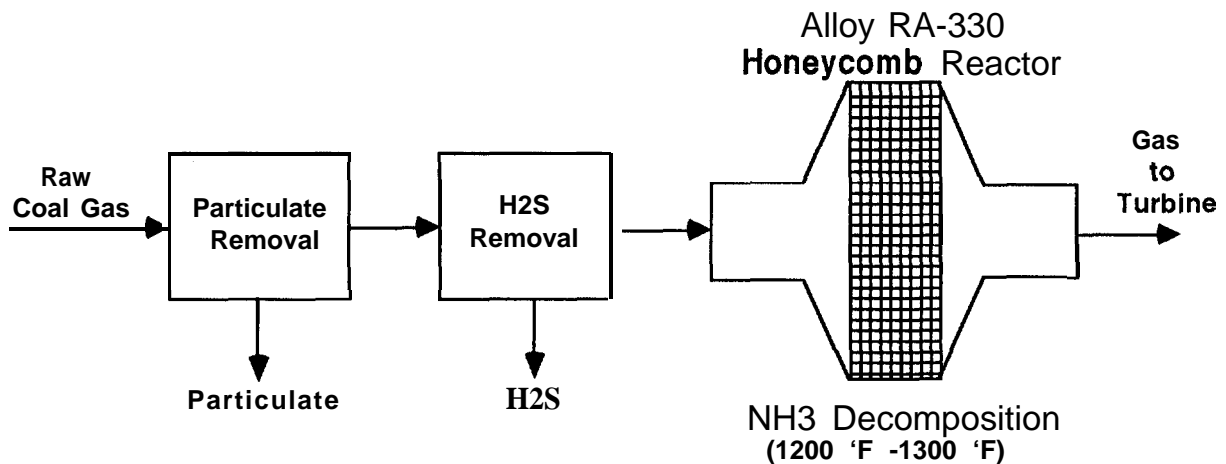


Figure 4. Schematic of Low Temperature RAPD Process for  $\text{NH}_3$  Decomposition

In the process scheme of Figure 3, coal gas enters the  $\text{NH}_3$  decomposition reactor which contains a packed bed of RA-330 honeycombs at a temperature of 1500 - 1600°F. Ammonia decomposes to  $\text{N}_2$  and  $\text{H}_2$  on RA-330 surface which promotes decomposition. In the process scheme of Figure 4, coal gas, after removal of particulate and  $\text{H}_2\text{S}$ , enters the  $\text{NH}_3$  decomposition reactor which contains a packed bed of M-330 honeycombs at a temperature of 1200-1300°F. Ammonia decomposes to  $\text{N}_2$  and  $\text{H}_2$  on RA-330 surface which promotes decomposition,



Table 5 contains NH<sub>3</sub> decomposition data applicable to IGCC technology. Ammonia decomposition depends upon temperature and H<sub>2</sub> concentration in the coal gas. At H<sub>2</sub> concentration of 19-20%, which is characteristic of air-blown coal gasification processes, NH<sub>3</sub> decomposition of 80-85% can be obtained at 1200- 1300F. At H<sub>2</sub> concentration of 30-35%, which is characteristic of oxygen-blown coal gasification processes, NH<sub>3</sub> decomposition of 85-90% can be obtained at 1500 - 1600F.


**Table 5: RAPD Ammonia Decomposition Process - Application to IGCC Technology**

Temperature (oF)	H <sub>2</sub> Concentration (%)	NH <sub>3</sub> Decomposition (%)	Potential Application
1200-1300	19-20	80-85	Air-blown gasification based IGCC technology
1500-1600	30-35	85-90	Oxygen-blown gasification based IGCC technology

These NH<sub>3</sub> decomposition percentages are calculated from raw experimental data. There is potential to improve NH<sub>3</sub> decomposition rates by providing more surface for decomposition and by optimizing process conditions,

### Catalytic Ammonia Removal (CAR) Process

Figure 5 contains a schematic of the CAR process for removal of NH<sub>3</sub> from coal gas. In this process, coal gas free of particulate and H<sub>2</sub>S enters the reactor in the temperature range of 800-1000oF. Air or oxygen is injected into the gas stream before it enters the catalyst bed. The process uses commercially available honeycomb catalysts, The technical feasibility of the process was established by performing tests in the flow system (Figure 1) using a quartz tube packed with an alumino-silicate catalyst of 3-4 mm pieces cut from a honeycomb. Tests were carried out in the temperature range of 850- 1000F in the presence of H<sub>2</sub> and O<sub>2</sub>.

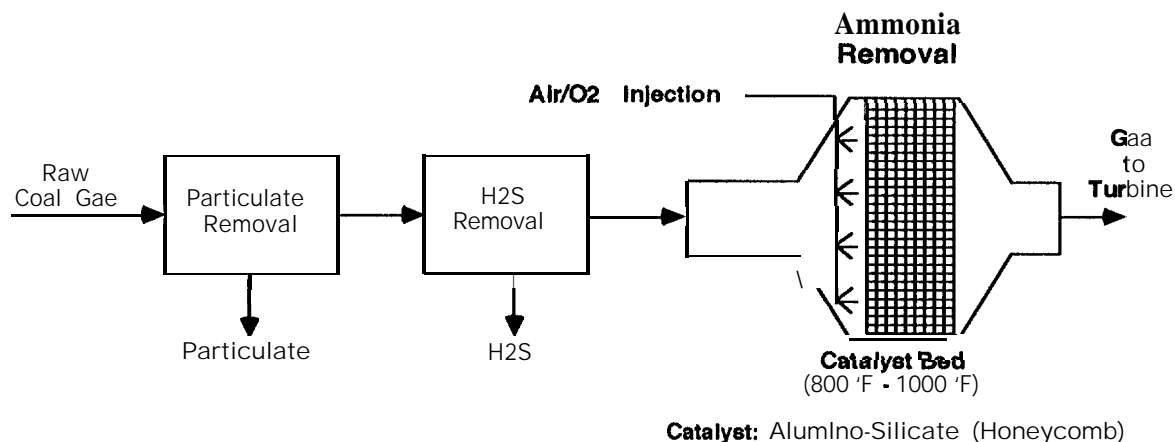

**Figure 5. Schematic of Catalytic Process for NH3 Removal**

Figure 6 contains process data obtained at 8500F and residence time of 0.5 -0.6 seconds. The data show that  $\text{NH}_3$  conversion decreases with increase in hydrogen concentration but increases with increase in  $\text{O}_2$  concentration. At  $\text{H}_2$  concentration of 10-20%, 85-90% of  $\text{NH}_3$  can be removed by maintaining  $\text{O}_2$  concentration of 2.0- 2.5%. At  $\text{H}_2$  concentration of 30-35%,  $\text{NH}_3$  conversion of only 50-70% was obtained in the same  $\text{O}_2$  concentration range. More  $\text{O}_2$  is required to get higher ammonia conversion at higher  $\text{H}_2$  concentration.

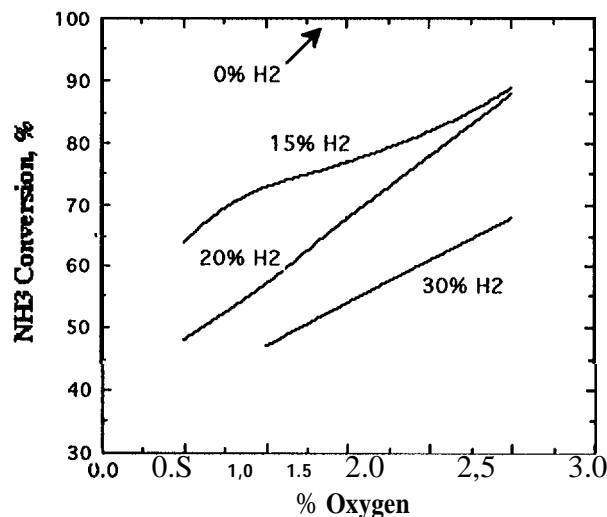


Figure 6. Effect of H2 and O2 on NH3 Removal at 850 F

Figure 7 contains process data obtained at 9000F and residence time of 0.5 -0.6 seconds, The data show similar effects of  $\text{H}_2$  and  $\text{O}_2$  on  $\text{NH}_3$  removal as the data of 8500F showed. Ammonia removal decreases with  $\text{H}_2$  concentration but increases with  $\text{O}_2$  concentration, However, higher  $\text{NH}_3$  conversions were obtained at 9000F when compared to conversions obtained at 850°F. At  $\text{H}_2$  concentration of 10-20%, 85-95% of  $\text{NH}_3$  can be removed by maintaining  $\text{O}_2$  concentration of 2.0- 2.5%. At  $\text{H}_2$  concentration of 30-35%, 65-70% of  $\text{NH}_3$  can only be removed at  $\text{O}_2$  concentration of 2.0- 2.5%.


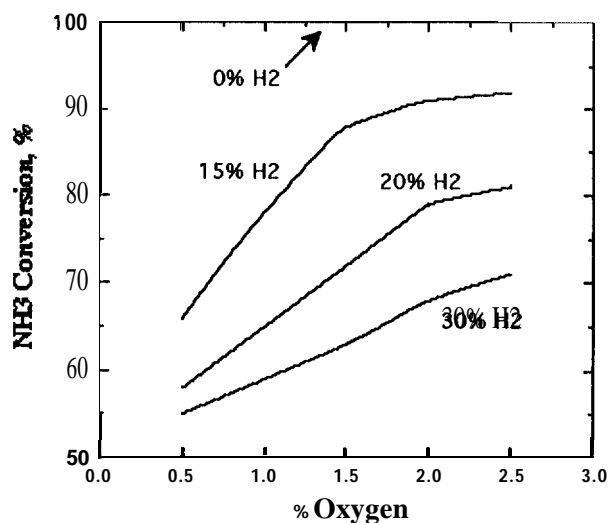


Figure 7. Effect of H2 and O2 on NH3 Removal at 900 F

Figure 8 contains process data obtained at 950 and 1000oF at H<sub>2</sub> concentration of 35%. At 9500F, NH<sub>3</sub> removal of 70-80% was obtained at O<sub>2</sub> concentration of 2.0- 2.5%. Ammonia removal has increased at 10000F. At O<sub>2</sub> concentration of 2.0- 2.5%, NH<sub>3</sub> removal of 85-95% was obtained.

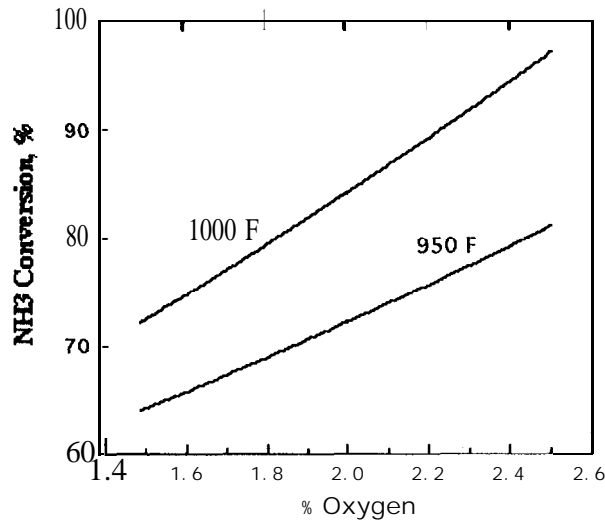

**Figure 8. Effect of Temperature and O<sub>2</sub> on NH<sub>3</sub> Removal with 35% H<sub>2</sub>**

### **Application of Catalytic Ammonia Removal Process**

The catalytic conversion data presented in Figures 6-8 and Table 6 show that the process has potential applications for NH<sub>3</sub> removal from both air-blown and oxygen-blown gasification based IGCC technologies. For air-blown gasification based application, 80-90% of NH<sub>3</sub> can be removed in the temperature range of 850- 9000F. For oxygen-blown gasification application, 85-95% of NH<sub>3</sub> can be removed in the temperature range of 950- 10000F. In both cases, O<sub>2</sub> concentration of 2.0- 2.5% is required.

**Table 6: Catalytic Ammonia Removal Process - Application to IGCC Technology**

<b>Hydrogen Concentration (%)</b>	<b>Temperature (oF)</b>	<b>Oxygen Concentration (%)</b>	<b>Ammonia Removal (%)</b>	<b>Potential Application</b>
15-20	<b>850-900</b>	2.0- 2.5	<b>80-90</b>	Air-blown gasification based IGCC technology
<b>30-35</b>	<b>950-1000</b>	2.0- 2.5	85-95	Oxygen-blown gasification based IGCC technology

There is potential to further improve NH<sub>3</sub> conversion by increasing residence time and optimizing process conditions.

## Accomplishments

The Energy and Environmental Technology Corporation developed two new process concepts for **decomposition/removal** of ammonia present in IGCC fuel gas streams. Bench-scale test data showed that the process concepts are technically feasible and are applicable to both air-blown and oxygen-blown coal gasification based IGCC technologies. The processes have potential for **decomposing/removing** ammonia by more than 90%.

## Future Activities

More work needs to be done to determine the full potential of the NH<sub>3</sub> **decomposition/removal** processes. More bench-scale tests and scale-up of the processes are required to determine viability for practical applications. Cost estimates of the processes have to be made to determine cost saving potential when compared to removal of NO<sub>x</sub> from gas turbine exhausts of IGCC plants.

## Acknowledgement

Research sponsored by the U. S. Department of Energy's SBIR Program under grant FG03-95ER8 1964 with Energy and Environmental Technology Corporation.

## References

1. Schonbucher, B., *Reduction of Nitrogen Oxides from Coal-Fired Power Plants by Using the SCR Process. Experience in the Federal Republic of Germany with Pilot and Commercial Scale DeNO<sub>x</sub> Plants*, Proceedings of 1989 Symposium on Stationary Combustion Nitrogen Oxide Control, EPRI GS-6423, Vol. 2, 1989, p. 6A-1 to 6A-17.
2. Mori, T., and Shimizu, N., *Operating Experience of SCR Systems at EPDC's Coal-Fired Power Station*, Proceedings of 1989 Symposium on Stationary Combustion Nitrogen Oxide Control, EPRI GS-6423, Vol. 2, 1989, p. 6A-85 to 6A-104.
3. Roble, C. P., and Ireland, P. A., *Technical Feasibility and Cost of Selective Catalytic Reduction (SCR) NO<sub>x</sub> Control*, EPRI GS-7266, 1991.
4. Kohl, A., and Riesenfeld, F., *Gas Purification*, 4th Edition, Gulf Publishing Company, Houston, 1985.
5. Jones, D. G., et al., *Two Stage DeNO<sub>x</sub> Process Test Data from Switzerland's Largest Incineration Plant*, EPRI Report GS-6423, Vol. 2, 1989.
6. Stanby, R. K., *High Temperature Catalytic Ammonia Decomposition for Reducing Fuel Bound NO<sub>x</sub> in Integrated Gasification Combined Cycle Plants*, METC Internal Document, April 21, 1994.