

**Sign Reversal of the MN-O bond Compressibility in
La₂Sr_{1.8}Mn_{2.0}O₇ Below T_c : Exchange Striction ECEI VED
in the Ferromagnetic State**

**JUL 07 1997
OSTI**

D. N. Argyriou§, J. F. Mitchell, J. B. Goodenough*, O. Chmaissem†
S. Short, and J. D. Jorgensen

† Science and Technology Center for Superconductivity and Materials Science Division
Argonne National Laboratory
Argonne, IL 60439

*Center for Materials Science and Engineering, ECT 9.102
University of Texas at Austin
Austin, TX 78712-1063

The submitted manuscript has been created by the University of Chicago as Operator of Argonne National Laboratory ("Argonne") under Contract No. W-31-109-ENG-38 with the U.S. Department of Energy. The U.S. Government retains for itself, and others acting on its behalf, a paid-up, non-exclusive, irrevocable worldwide license in said article to reproduce, prepare derivative works, distribute copies to the public, and perform publicly and display publicly, by or on behalf of the Government.

March_ 1997

ism **DISSEMINATION**

INTERNATIONAL UNLIMITED



Distribution:

- 1-3. M. J. Masek
4. B. D. Dunlap
5. G. W. Crabtree
6. J. D. Jorgensen
7. F. Y. Fradin
8. B. S. Brown/330
9. M. B. Brodsky
10. Editorial Office
11. Authors
12. S & T C (5)
13. High T_c

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

This work is supported by the Division of Materials Sciences, Office of Basic Energy Sciences of DOE, under contract No. W-31-109-ENG-38 (JFM, SS, JDJ) and the National Science Foundation, Office of Science and Technology Centers, under grant #DMR 91-20000 (DNA, OC).

§Present Address: Los Alamos Neutron Science Center, Los Alamos National Laboratory, Los Alamos, NM 87545

DECLAIMER

Portions of this document may be illegible in electronic image products. Images are produced from the best available original document.

**Sign Reversal of the MN-0 bond Compressibility in
La_{1,2}Sr_{1,8}Mn₂₀7BelowT_c : Exchange Striction
in the Ferromagnetic State**

D. N. Argyriou§ J. F. Mitchell, J. B. Goodenough*, **O. Chmaissem**
S. Short, and J. D. Jorgensen

Science and Technology Center for Superconductivity and Materials Science Division
Argonne National Laboratory
Argonne, IL 60439

*Center for Materials Science and Engineering, ECT 9.102
University of Texas at Austin
Austin, TX 78712-1063

The submitted manuscript has **been** created by the University of Chicago as Operator of Argonne National ("Argonne") under Contract No. W-31-109-ENG-38 with the U.S. Department of Energy. The U.S. Government retains for itself, and others acting on its behalf, a paid-up, non-exclusive, irrevocable worldwide license in said article to reproduce, prepare derivative works, distribute copies to the public, and perform publicly and display publicly, by or on behalf of the Government.

March, 1997

Submitted to Physical Review Letters

/sm

This work is supported by the Division of Materials Sciences, Office of Basic Energy Sciences of DOE, under contract No. W-31-109-ENG-38 (JFM, SS, JDJ) and the National Science Foundation, Office of Science and Technology Centers, under grant #DMR 91-20000 (DNA, OC).

§Present Address: Los Alamos Neutron Science Center, Los Alamos National Laboratory, Los Alamos, NM 87545

**Sign Reversal of the Mn-O bond Compressibility in La_{1.1}Sr_{1.8}Mn₂O₇ Below T_C :
Exchange Striction in the Ferromagnetic State**

D. N. Argyriou[§], J. F. Mitchell, J. B. Goodenough*, O. Chmaissem, S. Short, and J. D. Jorgensen

"Science and Technology Center for Superconductivity and Materials Science Division
Argonne National Laboratory, Argonne, IL, 60439

*Center for Material Science and Engineering, ECT 9.102
University of Texas at Austin, Austin, TX, 78712-1063

The crystal structure of the layered perovskite La_{1.2}Sr_{1.8}Mn₂O₇ has been studied under hydrostatic pressure up to —6 kbar, in the paramagnetic and ferromagnetic states, with neutron powder diffraction. The compressibility of the Mn-O apical bonds in the double layer of MnO₆ octahedra changes sign from the paramagnetic insulator (PI) to the ferromagnetic metal (FM) state; in the FM state the Mn-O-Mn linkage between MnO₂ planes expands under applied pressure, whereas they contract in the PI state. This counterintuitive behavior is interpreted in terms of *exchange striction*, which reflects the competition between super- and double-exchange. An increase of the Mn-moment with applied pressure in the FM state is consistent with a positive dT_C/dP , as well as a cant angle θ_0 between the magnetizations of neighboring MnO₂ sheets that decreases with pressure.

[§] Present Address, Los Alamos Neutron Science Center, Los Alamos National Laboratory, Los Alamos, New Mexico 87545.

The physical properties of transition metal oxides are particularly sensitive to pressure where an increase in the overlap between oxygen-2p and cation-d orbitals induces a transition from localized (or strongly correlated) to itinerant electronic behavior, as found in the perovskite PrNiO_3 ¹ and V_2O_3 .² Pressure affects magnetic properties where orbital degeneracies can lead to orbital ordering, as is illustrated by LaVO_3 .³ In mixed valent systems such as in the double exchange ferromagnet $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$, both electronic and ferromagnetic transitions are coupled, and pressure increases the Curie Temperature, T_c .^{4, 5} This is in sharp contrast to other itinerant perovskite systems (e.g. SrRuO_3) where application of pressure generally leads to a suppression of T_c .^{6, 7}

Recently Moritomo *et al.*⁸ have reported that the layered Ruddlesden-Popper compound $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$ is a ferromagnetic metal (FM) below $T_c=120$ K and a paramagnetic insulator (PI) above this temperature. They attribute the coupled electronic and magnetic transitions at T_c to a double exchange coupling in Mn-O-Mn linkages. Application of magnetic field on this compound leads to enhanced magnetoresistance (MR) (20,000% at 129 K in 7 T, —200% at 300 K in 0.3 T) with respect to a similarly doped perovskite material ($\text{La}_{0.825}\text{Sr}_{0.175}\text{MnO}_3$, —200% in 7 T)⁹. In this paper we report the crystal structure of the layered, perovskite related compound $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$ under hydrostatic pressure up to —6 kbar, in both the PI and FM states. We demonstrate that of the two apical Mn-O bonds along the c-axis, one expands with pressure while the other contracts. Remarkably, the compressibilities of both of these bonds change sign on traversing T_c . We argue that this unusual finding is a manifestation of *exchange striction* and predict that the compound is a canted-spin ferromagnet. This finding dramatically demonstrates how metal-oxygen bond strengths are modulated by metal-oxygen-metal interactions. Furthermore, it is an unusual example of an expansion of individual metal-oxygen bonds along an axis that shows a normal decrease with pressure.

Crystals of $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_{2.0}\text{O}_7$ were melt-grown in flowing 20% O_2 (balance Ar) in a floating zone optical image furnace (NEC SC-M15HD). The sample exhibits a transition from a paramagnetic insulator to a ferromagnetic metal at 120 K, in good agreement with the report of Moritomo *et al.*⁸ Further details on the growth and characterization of this sample can be found elsewhere.¹⁰

Time-of-flight neutron powder diffraction data were collected on the Special Environment Powder Diffractometer (SEPD) at Argonne's Intense Pulsed Neutron Source (IPNS) with the sample in a helium gas pressure cell.¹¹ Diffraction data were obtained for a series of pressures up to 6.5 kbar at 300, and 200 K in the paramagnetic state and 100 K in the ferromagnetic state.

Neutron diffraction patterns of $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_{2.0}\text{O}_7$ were consistent with a tetragonal cell, space group $I4/mnm$ at all pressures and temperatures. Powder diffraction patterns were analyzed with the Rietveld method and the program GSAS¹². For data measured at 100 K additional magnetic scattering was consistent with previous ambient pressure observations that the Mn-moment lies within the *ab* plane in $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_{2.0}\text{O}_7$. Results of the Rietveld analysis for data measured at 300 and 100 K as a function of pressure are given in table 1. The crystal structure of $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_{2.0}\text{O}_7$ (Fig. 1) consists of double perovskite layers, each layer made up of a two dimensional network of MnO_6 octahedra. The La,Sr-atoms are found between octahedra. Alternate perovskite bi-layers along the *c*-axis are misaligned with respect to each other, as shown in figure 1.

A linear fit to refined lattice parameters as a function of pressure measured at 300, 200 and 100 K were used to compute the compressibility of $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_{2.0}\text{O}_7$ at these temperatures (shown in Fig. 2a). The *a*-axis compressibilities remains almost constant with temperature, while the *c*-axis compressibility becomes more positive (less compressible) with decreasing

temperature. The combination of the a- and c-axis compressibility thus results in a volume compressibility that increases slightly with decreasing temperature (Fig. 2b). The a-axis compressibility is accounted for wholly by the reduction of the Mn-O(3) bond length (-0.15% over 6 kbars) (Fig. 3c and 3f) for all temperatures examined; the Mn-O(3)-Mn bond angle remains unchanged within experimental error at $178.6(4)^\circ$, indicating no additional buckling of MnO₆ octahedra occurs with applied pressure. This is in contrast to other perovskite materials^{13, 14}, where application of pressure results primarily in a tilting of the MnO₆ octahedra, rather than changes of the Mn-O bond lengths.

Although the c-axis compressibility changes linearly with temperature, Fig. 2, investigation of the compressibilities of the individual c-axis Mn-O bonds reveals two remarkable findings: (1) the pressure variations of distinguishable Mn-O(1) and Mn-O(2) bond lengths have opposite signs and (2) the signs of these variations are opposite in the PI regime at 300 K, Fig. 3a and 3b, to what they are in the FM state at 100 K, Fig. 3d and 3e. The compressibilities of the individual Mn-O apical bonds are not in proportion to the overall c-axis compressibility (Fig. 2a), reflecting that the remainder of the lattice compensates for the compressibility of the perovskite double layer. That the O(1) and O(2) oxygen atoms share the same Mn orbital while exhibiting opposite Mn-O compressibilities forces consideration of the Mn-O(1)-Mn interactions in contrast to the Mn-O(2)-La,Sr interactions.

The response of the individual Mn-O bond lengths to applied pressure in the PI and FM states reflects a change in the c-axis Mn-O-Mn interactions with the degree of ferromagnetic alignment of pairs of ferromagnetic MnO₂ sheets. The observed compressibilities are consistent with a magnetic structure in which the ferromagnetic MnO₂ sheets have magnetizations canted with respect to one another. To understand this model, two contributions to the c-axis Mn-O-Mn interactions need to be considered: the antiferromagnetic $t^3-A_n-t^3$ it-bonding component between half-filled t_{2g} orbitals of the high-

spin Mn^{3+} or Mn^{4+} configurations and the ferromagnetic $el-p_a-0$ component that dominates the bonding interactions via electrons in the twofold degenerate states of e_g orbital parentage¹⁵. Both interactions involve a charge transfer that preserves the spin angular momentum. The t^3 configurations remain localized, so transfer of a t electron to create a t^4 configuration at a neighboring Mn atom requires an energy U_{ir} and is constrained by the Pauli exclusion principle to have a component of the transferred electron spin antiparallel to the spin of the t^3 configuration at the acceptor Mn atom. This antiferromagnetic t^3-t^3 superexchange interaction is described by second-order perturbation theory; it gives a stabilization energy, $E = -b_s \sin^2(\theta/2)/U_x - b_c \cos\theta/U$, where b_s is the spin-independent transfer-energy matrix element and θ is the angle between spins at neighboring Mn atoms along the c-axis. A $\theta = \pi$ gives an attractive Mn-O-Mn interaction; a $\theta = 0$ gives a repulsive interaction.

The $el-p_a-e^o$ interaction, on the other hand, involves transfer of an e electron to an empty e orbital; this transfer is not constrained by the Pauli exclusion principle, but a strong ferromagnetic intra atomic exchange favors transfer to an acceptor having its spin ferromagnetically aligned with respect to that of the transferred electron. This ferromagnetic $el-p_a-e^o$ interaction is stronger than the t^3-t^3 interaction whether the charge transfer is virtual (superexchange) or real (double-exchange). A real charge transfer is described by first-order theory, so it gives a stabilization $E = -b_a \cos\theta/2$. In the FM state, the charge transfer between and within MnO₂ planes is real, and optimization of θ for the sum of the superexchange and double-exchange components gives a cant angle $\theta = 0$ if $\cos(\theta/2) > b_s/U_{ir}$. A $\theta = 0$ is stabilized below T_T *within* ferromagnetic MnO₂ planes, but the compressibility data imply a $\cos(\theta/2) < 1$ for the magnetic coupling *between* planes. Since b_a contains a larger Mn-O overlap integral than b_s , pressure increases $\cos(\theta/2)$, thereby reducing the angle θ and increasing the t^3-t^3 spin-spin repulsion between MnO₂

planes. A change in lattice parameters induced by changes in bonding as a result of magnetic order represents an *exchange striction*; a phenomenon common to magnetic oxides.^{15, 16}

In $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$, each Mn atom sees a Mn-O-Mn interaction on only one side along the *c*-axis; the Mn-O-(La,Sr) interaction contains a Mn-O bond length that is free to adjust to that on the Mn-O-Mn side so as to retain the mean Mn-O bond length characteristic of the valence-bond sum, which is why the *c*-axis Mn-O bonds on opposite sides of a Mn atom vary reciprocally with temperature¹⁰ and pressure. In the absence of magnetic order in the PI state, there is no spin-spin repulsion and pressure increases the overlap integrals in both b_x and b_a to give a normal reduction of the equilibrium Mn-O bond lengths within and between the MnO₂ sheets. This behavior is clearly seen for the Mn-0(1) and Mn-0(3) bonds at 300 K, Figure 3. The Mn-0(2) bond length behaves differently because it is not part of the MnO-Mn linkage, see Figure 1; it responds to the Mn-0(1) and Mn-0(3) bond-length changes so as to conserve the mean equilibrium bond-length sum for the Mn valences. We have omitted

from this qualitative discussion the influence of any redistribution of electrons between $d_{x^2-y^2}$ and $d_{3z^2-r^2}$ orbitals with pressure, as such a redistribution would not contribute to a sign reversal of the Mn-0(1) and Mn-0(2) compressibilities on crossing *T*.

In the absence of magnetic superlattice reflections, the neutron powder diffraction data are consistent with the type-A canted spin ferromagnetic model proposed. They indicate a ferromagnetic coupling within MnO₂ basal planes below *T_c*. Analysis of the diffraction data using models with a *z*-component of the spin parallel to the *c*-axis consistently produce values of $p_z = 0$ at all pressures examined. Because of the tetragonal symmetry of the lattice, single-crystal neutron-diffraction studies are needed to confirm whether there is the predicted cant angle in the *a-b* planes between spins of neighboring MnO₂ planes. However, an observed increase in the Mn moment from 2.5 to 2.8 μ_B over 6 kbar of pressure is consistent with the predicted decrease of cant angle, *00* and a positive dT/dP for this compound

In conclusion, the surprising reversal in the sign of the Mn-O(1) bond compressibility on passing from the PI to the FM state can be interpreted as a manifestation of exchange striction; a cant angle **80** between the magnetizations of the pairs of MnO₂ sheets within a perovskite layer is predicted for this layered manganite. The reciprocal response to temperature and pressure of the c-axis Mn-O(1) and Mn-O(2) bond-lengths reflects the asymmetric c-axis bonding at a Mn atom; the Mn-O(2) bonds are free to adjust their length so as to retain the equilibrium bond-length sum for the Mn valences.

This work was supported by the U.S. Department of Energy, Basic Energy Sciences-Materials Sciences, and ER-LIT, under contract W-31-109-ENG-38 (JFM, JDJ, SS) and by the NSF Office of Science and Technology Centers under DMR-91-20000 (DNA, OC). JBG thanks the NSF and the Robert A. Welch Foundation, Houston, TX, for financial support.

References

- ¹P. L. Canfield, J. D. Thompson, S.-W. Cheong and L. W. Rupp, *Phys. Rev. B* **47**, 12357 (1993).
- ^{2x}Obradors, L. M. Paulius, M. B. Maple, J. B. Torrance, A. I. Nazzal, I. Fontcuberta and X. Granados, *Phys. Rev. B* **47**, 12353 (1993).
- ³H. C. Nguyen and J. B. Goodenough, *Phys. Rev. B* **52**, 324 (1995).
- ⁴Y. Moritomo, A. Asamitsu and Y. Tokura, *Phys. Rev. B* **51**, 16491 (1995).
- ⁵W. Archibald, J.-S. Zhou and J. B. Goodenough, *Phys. Rev. B* **53**, 14445 (1996).
- ⁶N. Menyuk, J. A. Kafalas, K. Dwight and J. B. Goodenough, *J. App. Phys.* **40**, 1324 (1969).⁷
M. Shikano, T. Huang, Y. Inaguma, M. Itho and T. Nakamura, *Solid State Commun.* **90**, 115 (1994).
- ⁸Y. Moritomo, A. Asamitsu, H. Kuwahara and Y. Tokura, *Nature* **380**, 141 (1996).
- ⁹A. Urushibara, Y. Moritomo, T. Arima, A. Asamitsu, G. Kido and Y. Tokura, *Phys. Rev. B* **51**, 14103 (1995).
- ¹⁰J. F. Mitchell, D. N. Argyriou, J. D. Jorgensen, D. G. Hinks, C. D. Potter and S. D. Bader, *Phys. Rev. B*, *in press* (1996).
- ¹¹J. D. Jorgensen, S. Pei, P. Lightfoot, D. G. Hinks, B. W. Veal, B. Dabrowski, A. P. Paulikas and R. Kieb, *Physica C* **171**, 93 (1990).
- ¹²A. C. Larson and R. B. von Dreele, *General Structure Analysis System University of California* (1985-1990).
- ¹³Y. Zhao, D. J. Weidner, J. B. Parise and D. E. Cox, *Phys. Earth Planet. Inter.* **76**, 17 (1993).
- ¹⁴L-E. Jorgensen, J. D. Jorgensen, B. Batlogg, J. P. Remeika and J. D. Axe, *Phys. Rev. B* **33**, 4793 (1986).
- ¹⁵J. B. Goodenough. in *Progress in Solid State Chemistry* (eds. Reiss, H.) 145 (Pergmon Press, Oxford, 1971).

¹⁶J. B. Goodenough. *Magnetism and the Chemical Bond* (John Wiley & Sons, New York, 1963).

Table I: Structural parameters for La₁₂Sr₁₅Mn₂₀7 at (a) 300 and (b) 100 K over the pressure range 0 to -6.5 kbar. The space group used in the analysis of diffraction data was I4/mmm. In this structure the Mn is placed at (0,0,z), La/Sr(1) at (0,0,1/2), La/Sr(2) at (0,0,z), 0(1) at (0,0,0), 0(2) at (0,0,z) and 0(3) at (0,1/2,0). The Mn-moment g_{ab} at 100 K is given as 1.43/Mn•

T=300 K		0.08 kbar	1.54 kbar	3.12 kbar	4.62 kbar	6.21 kbar
<i>a</i> (Å)		3.87197(5)	3.87044(5)	3.86893(5)	3.86737(5)	3.86598(5)
<i>c</i> (Å)		20.1083(5)	20.1043(5)	20.0981(5)	20.0937(5)	20.0888(5)
Mn	<i>z</i>	0.0968(2)	0.0968(2)	0.0966(2)	0.0965(2)	0.0966(2)
La/Sr(2)	<i>z</i>	0.3173(1)	0.3176(1)	0.3175(1)	0.3176(1)	0.3175(1)
0(2)	<i>z</i>	0.1957(2)	0.1961(2)	0.1963(1)	0.1962(1)	0.1959(2)
0(3)	<i>z</i>	0.0952(1)	0.0950(1)	0.0950(1)	0.0951(1)	0.0947(1)


T=100 K		0.48 kbar	1.52 kbar	3.10 kbar	4.85 kbar	6.3 kbar
<i>a</i> (Å)		3.86706(5)	3.86602(5)	3.8649(5)	3.86305(5)	3.86124(5)
<i>c</i> (Å)		20.0475(5)	20.0463(5)	20.0423(5)	20.0366(5)	20.0326(5)
Mn		0.0966(2)	0.0967(2)	0.0968(3)	0.0970(3)	0.0971(3)
	<i>liab</i>	2.51(7)	2.61(6) 0.	2.68(6) 0.	2.74(8) 0.	2.80(6) 0.
La/Sr(2)		0.3175(1)	3177(1) 0.	3174(1)	3174(1) 0.	3175(1) 0.
0(2)		0.1960(2)	1961(2) 0.	0.1959(2)	1958(2) 0.	1958(2) 0.
0(3)		0.0951(1)	0952(1)	0.0951(1)	0949(1)	0949(1)


Figure Captions

Figure 1: The crystal structure of $\text{La}_{11}\text{Sr}_{1.8}\text{Mn}_{20}\text{O}_{70}$ projected along [010]. The unit cell is shown with a solid line.


Figure 2: The compressibilities of the a- and c-axis (upper panel) and unit cell volume (lower panel) vs. temperature.

Figure 3: The variation of Mn-O bondlengths in $\text{La}_{11.2}\text{Sr}_{1.8}\text{Mn}_{20}\text{O}_{70}$ with pressure at **300 K** (3a-3c) and 100 K (3d-3f). Lines are weighted least square fits to the data.

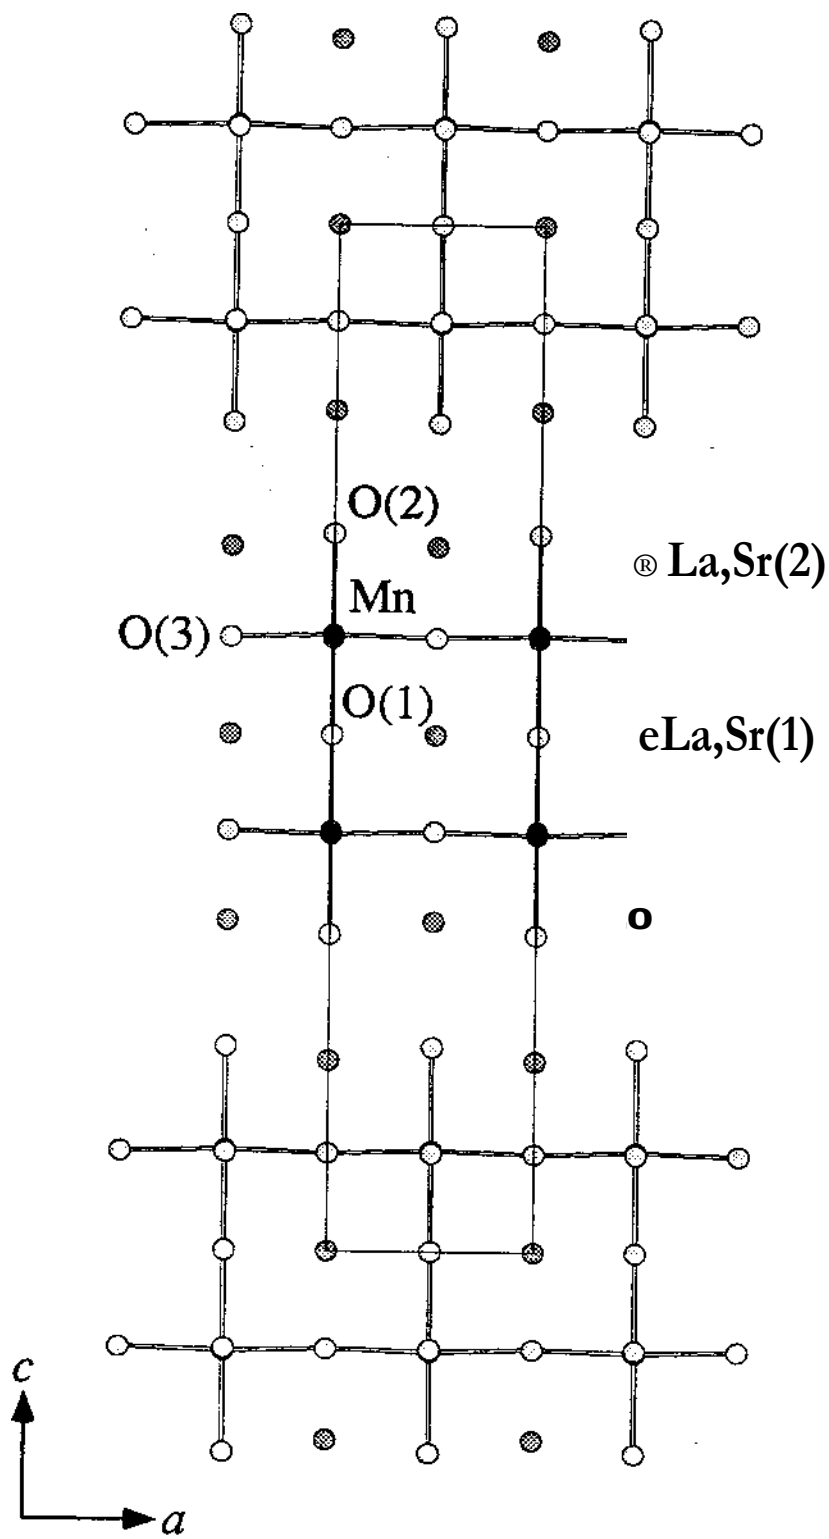

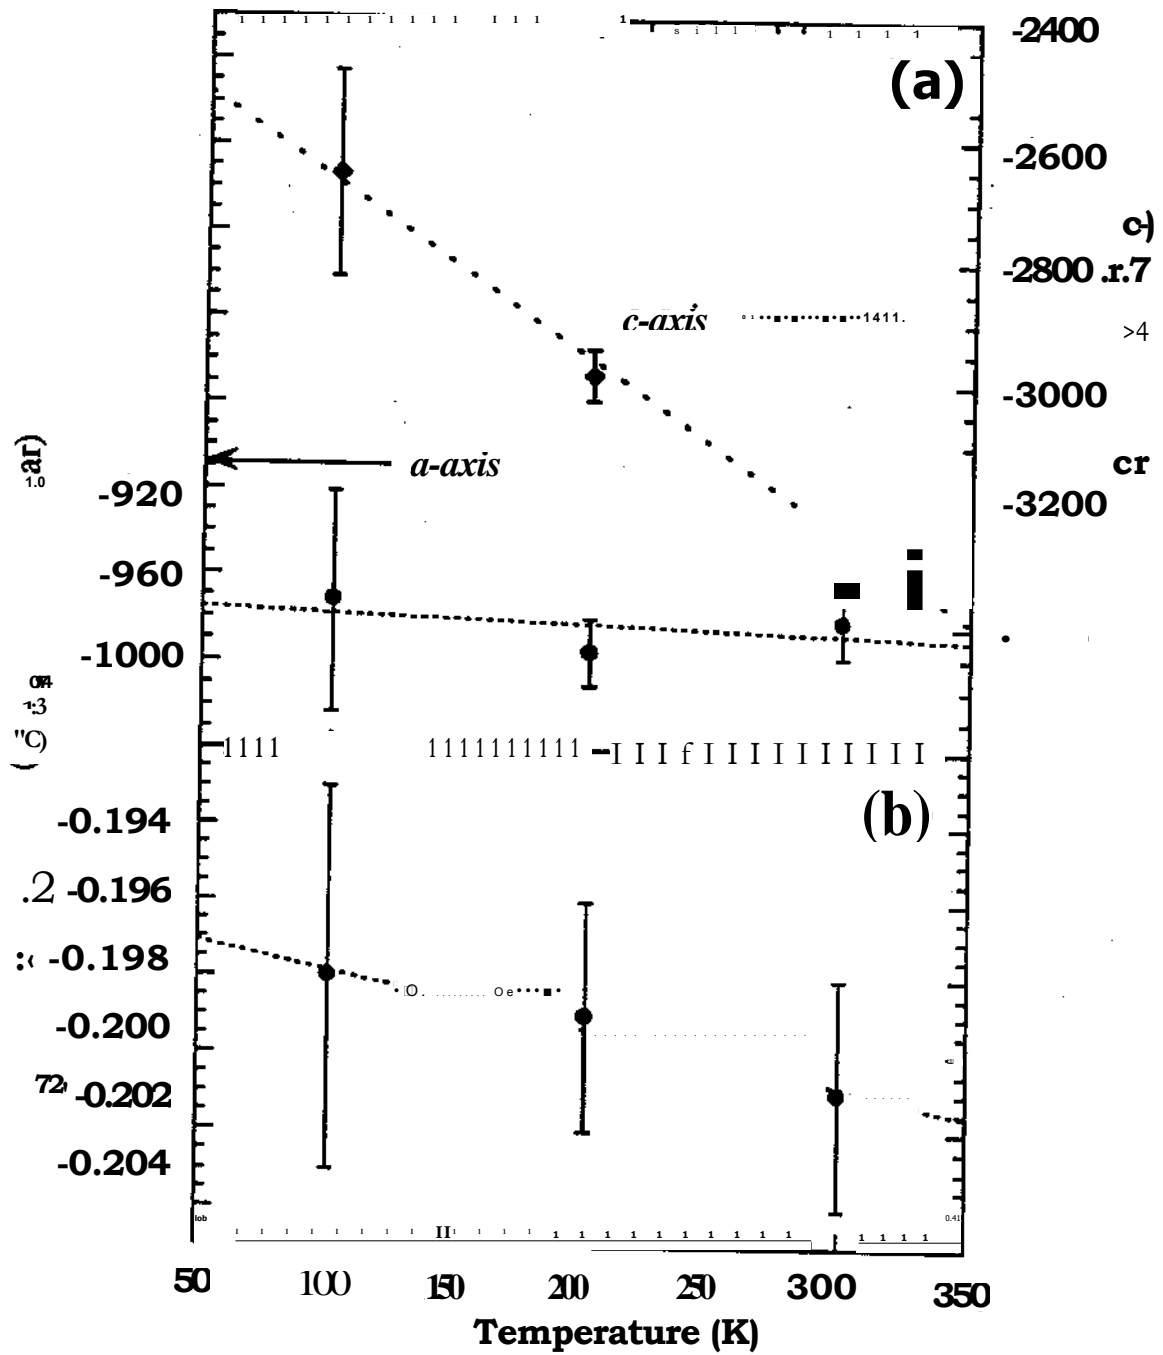

300K

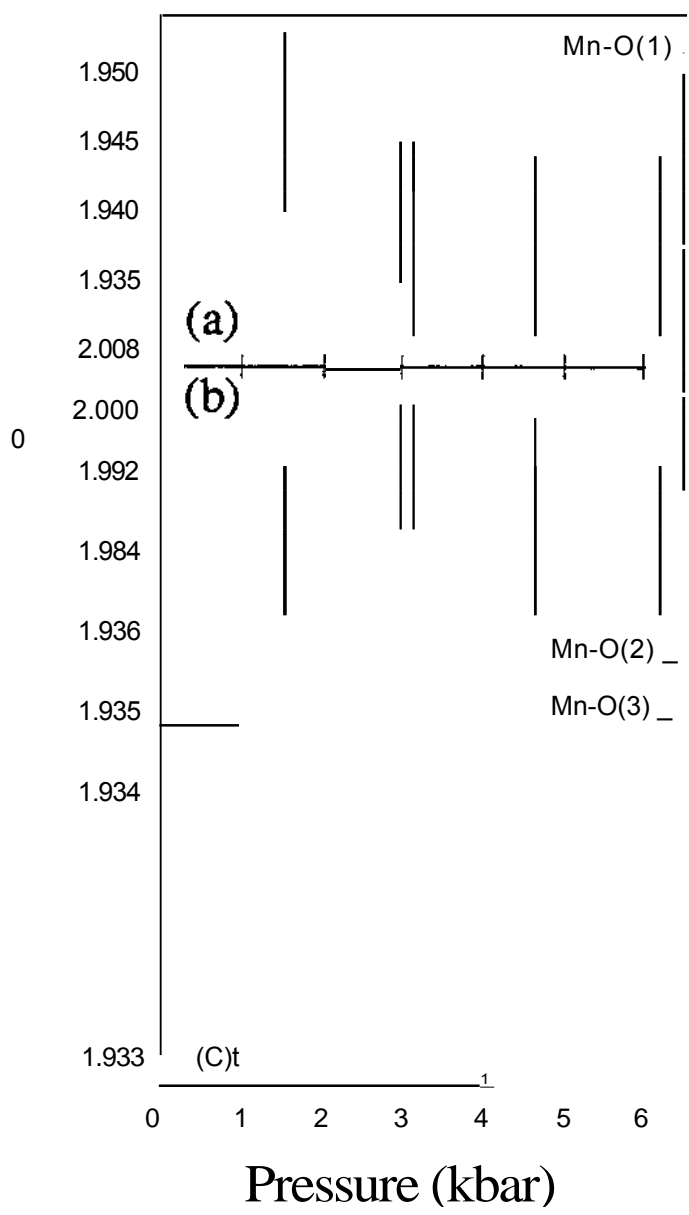

100K

