

KINGSTON

Ponded Fly Ash (Cell III)

Grain Size Distribution Test Report
Moisture-Density Relationship (Standard Proctor)
Moisture-Density Relationship (Modified Proctor)
Consolidation Test Report
Hydraulic Conductivity - Falling Head (2 Pages)
Triaxial Compression Test (2 Pages)
Direct Shear Test
California Bearing Ratio
Resilient Modulus (Standard Proctor) (9 Pages)
Resilient Modulus (Modified Proctor) (9 Pages)




**TVA - KINGSTON
PONDED FLY ASH (CELL III)**

Description	Test Method	Property	Sample 1	Sample 2	Sample 3
Grain Size	ASTM D 422	Percent Retained on the #4 Sieve	0.0	0.0	0.0
		Percent Passing the #200 Sieve	96.5	96.3	96.1
		Percent Passing the 0.005 mm Sieve	22.6	25.0	18.4
Atterberg Limits	ASTM D 4318	Liquid Limit	NL	NL	NL
		Plastic Limit	NP	NP	NP
		Plasticity Index	N/A	N/A	N/A
Specific Gravity	ASTM D 854	Specific Gravity at 20°C	2.31	2.29	2.34
Classification	ASTM D 2487	Unified Soil Classification System (USCS)	ML	ML	ML
	AASHTO M 145	AASHTO Classification	A-4(0.0)	A-4(0.0)	A-4(0.0)
Composite Sample					
Moisture-Density Relations (Standard Effort)	ASTM D 698	Maximum Dry Density, pcf	81.0		
		Optimum Moisture Content, %	23.5		
Moisture-Density Relations (Modified Effort)	ASTM D 1557	Maximum Dry Density, pcf	84.4		
		Optimum Moisture Content, %	23.7		
Consolidation	ASTM D2435	Compression Index C_c	Result	Dry Density, pcf	Moisture Content, %
			0.05	76.9	25.3
Hydraulic Conductivity	ASTM D 5084	Hydraulic Conductivity, cm/sec	3.4E-5	76.2	24.1
Triaxial Shear Strength Consolidated-Undrained (CU)	ASTM D4767	Effective Stress, Cohesion, c' , ksf	0.03	75.4	25.6
		Effective Stress, Internal Friction Angle, ϕ' , degrees	24.4		
		Total Stress, Cohesion, c , ksf	0.00	75.4	25.6
		Total Stress, Internal Friction Angle, ϕ , degrees	17.8		
Direct Shear Strength	ASTM D 3080	Cohesion, c , ksf	1.47	74.6	25.3
		Internal Friction Angle, ϕ , degrees	37.6		
California Bearing Ratio	ASTM D 1883	CBR, %	1	76.8	23.1
Resilient Modulus (Standard Compactive Effort)	SHRP P46	Resilient Modulus at 4psi axial stress and 4psi confining pressure	4,350	74.4	25.4
Resilient Modulus (Modified Compactive Effort)	SHRP P46	Resilient Modulus at 4psi axial stress and 4psi confining pressure	5,199	80.6	23.9
Soil Resistivity	AASHTO T 288	Minimum Resistivity, Ohm-cm	6,400		
pH of Soil	AASHTO T 289	pH	6.8		
Water Soluble Sulfate Ion	AASHTO T 290	Sulfate Ion Content, mg/kg	140		
Water Soluble Chloride Ion	AASHTO T 290	Chloride Ion Content, mg/kg	<10		

kif-fa3.xls

GRAIN SIZE DISTRIBUTION TEST REPORT

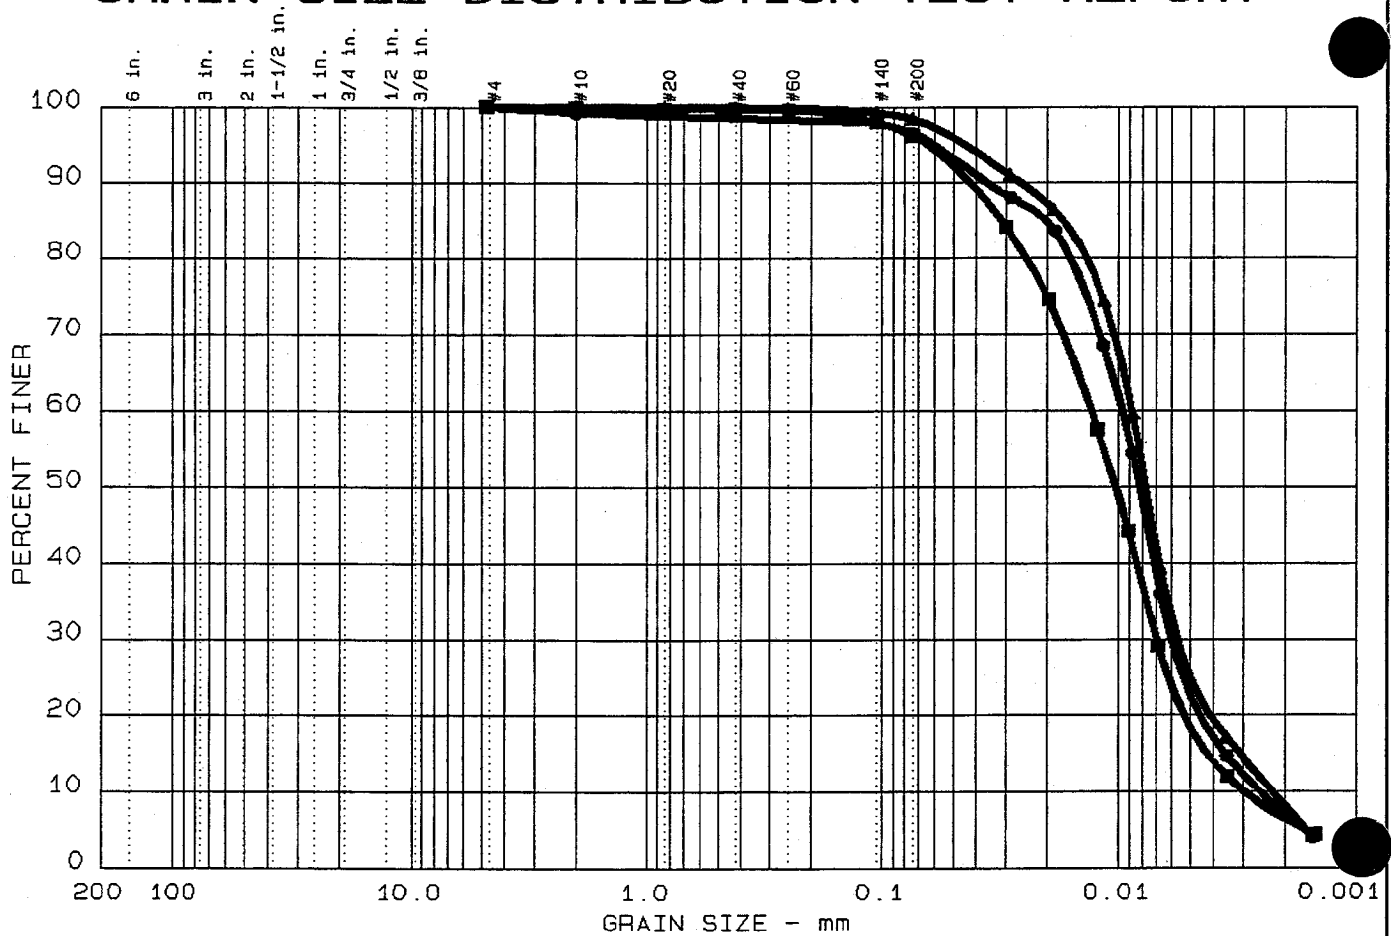

Test	% +3"	% GRAVEL	% SAND	% SILT	% CLAY
● 15	0.0	0.0	3.5	73.9	22.6
▲ 16	0.0	0.0	1.7	73.3	25.0
■ 17	0.0	0.0	3.9	77.7	18.4

	LL	PI	D85	D60	D50	D30	D15	D10	C _c	C _u
●	NL	NP			0.01	0.006	0.0036	0.0025	1.48	3.8
▲	NL	NP			0.01	0.006	0.0031	0.0022	1.65	3.9
■	NL	NP			0.01	0.007	0.0042	0.0030	1.25	4.4

MATERIAL DESCRIPTION	USCS	AASHTO
● Cell III	ML	A-4 (0.0)
▲ Cell III	ML	A-4 (0.0)
■ Cell III	ML	A-4 (0.0)


Project No.: 5810860101
 Project: TVA - Kingston
 ● Location: Poned Fly Ash A & B
 ▲ Location: Poned Fly Ash C & D
 ■ Location: Poned Fly Ash E & F
 Date: July 18, 1995

Remarks:
 Tested by: *JCR*
 Reviewed by: *HS*

GRAIN SIZE DISTRIBUTION TEST REPORT
LAW ENGINEERING, INC.

Figure No.

MOISTURE-DENSITY RELATIONSHIP

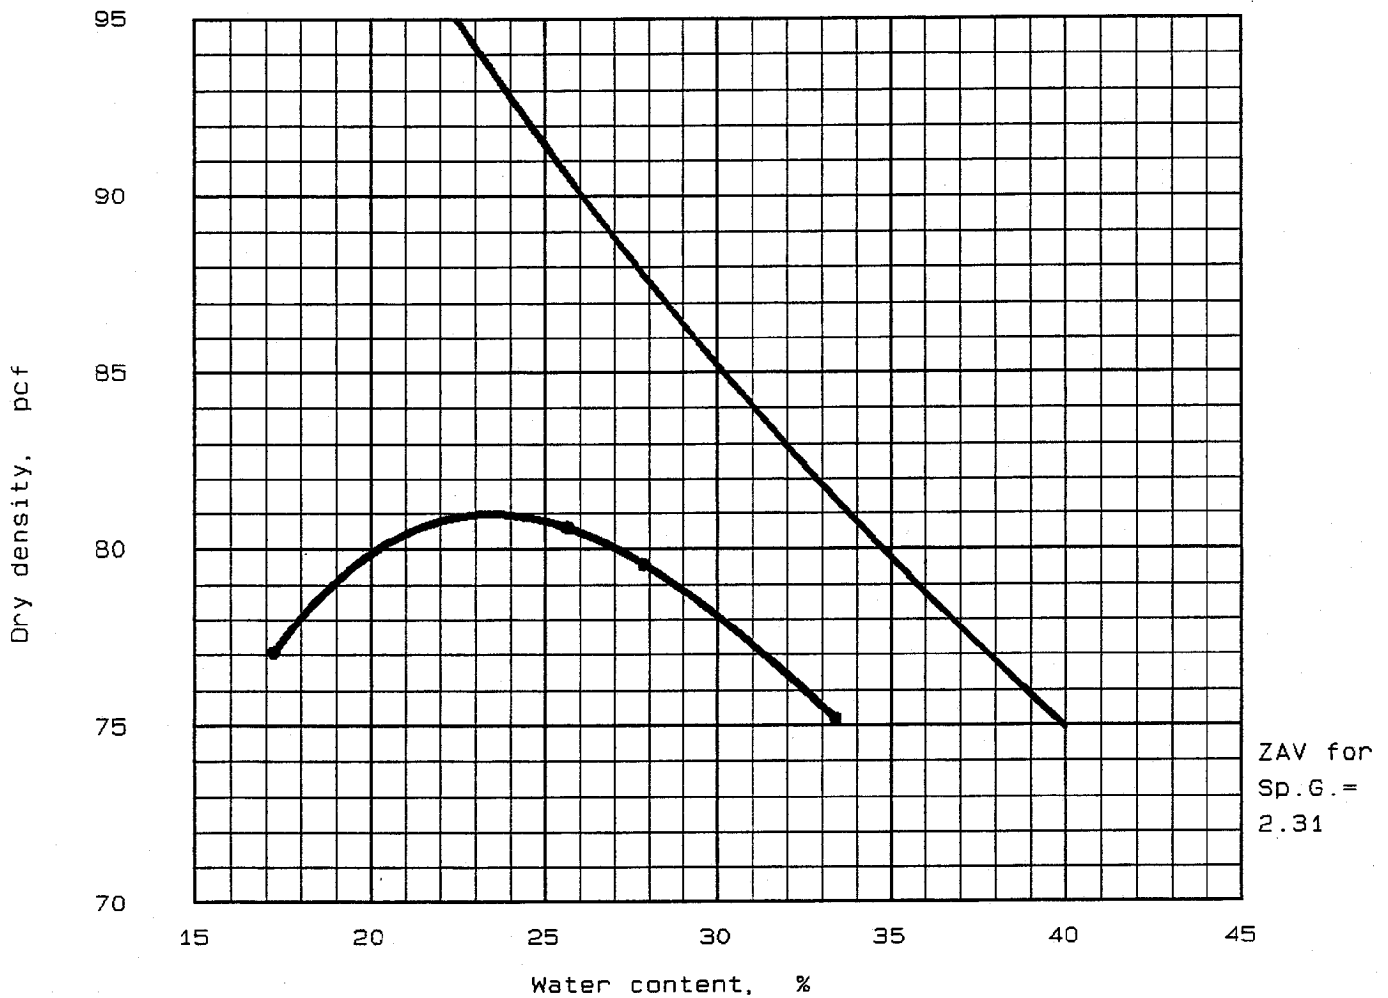


"Standard" Proctor, ASTM D 698, Method A

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > No. 4	% < No. 200
	USCS	AASHTO						
	ML	A-4 (0.0)	36.1 %	2.31	NL	NP	0 %	97.0 %

TEST RESULTS	MATERIAL DESCRIPTION
Optimum moisture = 23.5 % Maximum dry density = 81.0 pcf	
Project No.: 5810850101 Project: TVA - Kingston Location: Ponded Fly Ash Cell III Date: July 25, 1995	Remarks: Tested by: <i>EM/ice</i> Reviewed by: <i>RUB</i>
MOISTURE-DENSITY RELATIONSHIP LAW ENGINEERING, INC.	Figure No. _____

MOISTURE-DENSITY RELATIONSHIP

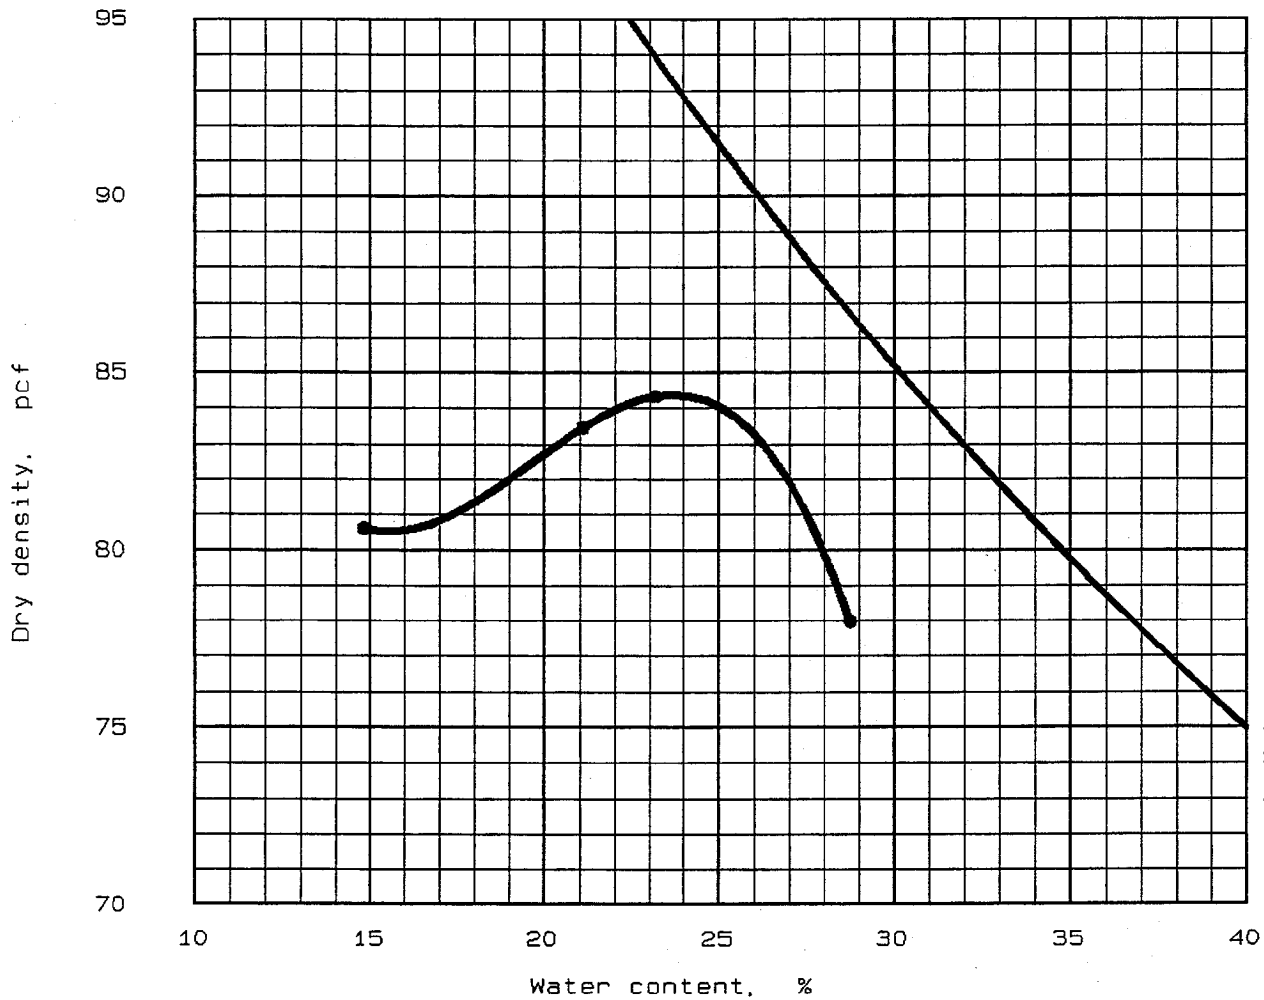

"Modified" Proctor, ASTM D 1557, Method A

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > No. 4	% < No. 200
	USCS	AASHTO						
	ML	A-4 (0.0)	36.1 %	2.31	NL	NP	0 %	97.0 %

TEST RESULTS	MATERIAL DESCRIPTION
--------------	----------------------

Optimum moisture = 23.7 %
Maximum dry density = 84.4 pcf

Remarks:


Project No.: 5810860101
Project: TVA - Kingston
Location: Poned Fly Ash
Cell III
Date: July 25, 1995

Tested by: *JCV*
Reviewed by: *RUB*

MOISTURE-DENSITY RELATIONSHIP
LAW ENGINEERING, INC.

Figure No. _____

CONSOLIDATION TEST REPORT

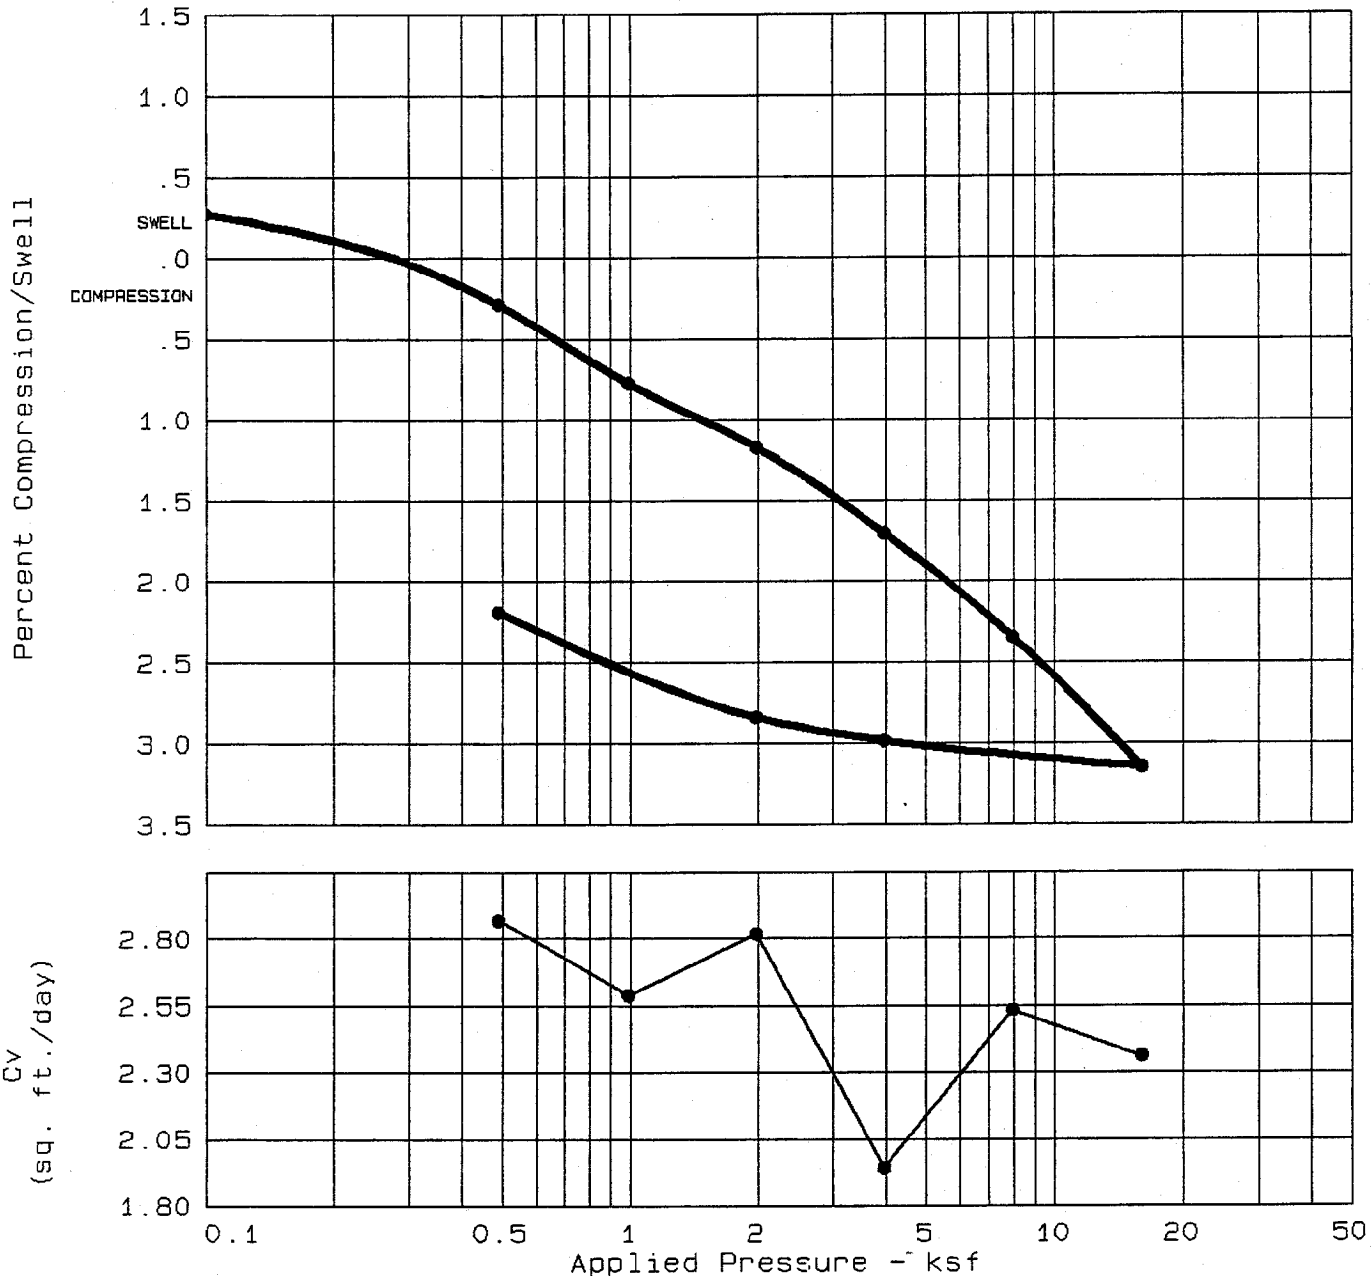

Natural Saturation	Natural Moisture	Dry Density	LL	PI	Sp. Gr.	Precons. press.	Cc	e ₀
66.7 %	25.3	76.9	NL	NP	2.312	1.75	0.05	0.8774

TEST RESULTS	MATERIAL DESCRIPTION
Compression Index = 0.05 Project No.: 5810860101 Project: TVA - Kingston Location: Poned Fly Ash Cell III Date: 6/29/95	Class: USCS: ML Remarks: Tested by: <i>AKK</i> Reviewed by: <i>HS</i>
CONSOLIDATION TEST REPORT LAW ENGINEERING, INC.	Fig. No. _____

HYDRAULIC CONDUCTIVITY



Project No. **5810860101**
Project Name **TVA - Kingston**
Material (Source) **Ponded Fly Ash**
(Cell III)

Tested By **HEJ**
Test Date **06/12/95**
Reviewed By **RLB**
Review Date **09/06/95**

ASTM D5084 - Falling Head

Sample Type:	<i>Remolded</i>
Sample Orientation:	<i>Vertical</i>
Initial Water Content, %:	<i>24.1</i>
Wet Unit Weight, pcf:	<i>94.6</i>
Dry Unit Weight, pcf:	<i>76.2</i>
Compaction, %:	<i>94.1</i>
Hydraulic Conductivity, cm/sec. @20 °C:	3.4E-05

PERMEABILITY TEST - FALLING HEAD (ASTM D5084 - 90)

Job Number 5810860101 Tested By HEJ
 Project Name TVA - Kingston Test Date 06/12/95
 Material (Source) Ponded Fly Ash Reviewed By RLB
 (Cell III) Review Date 09/06/95

Sample Data

Length, in	Diameter, in		Pan No.	
	Location 1	Location 2	Dry Soil+Pan, grams	755.14
Location 1	6.000	2.830	Dry Soil+Pan, grams	755.14
Location 2	6.000	2.830	Pan Weight, grams	0.00
Location 3	6.000	2.830		
Average	6.000	2.830	Moisture Content, %	24.1
			Wet Soil + Tare, grams	936.90
			Tare Weight, grams	0.00
			Wet Unit Wt, pcf	94.6
			Dry Unit Wt, pcf	76.2



Chamber Pressure, psi 39
 Back Pressure, psi 25
 Confining Pressure, psi 14

Date Start	Date Finish	Time Start	Time Finish	Time (sec)	Division Start	Division Finish	H ₀ (cm)	H _r (cm)	k cm/sec	Temp (°C)	k cm/sec at 20 °C
				2062	0.0	22.0	125.08	103.08	3.5E-05	21	3.5E-05
				2384	0.0	25.0	125.08	100.08	3.5E-05	21	3.4E-05
				2185	0.0	23.0	125.08	102.08	3.5E-05	21	3.4E-05

No. of Trial	Sample Type	Max. Density (pcf)	Compaction %	Sample Orientation
3	Remolded	81.0	94.1	Vertical

Avg. k at 20 °C 3.4E-05 cm/sec

a = area of burette in cm² a = 1.00 cm²
 L = length of sample in cm A = 40.582 cm²
 A = area of sample in cm² L = 15.24 cm
 H₀ = initial head in cm
 H_r = final head in cm
 t = time in seconds

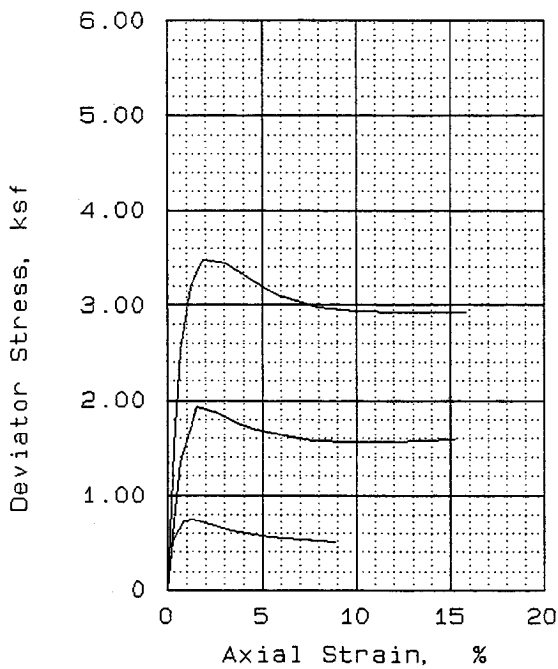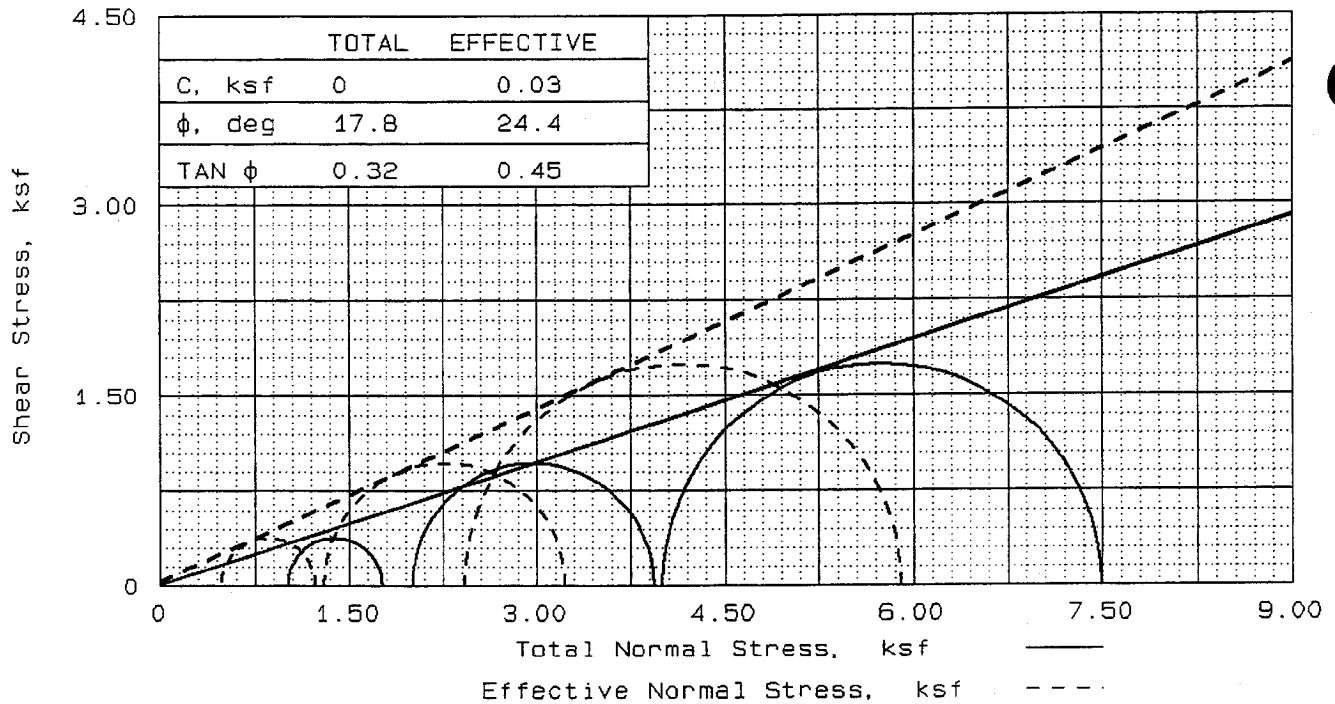



SAMPLE NO.		1	2	3
INITIAL	WATER CONTENT, %	26.7	24.1	25.9
	DRY DENSITY, pcf	74.7	76.2	75.2
	SATURATION, %	66.3	62.3	65.1
	VOID RATIO	0.930	0.892	0.917
	DIAMETER, in	2.83	2.83	2.83
	HEIGHT, in	6.00	6.00	6.00
AT TEST	WATER CONTENT, %	39.6	36.1	38.0
	DRY DENSITY, pcf	75.3	78.6	76.8
	SATURATION, %	100.0	100.0	100.0
	VOID RATIO	0.916	0.835	0.879
	DIAMETER, in	2.82	2.80	2.80
	HEIGHT, in	6.00	5.96	6.00
BACK PRESSURE, ksf		4.41	3.60	3.57
CELL PRESSURE, ksf		5.41	7.60	5.57
FAILURE STRESS, ksf		0.75	3.49	1.93
PORE PRESSURE, ksf		4.94	5.18	4.28
STRAIN RATE, %/min.		0.100	0.100	0.100
ULTIMATE STRESS, ksf				
PORE PRESSURE, ksf				
$\bar{\sigma}_1$ FAILURE, ksf		1.23	5.91	3.23
$\bar{\sigma}_3$ FAILURE, ksf		0.48	2.42	1.3

TYPE OF TEST:
 CU with pore pressures
 SAMPLE TYPE: Remolded
 DESCRIPTION:
 LL= NL PL= NP PI=
 SPECIFIC GRAVITY= 2.31
 REMARKS: Tested by: *HS*




Reviewed by: *RUB*

FIG. NO.

CLIENT:
 PROJECT: TVA - Kingston
 SAMPLE LOCATION: Poned Fly Ash
 Cell III
 PROJ. NO.: 5810860101 DATE: August 28, 1995
 TRIAXIAL COMPRESSION TEST
LAW ENGINEERING, INC.

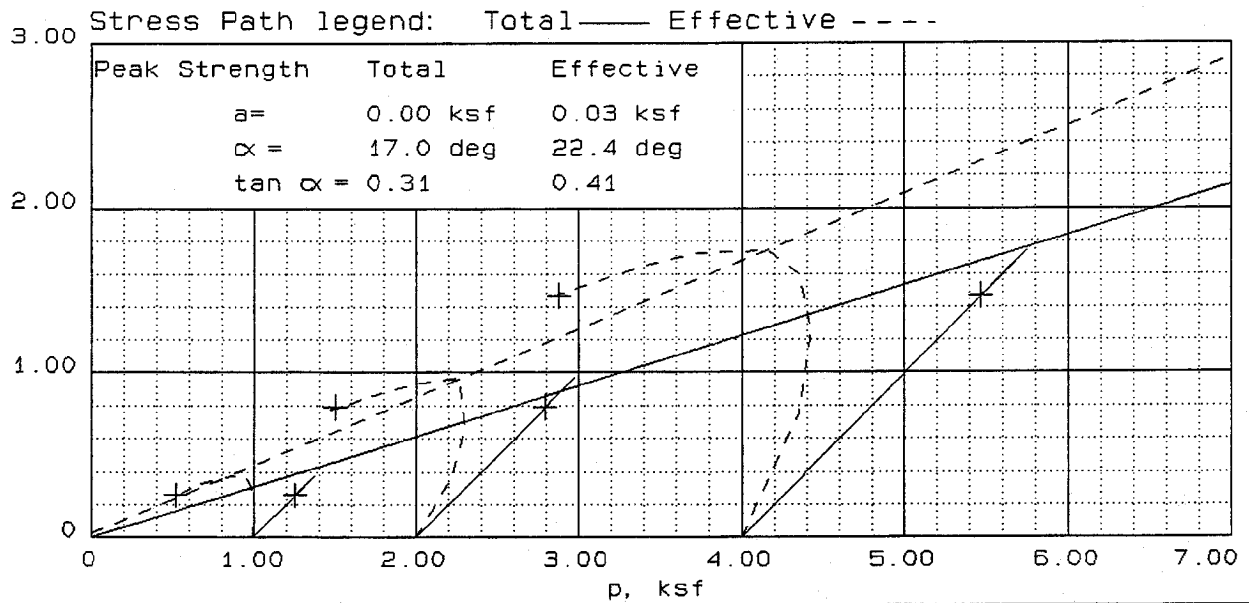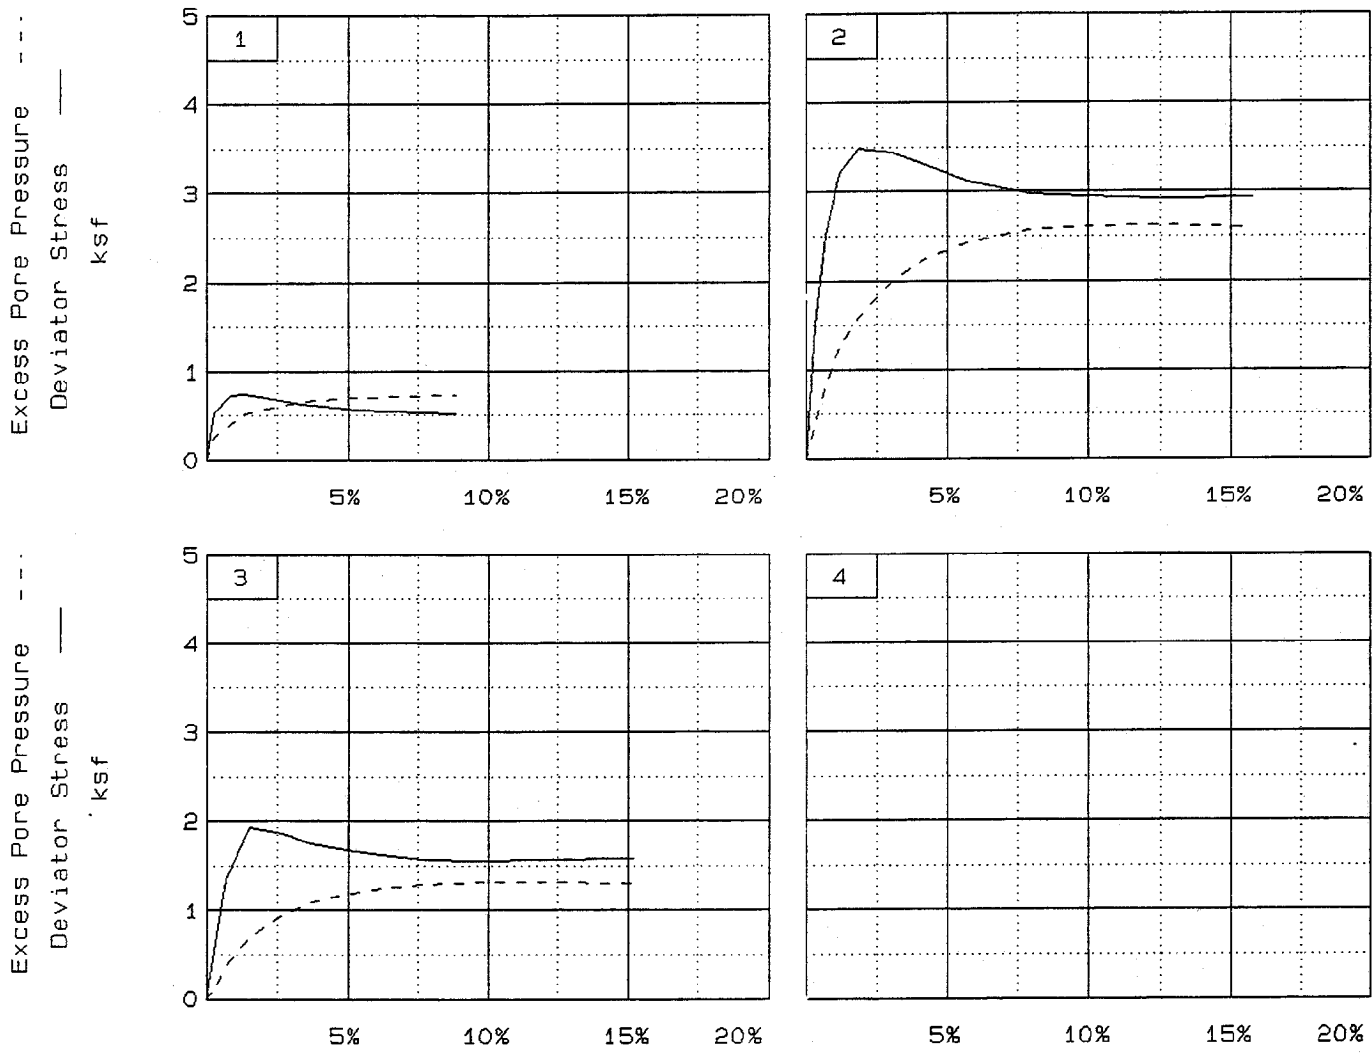

Client:
 Project: TVA - Kingston
 Location: Poned Fly Ash Cell III
 File: 8601N Project No.: 5810860101 Page 2/2 Fig. No. _____

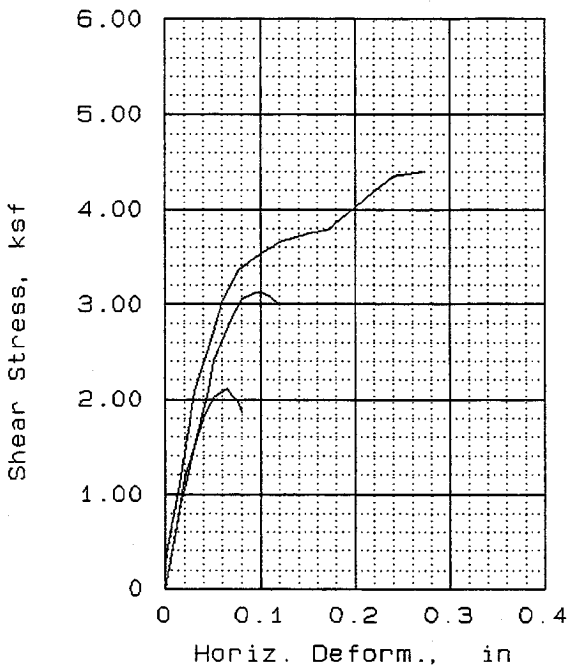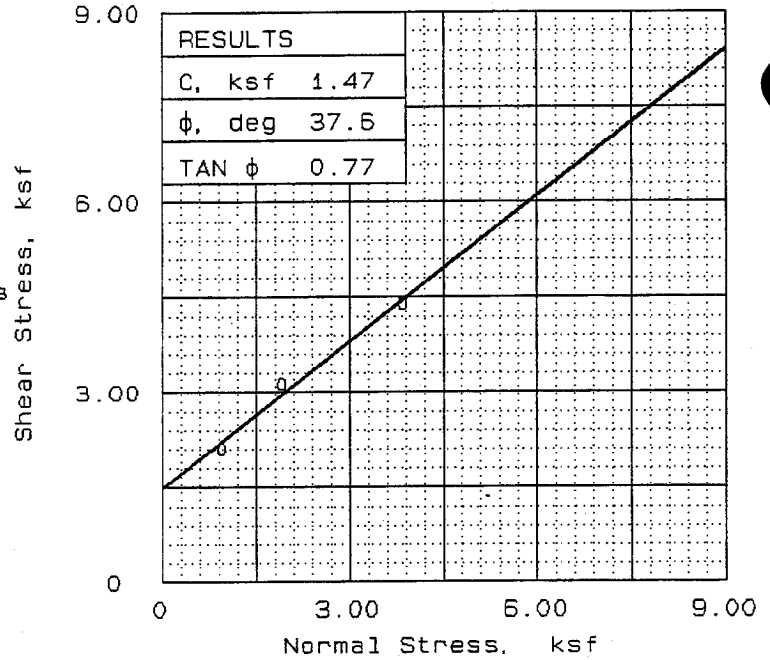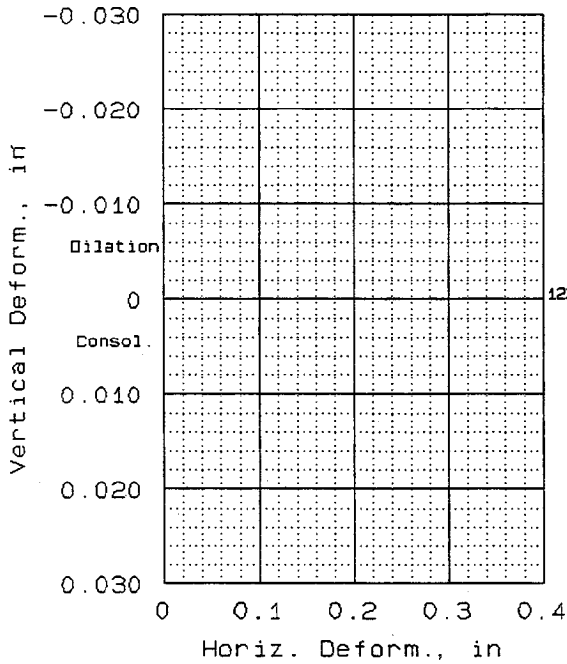

SAMPLE NO.		1	2	3
INITIAL	WATER CONTENT, %	25.0	25.6	25.3
	DRY DENSITY, pcf	75.3	74.4	74.1
	SATURATION, %	63.2	62.9	61.7
	VOID RATIO	0.914	0.939	0.946
	DIAMETER, in	2.50	2.50	2.50
	HEIGHT, in	0.81	0.81	0.81
AT TEST	WATER CONTENT, %	25.0	25.6	25.3
	DRY DENSITY, pcf	75.3	74.4	74.1
	SATURATION, %	63.2	62.9	61.7
	VOID RATIO	0.914	0.939	0.946
	DIAMETER, in	2.50	2.50	2.50
	HEIGHT, in	0.81	0.81	0.81
NORMAL STRESS, ksf		0.97	1.94	3.88
MAX. SHEAR, ksf		2.11	3.13	4.40
STRAIN RATE, %/min.		0.500	0.500	0.500
ULT. SHEAR, ksf				

SAMPLE DATA
 SAMPLE TYPE: Remolded
 DESCRIPTION:
 LL= NL PL= NP PI=
 SPECIFIC GRAVITY= 2.31
 REMARKS: Tested by: *HJ*

Reviewed by: *RUB*

FIG. NO.

CLIENT:

PROJECT: TVA - Kingston

SAMPLE LOCATION: Poned Fly Ash
 Cell III

PROJ. NO.: 5810860101 DATE: 30 August, 1995

DIRECT SHEAR TEST

LAW ENGINEERING, INC.

California Bearing Ratio


(ASTM D1883-92)



Project No. 5810860101
 Project Name TVA - Kingston
 Material (Source) Ponded Fly Ash (Cell III)

Tested By EM
 Test Date 07/31/95
 Reviewed By RLB
 Review Date 08/30/95

Compaction, %	98.1	92.5	94.1
Before Soak Dry Density, pcf	79.4	74.9	76.2
Before Soak Moisture Content,	24.7	21.5	23.1
After Soak Dry Density, pcf	76.3	71.7	72.9
After Soak Moisture Content, %	33.6	37.2	36.7
CBR @ 0.1 in.	1.4	0.5	0.7
CBR @ 0.2 in.	1.7	0.5	0.7

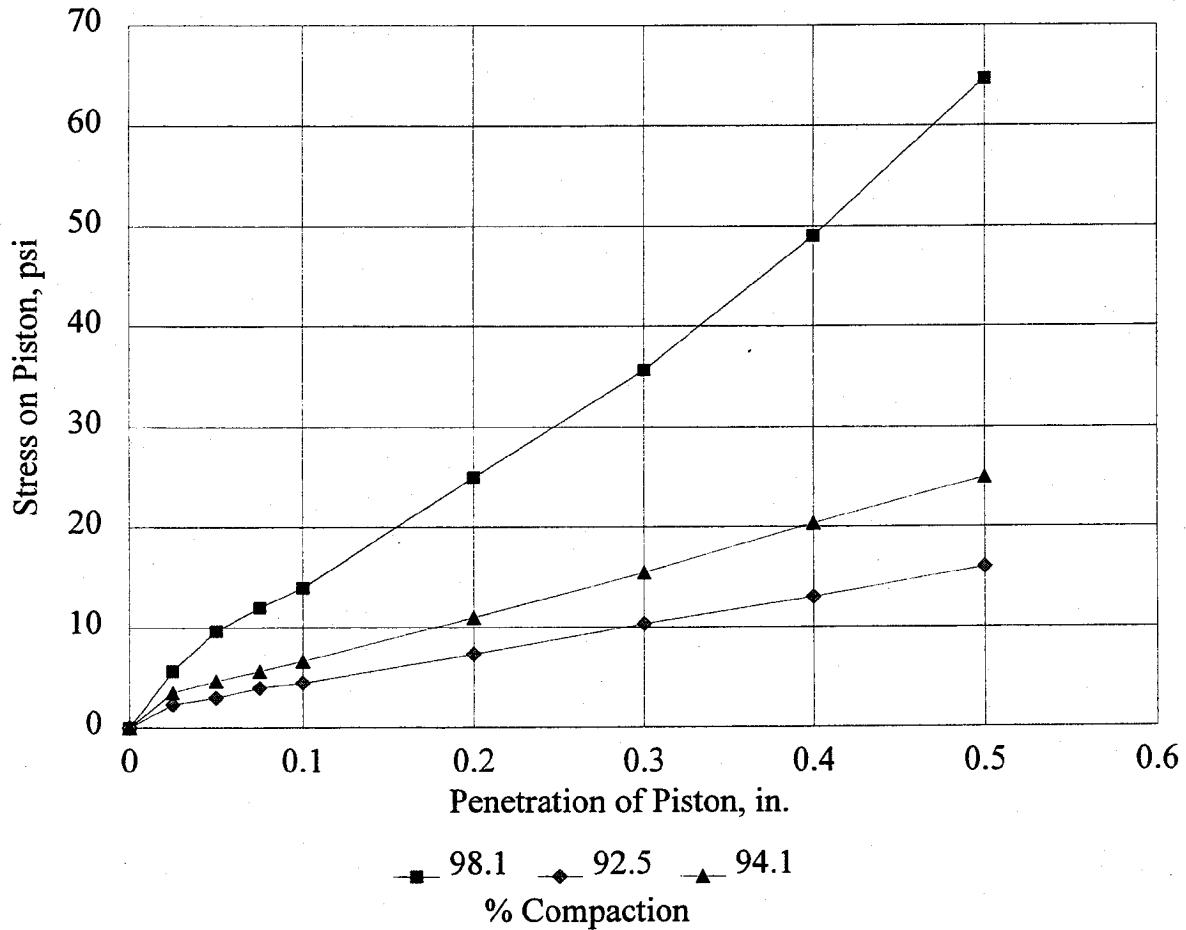

LABORATORY MATERIAL HANDLING AND TESTING
 LABORATORY MATERIAL TEST DATA
 RESILIENT MODULUS OF UNBOUND GRANULAR BASE/SUBBASE
 MATERIALS AND SUBGRADE SOILS
 LAB DATA SHEET T46 - RECOMPACTED SAMPLES

SHEET NO 1 OF 2

UNBOUND GRANULAR BASE/SUBBASE LAYERS AND SUBGRADE SOILS
 SHRP TEST DESIGNATION UG07, SS07/SHRP PROTOCOL P46

LABORATORY PERFORMING TEST: LAW ENGINEERING, INC. - ATLANTA, GEORGIA

PROJECT NAME: TVA - Fly Ash, Bottom Ash and Scrubber Gypsum Study

LAW PROJECT NO.: 5810860101

1.	MATERIAL SOURCE:	Kingston	
2.	MATERIAL DESCRIPTION:	Ponded Fly Ash (Cell III)	
3.	REMODELING TARGETS:	95% Standard Dry Density at Optimum Moisture Content	
4.	MATERIAL TYPE (Type 1 or Type 2)		2
5.	TEST INFORMATION		
	PRECONDITIONING - GREATER THAN 5% PERM. STRAIN? (Y = YES OR N = NO)		N
	TESTING - GREATER THAN 5% PERM. STRAIN? (Y = YES OR N = NO)		N
	TESTING - NUMBER OF LOAD SEQUENCES COMPLETED (0 - 15)		15
6.	SPECIMEN INFO.:		
	SPECIMEN DIAM., inch		
	TOP		2.85
	MIDDLE		2.85
	BOTTOM		2.86
	AVERAGE		2.85
	MEMBRANE THICKNESS (1), inch		0.01
	MEMBRANE THICKNESS (2), inch		0.01
	NET DIAM., inch		2.83
	HEIGHT OF SPECIMEN, CAP AND BASE, inch		6.09
	HEIGHT OF CAP AND BASE, inch		0.00
	INITIAL LENGTH, L ₀ , inch		6.09
	INITIAL AREA, A ₀ , in ²		6.28
	INITIAL VOLUME A ₀ L ₀ , in ³		38.26
7.	SOIL SPECIMEN WEIGHT:		
	INITIAL WEIGHT OF CONTAINER AND WET SOIL, grams		937.95
	FINAL WEIGHT OF CONTAINER AND WET SOIL, grams		0.00
	WEIGHT OF WET SOIL USED, grams		937.95
8.	SOIL PROPERTIES.:		
	IN SITU MOISTURE CONTENT (NUCLEAR), %		N/A
	IN SITU WET DENSITY (NUCLEAR), pcf		N/A
	or		
	OPTIMUM MOISTURE CONTENT, %		23.5
	MAX. DRY DENSITY, pcf		81.0
	95 % MAX. DRY DENSITY, pcf		77.0
9.	SPECIMEN PROPERTIES:		
	COMPACTION MOISTURE CONTENT, %		25.4
	MOISTURE CONTENT AFTER RESILIENT MODULUS TESTING, %		25.4
	COMPACTION DRY DENSITY, γ _d pcf		74.4
10.	QUICK SHEAR TEST		
	STRESS - STRAIN PLOT ATTACHED (Y = YES, N = NO)		Y
	TRIAxIAL SHEAR MAXIMUM STRENGTH (MAX. LOAD/X-SECTION AREA), psi		24.6
	SPECIMEN FAIL DURING TRIAXIAL SHEAR? (Y = YES, N = NO)		Y
11.	COMMENTS (Section 10.4 of Protocol P46)		
	(a) CODE	0	0
	(b) NOTE	0	0
12.	TEST DATE		08-04-1995

GENERAL REMARKS:

SUBMITTED BY, DATE

RT Bandman 9/10/95
 LABORATORY MANAGER

PROJECT NAME: TVA - Fly Ash, Bottom Ash and Scrubber Gypsum Study
 LAW PROJECT NO.: 5810860101
 MATERIAL SOURCE: Kingston
 MATERIAL DESCRIPTION: Ponded Fly Ash (Cell III)
 REMOLDING TARGETS: 95% Standard Dry Density at Optimum Moisture Content
 MATERIAL TYPE: 2
 TEST DATE: 08-04-1995
 RESILIENT MODULUS TESTING

COLUMN #	1	2	3	4	5	6	7	8	9	10	11	12	13	14
PARAMETER	Chamber Confining Pressure	Nominal Maximum Axial Stress	Cycle No.	Actual Applied Max. Axial Load	Actual Applied Cyclic Load	Actual Applied Contact Load	Actual Applied Max. Axial Stress	Actual Applied Cyclic Stress	Actual Applied Contact Stress	Recov. Def. LVDT #1 Reading	Recov. Def. LVDT #2 Reading	Average Recov Def. LVDT 1 and 2	Resilient Strain	Resilient Modulus
DESIGNATION	S ₃	S _{cyclic}	C ₁	P _{max}	P _{cyclic}	P _{contact}	S _{max}	S _{cyclic}	S _{contact}	H ₁	H ₂	H _{avg}	ε _r	M _r
UNIT	psi	psi	---	lbs	lbs	lbs	psi	psi	psi	in.	in.	in.	in/in	psi
PRECISION														
SEQUENCE 1	6.0	2.0	1	12.6	11.4	1.2	2.0	1.8	0.2	0.00174	0.00177	0.00176	0.00029	6,297
			2	12.8	11.6	1.2	2.0	1.8	0.2	0.00175	0.00178	0.00177	0.00029	6,379
			3	12.7	11.5	1.2	2.0	1.8	0.2	0.00177	0.00178	0.00178	0.00029	6,274
			4	12.7	11.5	1.2	2.0	1.8	0.2	0.00173	0.00177	0.00175	0.00029	6,360
			5	12.8	11.6	1.2	2.0	1.8	0.2	0.00176	0.00178	0.00177	0.00029	6,328
COLUMN AVERAGE				12.7	11.5	1.2	2.0	1.8	0.2	0.00175	0.00178	0.00176	0.00029	6,328
STANDARD DEV.				0.1	0.1	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00001	0.00000	44

Source: Kingston	Description: Poned Fly Ash (Cell III)					95% Standard Dry Density at Optimum Moisture Content								
SEQUENCE 2	6.0	4.0	1	25.3	22.9	2.4	4.0	3.6	0.4	0.00366	0.00372	0.00369	0.00061	6,010
			2	25.1	22.7	2.4	4.0	3.6	0.4	0.00367	0.00372	0.00369	0.00061	5,969
			3	25.1	22.8	2.4	4.0	3.6	0.4	0.00365	0.00370	0.00368	0.00060	5,998
			4	25.2	22.8	2.4	4.0	3.6	0.4	0.00367	0.00371	0.00369	0.00061	5,990
			5	25.1	22.8	2.4	4.0	3.6	0.4	0.00367	0.00371	0.00369	0.00061	5,974
	COLUMN AVERAGE			25.2	22.8	2.4	4.0	3.6	0.4	0.00366	0.00371	0.00369	0.00061	5,988
	STANDARD DEV.			0.1	0.1	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00001	0.00000	17
SEQUENCE 3	6.0	6.0	1	37.7	34.1	3.6	6.0	5.4	0.6	0.00588	0.00596	0.00592	0.00097	5,575
			2	37.6	34.0	3.6	6.0	5.4	0.6	0.00589	0.00596	0.00592	0.00097	5,564
			3	37.6	34.0	3.6	6.0	5.4	0.6	0.00590	0.00594	0.00592	0.00097	5,558
			4	37.6	34.0	3.6	6.0	5.4	0.6	0.00588	0.00595	0.00591	0.00097	5,576
			5	37.6	34.0	3.6	6.0	5.4	0.6	0.00588	0.00596	0.00592	0.00097	5,571
	COLUMN AVERAGE			37.6	34.0	3.6	6.0	5.4	0.6	0.00589	0.00595	0.00592	0.00097	5,569
	STANDARD DEV.			0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00000	0.00000	8
SEQUENCE 4	6.0	8.0	1	50.3	45.5	4.8	8.0	7.2	0.8	0.00815	0.00824	0.00819	0.00135	5,381
			2	50.2	45.5	4.7	8.0	7.2	0.8	0.00815	0.00826	0.00821	0.00135	5,367
			3	50.2	45.4	4.8	8.0	7.2	0.8	0.00815	0.00826	0.00821	0.00135	5,363
			4	50.3	45.5	4.8	8.0	7.2	0.8	0.00813	0.00824	0.00819	0.00134	5,382
			5	50.4	45.6	4.7	8.0	7.3	0.8	0.00815	0.00828	0.00822	0.00135	5,382
	COLUMN AVERAGE			50.3	45.5	4.8	8.0	7.2	0.8	0.00815	0.00826	0.00820	0.00135	5,375
	STANDARD DEV.			0.1	0.1	0.0	0.0	0.0	0.0	0.00001	0.00002	0.00001	0.00000	9

Source: Kingston	Description: Poned Fly Ash (Cell III)	95% Standard Dry Density at Optimum Moisture Content												
SEQUENCE 5	6.0	10.0	1	62.7	56.7	6.1	10.0	9.0	1.0	0.01027	0.01040	0.01034	0.00170	5,312
			2	62.7	56.6	6.0	10.0	9.0	1.0	0.01027	0.01041	0.01034	0.00170	5,304
			3	62.8	56.8	6.0	10.0	9.0	1.0	0.01025	0.01040	0.01033	0.00170	5,326
			4	62.7	56.7	6.1	10.0	9.0	1.0	0.01026	0.01039	0.01032	0.00170	5,318
			5	62.7	56.7	6.0	10.0	9.0	1.0	0.01025	0.01040	0.01033	0.00170	5,317
	COLUMN AVERAGE		62.7	56.7	6.1	10.0	9.0	1.0	0.01026	0.01040	0.01033	0.00170	5,316	
	STANDARD DEV.		0.1	0.1	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00001	0.00000	8	
SEQUENCE 6	4.0	2.0	1	13.0	11.3	1.7	2.1	1.8	0.3	0.00199	0.00205	0.00202	0.00033	5,416
			2	13.1	11.4	1.7	2.1	1.8	0.3	0.00197	0.00205	0.00201	0.00033	5,490
			3	13.0	11.3	1.7	2.1	1.8	0.3	0.00199	0.00204	0.00202	0.00033	5,429
			4	13.0	11.3	1.7	2.1	1.8	0.3	0.00199	0.00203	0.00201	0.00033	5,448
			5	13.1	11.4	1.7	2.1	1.8	0.3	0.00199	0.00205	0.00202	0.00033	5,455
	COLUMN AVERAGE		13.0	11.3	1.7	2.1	1.8	0.3	0.00199	0.00204	0.00202	0.00033	5,448	
	STANDARD DEV.		0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00000	0.00000	28	
SEQUENCE 7	4.0	4.0	1	24.9	22.6	2.3	4.0	3.6	0.4	0.00474	0.00482	0.00478	0.00079	4,572
			2	24.9	22.6	2.3	4.0	3.6	0.4	0.00474	0.00482	0.00478	0.00079	4,573
			3	24.9	22.6	2.3	4.0	3.6	0.4	0.00474	0.00483	0.00479	0.00079	4,572
			4	24.9	22.5	2.3	4.0	3.6	0.4	0.00475	0.00483	0.00479	0.00079	4,560
			5	24.8	22.5	2.3	4.0	3.6	0.4	0.00474	0.00483	0.00479	0.00079	4,550
	COLUMN AVERAGE		24.9	22.5	2.3	4.0	3.6	0.4	0.00474	0.00483	0.00479	0.00079	4,565	
	STANDARD DEV.		0.0	0.0	0.0	0.0	0.0	0.0	0.00000	0.00000	0.00000	0.00000	10	

Source:	Kingston	Description:	Ponded Fly Ash (Cell III)	95% Standard Dry Density at Optimum Moisture Content										
SEQUENCE 8	4.0	6.0	1	37.3	33.7	3.6	5.9	5.4	0.6	0.00760	0.00772	0.00766	0.00126	4,262
			2	37.4	33.8	3.6	5.9	5.4	0.6	0.00761	0.00772	0.00766	0.00126	4,272
			3	37.4	33.9	3.6	6.0	5.4	0.6	0.00760	0.00773	0.00766	0.00126	4,282
			4	37.4	33.8	3.6	5.9	5.4	0.6	0.00761	0.00772	0.00766	0.00126	4,276
			5	37.4	33.8	3.6	6.0	5.4	0.6	0.00761	0.00772	0.00766	0.00126	4,277
				37.4	33.8	3.6	5.9	5.4	0.6	0.00760	0.00772	0.00766	0.00126	4,274
				0.1	0.1	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00000	0.00000	8
SEQUENCE 9	4.0	8.0	1	50.1	45.3	4.8	8.0	7.2	0.8	0.01002	0.01017	0.01009	0.00166	4,348
			2	50.0	45.2	4.8	8.0	7.2	0.8	0.01004	0.01017	0.01010	0.00166	4,337
			3	49.9	45.1	4.8	7.9	7.2	0.8	0.01002	0.01017	0.01010	0.00166	4,330
			4	49.9	45.1	4.8	7.9	7.2	0.8	0.01002	0.01016	0.01009	0.00166	4,328
			5	49.9	45.1	4.8	7.9	7.2	0.8	0.01002	0.01016	0.01009	0.00166	4,332
				50.0	45.2	4.8	8.0	7.2	0.8	0.01003	0.01016	0.01009	0.00166	4,335
				0.1	0.1	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00001	0.00000	8
SEQUENCE 10	4.0	10.0	1	62.3	56.3	6.0	9.9	9.0	1.0	0.01200	0.01214	0.01207	0.00198	4,520
			2	62.3	56.3	6.0	9.9	9.0	1.0	0.01198	0.01214	0.01206	0.00198	4,522
			3	62.4	56.3	6.0	9.9	9.0	1.0	0.01199	0.01214	0.01206	0.00198	4,523
			4	62.3	56.3	6.0	9.9	9.0	1.0	0.01198	0.01215	0.01206	0.00198	4,522
			5	62.4	56.3	6.0	9.9	9.0	1.0	0.01198	0.01215	0.01207	0.00198	4,525
				62.3	56.3	6.0	9.9	9.0	1.0	0.01199	0.01215	0.01207	0.00198	4,522
				0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00000	0.00000	2

Source:	Kingston	Description:	Ponded Fly Ash (Cell III)	95% Standard Dry Density at Optimum Moisture Content										
SEQUENCE 11	2.0	2.0	1	13.4	11.2	2.1	2.1	1.8	0.3	0.00245	0.00253	0.00249	0.00041	4,381
			2	13.4	11.3	2.1	2.1	1.8	0.3	0.00246	0.00254	0.00250	0.00041	4,361
			3	13.4	11.3	2.1	2.1	1.8	0.3	0.00246	0.00251	0.00249	0.00041	4,383
			4	13.4	11.3	2.1	2.1	1.8	0.3	0.00246	0.00254	0.00250	0.00041	4,364
			5	13.4	11.3	2.1	2.1	1.8	0.3	0.00247	0.00253	0.00250	0.00041	4,373
		COLUMN AVERAGE	13.4	11.3	2.1	2.1	1.8	0.3	0.00246	0.00253	0.00250	0.00041	4,372	
		STANDARD DEV.	0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00001	0.00000	10	
SEQUENCE 12	2.0	4.0	1	24.4	22.1	2.4	3.9	3.5	0.4	0.00589	0.00602	0.00596	0.00098	3,586
			2	24.4	22.0	2.4	3.9	3.5	0.4	0.00591	0.00600	0.00595	0.00098	3,582
			3	24.4	22.0	2.4	3.9	3.5	0.4	0.00590	0.00601	0.00596	0.00098	3,587
			4	24.4	22.0	2.4	3.9	3.5	0.4	0.00591	0.00600	0.00595	0.00098	3,588
			5	24.4	22.0	2.4	3.9	3.5	0.4	0.00590	0.00601	0.00596	0.00098	3,584
		COLUMN AVERAGE	24.4	22.0	2.4	3.9	3.5	0.4	0.00590	0.00601	0.00595	0.00098	3,585	
		STANDARD DEV.	0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00000	0.00000	2	
SEQUENCE 13	2.0	6.0	1	36.6	33.0	3.6	5.8	5.3	0.6	0.00925	0.00940	0.00933	0.00153	3,432
			2	36.7	33.1	3.6	5.8	5.3	0.6	0.00928	0.00938	0.00933	0.00153	3,439
			3	36.6	33.0	3.6	5.8	5.3	0.6	0.00927	0.00939	0.00933	0.00153	3,429
			4	36.6	33.0	3.6	5.8	5.2	0.6	0.00926	0.00939	0.00933	0.00153	3,427
			5	36.6	33.0	3.6	5.8	5.2	0.6	0.00926	0.00939	0.00932	0.00153	3,426
		COLUMN AVERAGE	36.6	33.0	3.6	5.8	5.3	0.6	0.00926	0.00939	0.00933	0.00153	3,431	
		STANDARD DEV.	0.1	0.1	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00000	0.00000	5	

Source:	Kingston	Description:	Ponded Fly Ash (Cell III)	95% Standard Dry Density at Optimum Moisture Content										
SEQUENCE 14	2.0	8.0	1	49.5	44.6	4.9	7.9	7.1	0.8	0.01182	0.01196	0.01189	0.00195	3,639
			2	49.5	44.6	4.9	7.9	7.1	0.8	0.01182	0.01194	0.01188	0.00195	3,637
			3	49.5	44.6	4.8	7.9	7.1	0.8	0.01182	0.01194	0.01188	0.00195	3,638
			4	49.5	44.6	4.8	7.9	7.1	0.8	0.01180	0.01196	0.01188	0.00195	3,639
			5	49.4	44.5	4.8	7.9	7.1	0.8	0.01181	0.01197	0.01189	0.00195	3,630
				49.5	44.6	4.9	7.9	7.1	0.8	0.01181	0.01195	0.01188	0.00195	3,637
				0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00000	0.00000	4
SEQUENCE 15	2.0	10.0	1	62.5	56.4	6.1	9.9	9.0	1.0	0.01381	0.01399	0.01390	0.00228	3,930
			2	62.4	56.3	6.1	9.9	9.0	1.0	0.01381	0.01400	0.01391	0.00228	3,923
			3	62.3	56.2	6.1	9.9	8.9	1.0	0.01380	0.01398	0.01389	0.00228	3,924
			4	62.4	56.3	6.1	9.9	9.0	1.0	0.01380	0.01397	0.01388	0.00228	3,930
			5	62.5	56.4	6.1	9.9	9.0	1.0	0.01381	0.01398	0.01390	0.00228	3,933
				62.4	56.3	6.1	9.9	9.0	1.0	0.01381	0.01399	0.01390	0.00228	3,928
				0.1	0.1	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00001	0.00000	4

SUBMITTED BY, DATE

RP Buchanan 9/10/95

LABORATORY MANAGER

FIGURE 1 - Logarithmic Plot of Resilient Modulus (M_R) vs Cyclic Stress (S_C)

PROJECT NAME: TVA - Fly Ash, Bottom Ash and Scrubber Gypsum Study
 LAW PROJECT NO.: 5810860101
 1. MATERIAL SOURCE: Kingston
 2. MATERIAL DESCRIPTION: Ponded Fly Ash (Cell III)
 3. REMOLDING TARGETS: 95% Standard Dry Density at Optimum Moisture Content
 4. MATERIAL TYPE: 2
 5. TEST DATE: 08-04-1995

$$M_R = K1 (S_C)^{K2} (1+S_3)^{K5}$$

$K1 = \underline{\quad 2,592 \quad}$
 $K2 = \underline{\quad -0.10787 \quad}$
 $K5 = \underline{\quad 0.48134 \quad}$
 $R^2 = \underline{\quad 0.91 \quad}$


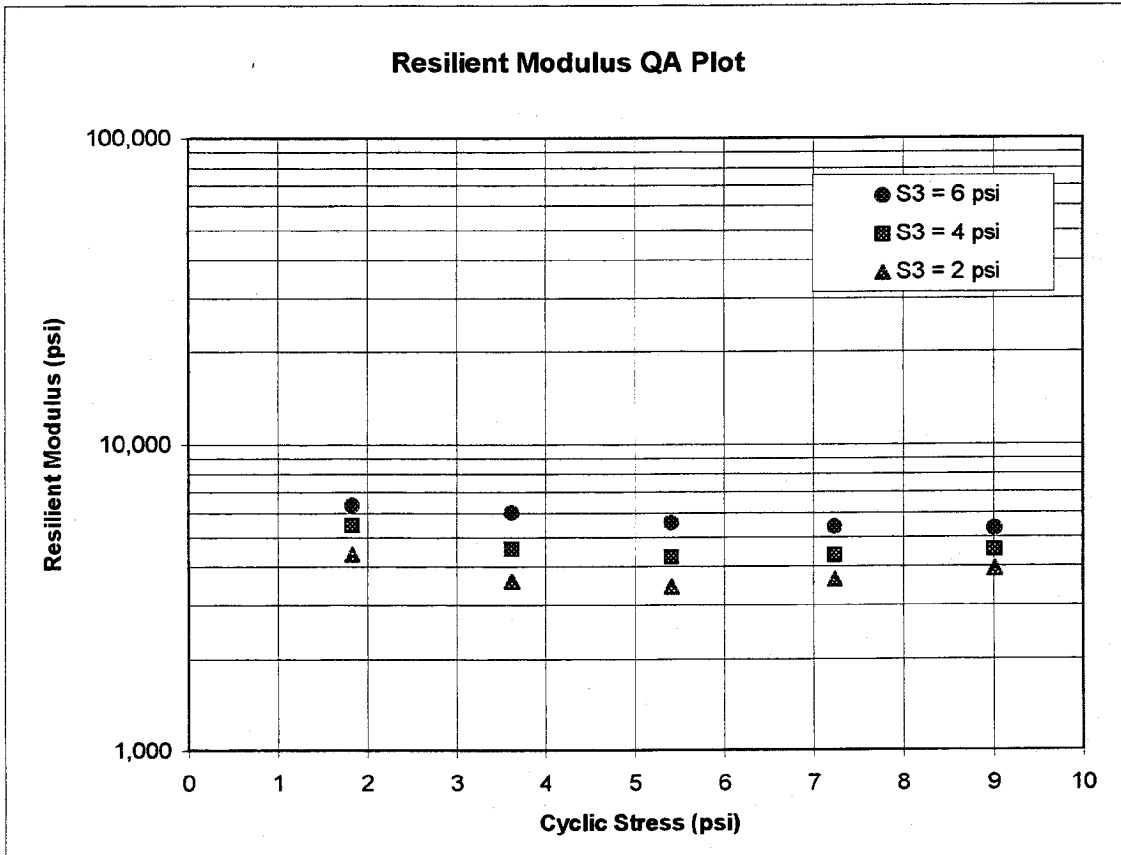


FIGURE 2 - Quick Shear Stress vs Strain

PROJECT NAME: TVA - Fly Ash, Bottom Ash and Scrubber Gypsum Study
LAW PROJECT NO.: 5810860101
1. *MATERIAL SOURCE:* Kingston
2. *MATERIAL DESCRIPTION:* Ponded Fly Ash (Cell III)
3. *REMOLDING TARGETS:* 95% Standard Dry Density at Optimum Moisture Content
4. *MATERIAL TYPE* 2
5. *TEST DATE* 08-04-1995

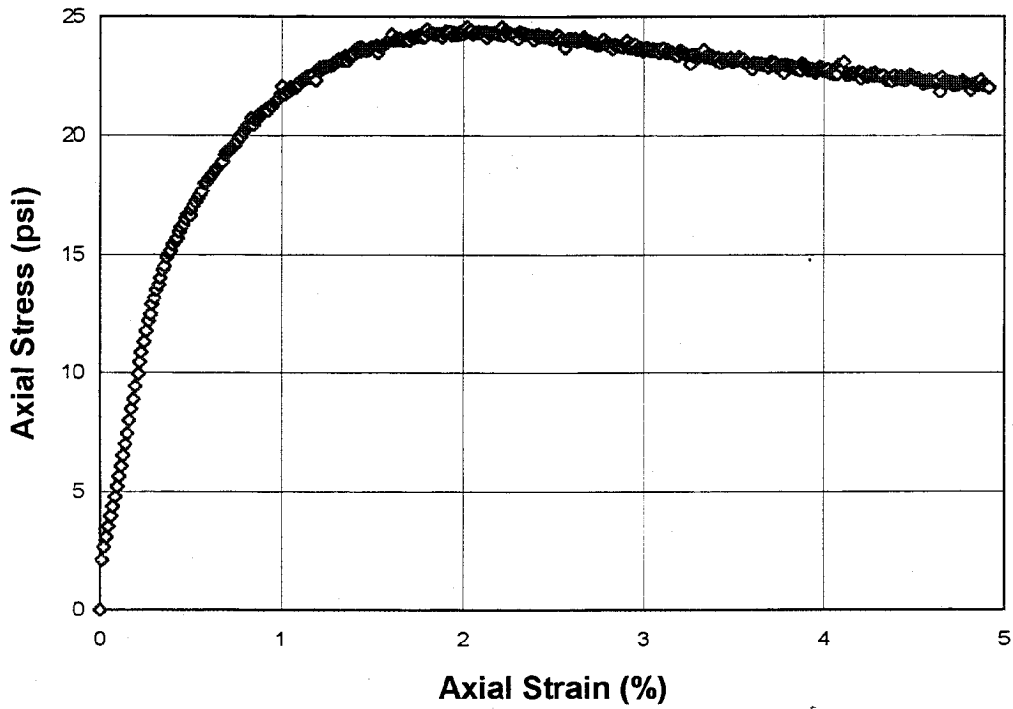

LABORATORY MATERIAL HANDLING AND TESTING
LABORATORY MATERIAL TEST DATA
RESILIENT MODULUS OF UNBOUND GRANULAR BASE/SUBBASE
MATERIALS AND SUBGRADE SOILS
LAB DATA SHEET T46 - RECOMPACTED SAMPLES

SHEET NO 1 OF 2

UNBOUND GRANULAR BASE/SUBBASE LAYERS AND SUBGRADE SOILS
SHRP TEST DESIGNATION UG07, SS07/SHRP PROTOCOL P46

LABORATORY PERFORMING TEST: LAW ENGINEERING, INC. - ATLANTA, GEORGIA

PROJECT NAME: TVA - Fly Ash, Bottom Ash and Scrubber Gypsum Study

LAW PROJECT NO.: 5810860101

1.	MATERIAL SOURCE:	Kingston		
2.	MATERIAL DESCRIPTION:	Ponded Fly Ash (Cell III)		
3.	REMOULDING TARGETS:	95% Modified Dry Density at Optimum Moisture Content		
4.	MATERIAL TYPE (Type 1 or Type 2)			2
5.	TEST INFORMATION			
	PRECONDITIONING - GREATER THAN 5% PERM. STRAIN? (Y = YES OR N = NO)			N
	TESTING - GREATER THAN 5% PERM. STRAIN? (Y = YES OR N = NO)			N
	TESTING - NUMBER OF LOAD SEQUENCES COMPLETED (0 - 15)			15
6.	SPECIMEN INFO.:			
	SPECIMEN DIAM., inch			
	TOP			2.83
	MIDDLE			2.83
	BOTTOM			2.83
	AVERAGE			2.83
	MEMBRANE THICKNESS (1), inch			0.01
	MEMBRANE THICKNESS (2), inch			0.01
	NET DIAM., inch			2.81
	HEIGHT OF SPECIMEN, CAP AND BASE, inch			6.14
	HEIGHT OF CAP AND BASE, inch			0.00
	INITIAL LENGTH, L ₀ , inch			6.14
	INITIAL AREA, A ₀ , in ²			6.19
	INITIAL VOLUME A ₀ L ₀ , in ³			38.01
7.	SOIL SPECIMEN WEIGHT:			
	INITIAL WEIGHT OF CONTAINER AND WET SOIL, grams			997.40
	FINAL WEIGHT OF CONTAINER AND WET SOIL, grams			0.00
	WEIGHT OF WET SOIL USED, grams			997.40
8.	SOIL PROPERTIES.:			
	IN SITU MOISTURE CONTENT (NUCLEAR), %			N/A
	IN SITU WET DENSITY (NUCLEAR), pcf			N/A
	or			
	OPTIMUM MOISTURE CONTENT, %			23.7
	MAX. DRY DENSITY, pcf			84.4
	95 % MAX. DRY DENSITY, pcf			80.2
9.	SPECIMEN PROPERTIES:			
	COMPACTION MOISTURE CONTENT, %			23.9
	MOISTURE CONTENT AFTER RESILIENT MODULUS TESTING, %			23.5
	COMPACTION DRY DENSITY, γ _d pcf			80.6
10.	QUICK SHEAR TEST			
	STRESS - STRAIN PLOT ATTACHED (Y = YES, N = NO)			Y
	TRIAXIAL SHEAR MAXIMUM STRENGTH (MAX. LOAD/X-SECTION AREA), psi			38.1
	SPECIMEN FAIL DURING TRIAXIAL SHEAR? (Y = YES, N = NO)			Y
11.	COMMENTS (Section 10.4 of Protocol P46)			
	(a) CODE	0	0	0
	(b) NOTE	0	0	0
12.	TEST DATE			07-06-1995

GENERAL REMARKS:

SUBMITTED BY, DATE

RJ Buchanan 9/5/95
LABORATORY MANAGER

PROJECT NAME: TVA - Fly Ash, Bottom Ash and Scrubber Gypsum Study
 LAW PROJECT NO.: 5810860101
 MATERIAL SOURCE: Kingston
 MATERIAL DESCRIPTION: Ponded Fly Ash (Cell III)
 REMOLDING TARGETS: 95% Modified Dry Density at Optimum Moisture Content
 MATERIAL TYPE: 2
 TEST DATE: 07-06-1995
 RESILIENT MODULUS TESTING

COLUMN #	1	2	3	4	5	6	7	8	9	10	11	12	13	14
PARAMETER	Chamber Confining Pressure	Nominal Maximum Axial Stress	Cycle No.	Actual Applied Max. Axial Load	Actual Applied Cyclic Load	Actual Applied Contact Load	Actual Applied Max. Axial Stress	Actual Applied Cyclic Stress	Actual Applied Contact Stress	Recov. Def. LVDT #1 Reading	Recov. Def. LVDT #2 Reading	Average Recov Def. LVDT 1 and 2	Resilient Strain	Resilient Modulus
DESIGNATION	S ₃	S _{cyclic}	C ₁	P _{max}	P _{cyclic}	P _{contact}	S _{max}	S _{cyclic}	S _{contact}	H ₁	H ₂	H _{avg}	ε	
UNIT	psi	psi	---	lbs	lbs	lbs	psi	psi	psi	in.	in.	in.	in/in	psi
PRECISION														
SEQUENCE 1	6.0	2.0	1	12.4	11.2	1.3	2.0	1.8	0.2	0.00147	0.00161	0.00154	0.00025	7,180
			2	12.4	11.1	1.3	2.0	1.8	0.2	0.00148	0.00162	0.00155	0.00025	7,092
			3	12.3	11.1	1.2	2.0	1.8	0.2	0.00150	0.00164	0.00157	0.00026	7,019
			4	12.4	11.2	1.2	2.0	1.8	0.2	0.00147	0.00162	0.00154	0.00025	7,199
			5	12.4	11.1	1.2	2.0	1.8	0.2	0.00151	0.00163	0.00157	0.00026	7,035
	COLUMN AVERAGE			12.4	11.1	1.2	2.0	1.8	0.2	0.00149	0.00163	0.00156	0.00025	7,105
	STANDARD DEV.			0.0	0.0	0.0	0.0	0.0	0.0	0.00002	0.00001	0.00001	0.00000	82

Source: Kingston		Description: Poned Fly Ash (Cell III)										95% Modified Dry Density at Optimum Moisture Content									
SEQUENCE 2	6.0	4.0	1	24.7	22.4	2.3	4.0	3.6	0.4	0.00317	0.00321	0.00319	0.00052	6.958							
			2	24.7	22.4	2.4	4.0	3.6	0.4	0.00317	0.00324	0.00321	0.00052	6.926							
			3	24.8	22.4	2.4	4.0	3.6	0.4	0.00320	0.00323	0.00321	0.00052	6.917							
			4	24.7	22.4	2.3	4.0	3.6	0.4	0.00318	0.00322	0.00320	0.00052	6.929							
			5	24.7	22.4	2.3	4.0	3.6	0.4	0.00319	0.00323	0.00321	0.00052	6.918							
	COLUMN AVERAGE		24.7	22.4	2.3	4.0	3.6	0.4	0.00318	0.00323	0.00320	0.00052	6.930								
	STANDARD DEV.		0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00000	0.00000	17							
SEQUENCE 3	6.0	6.0	1	37.0	33.3	3.6	6.0	5.4	0.6	0.00499	0.00503	0.00501	0.00082	6.594							
			2	36.9	33.3	3.6	6.0	5.4	0.6	0.00501	0.00505	0.00503	0.00082	6.560							
			3	36.9	33.3	3.7	6.0	5.4	0.6	0.00502	0.00505	0.00504	0.00082	6.551							
			4	37.0	33.3	3.7	6.0	5.4	0.6	0.00500	0.00504	0.00502	0.00082	6.581							
			5	37.0	33.3	3.7	6.0	5.4	0.6	0.00500	0.00506	0.00503	0.00082	6.572							
	COLUMN AVERAGE		37.0	33.3	3.7	6.0	5.4	0.6	0.00500	0.00505	0.00503	0.00082	6.572								
	STANDARD DEV.		0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00000	0.00000	17							
SEQUENCE 4	6.0	8.0	1	49.5	44.6	4.9	8.0	7.2	0.8	0.00701	0.00700	0.00701	0.00114	6.320							
			2	49.5	44.6	4.9	8.0	7.2	0.8	0.00697	0.00698	0.00697	0.00114	6.348							
			3	49.6	44.7	4.9	8.0	7.2	0.8	0.00700	0.00701	0.00700	0.00114	6.331							
			4	49.6	44.7	4.9	8.0	7.2	0.8	0.00701	0.00701	0.00701	0.00114	6.321							
			5	49.5	44.7	4.9	8.0	7.2	0.8	0.00700	0.00701	0.00701	0.00114	6.320							
	COLUMN AVERAGE		49.5	44.7	4.9	8.0	7.2	0.8	0.00700	0.00700	0.00700	0.00114	6.328								
	STANDARD DEV.		0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.00002	0.00001	0.00002	0.00000	12							

Source:	Kingston	Description:	Ponded Fly Ash (Cell III)	95% Modified Dry Density at Optimum Moisture Content											
SEQUENCE 5	6.0	10.0	1	62.1	56.0	6.1	10.0	9.1	1.0	0.00885	0.00885	0.00885	0.00885	0.00144	6,278
			2	62.1	56.0	6.1	10.0	9.0	1.0	0.00884	0.00886	0.00885	0.00885	0.00144	6,272
			3	62.1	56.0	6.1	10.0	9.0	1.0	0.00882	0.00886	0.00884	0.00884	0.00144	6,281
			4	62.1	56.0	6.1	10.0	9.0	1.0	0.00881	0.00886	0.00883	0.00883	0.00144	6,286
			5	62.1	56.0	6.1	10.0	9.0	1.0	0.00886	0.00884	0.00885	0.00885	0.00144	6,270
		COLUMN AVERAGE	62.1	56.0	6.1	10.0	9.0	1.0	0.00884	0.00885	0.00885	0.00885	0.00144	6,277	
		STANDARD DEV.	0.0	0.0	0.0	0.0	0.0	0.0	0.00002	0.00001	0.00001	0.00001	0.00000	6	
SEQUENCE 6	4.0	2.0	1	12.9	11.2	1.7	2.1	1.8	0.3	0.00169	0.00177	0.00173	0.00028	6,418	
			2	12.8	11.1	1.7	2.1	1.8	0.3	0.00171	0.00180	0.00175	0.00029	6,307	
			3	12.9	11.2	1.7	2.1	1.8	0.3	0.00169	0.00179	0.00174	0.00028	6,374	
			4	12.8	11.1	1.7	2.1	1.8	0.3	0.00169	0.00179	0.00174	0.00028	6,328	
			5	12.8	11.1	1.7	2.1	1.8	0.3	0.00171	0.00180	0.00175	0.00029	6,281	
		COLUMN AVERAGE	12.8	11.1	1.7	2.1	1.8	0.3	0.00170	0.00179	0.00174	0.00028	6,342		
		STANDARD DEV.	0.1	0.1	0.0	0.0	0.0	0.0	0.00001	0.00001	0.00001	0.00000	55		
SEQUENCE 7	4.0	4.0	1	24.6	22.2	2.3	4.0	3.6	0.4	0.00402	0.00408	0.00405	0.00066	5,445	
			2	24.5	22.2	2.3	4.0	3.6	0.4	0.00404	0.00410	0.00407	0.00066	5,409	
			3	24.5	22.2	2.3	4.0	3.6	0.4	0.00405	0.00412	0.00408	0.00067	5,394	
			4	24.6	22.3	2.3	4.0	3.6	0.4	0.00403	0.00410	0.00406	0.00066	5,439	
			5	24.6	22.3	2.3	4.0	3.6	0.4	0.00402	0.00407	0.00405	0.00066	5,463	
		COLUMN AVERAGE	24.6	22.3	2.3	4.0	3.6	0.4	0.00403	0.00409	0.00406	0.00066	5,430		
		STANDARD DEV.	0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00002	0.00002	0.00000	28		

Source: Kingston Description: Poned Fly Ash (Cell III) 95% Modified Dry Density at Optimum Moisture Content

SEQUENCE 8	4.0	6.0	1	37.1	33.4	3.7	6.0	5.4	0.6	0.00653	0.00655	0.00654	0.00106	5.066
			2	37.2	33.5	3.7	6.0	5.4	0.6	0.00652	0.00655	0.00653	0.00106	5.085
			3	37.2	33.5	3.7	6.0	5.4	0.6	0.00649	0.00655	0.00652	0.00106	5.101
			4	37.1	33.4	3.7	6.0	5.4	0.6	0.00652	0.00655	0.00653	0.00106	5.075
			5	37.1	33.4	3.7	6.0	5.4	0.6	0.00653	0.00655	0.00654	0.00106	5.066
	COLUMN AVERAGE			37.2	33.5	3.7	6.0	5.4	0.6	0.00652	0.00655	0.00653	0.00106	5.078
	STANDARD DEV.			0.1	0.1	0.0	0.0	0.0	0.0	0.00001	0.00000	0.00001	0.00000	15

SEQUENCE 9	4.0	8.0	1	49.9	45.0	4.8	8.1	7.3	0.8	0.00861	0.00861	0.00861	0.00140	5.185
			2	49.9	45.0	4.9	8.1	7.3	0.8	0.00860	0.00857	0.00858	0.00140	5.202
			3	49.8	45.0	4.8	8.0	7.3	0.8	0.00862	0.00862	0.00862	0.00140	5.176
			4	49.8	44.9	4.9	8.0	7.3	0.8	0.00863	0.00861	0.00862	0.00140	5.171
			5	49.8	45.0	4.9	8.0	7.3	0.8	0.00860	0.00861	0.00860	0.00140	5.181
	COLUMN AVERAGE			49.8	45.0	4.9	8.1	7.3	0.8	0.00861	0.00860	0.00861	0.00140	5.183
	STANDARD DEV.			0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00002	0.00002	0.00000	12

SEQUENCE 10	4.0	10.0	1	62.4	56.3	6.1	10.1	9.1	1.0	0.01033	0.01030	0.01032	0.00168	5.412
			2	62.4	56.3	6.1	10.1	9.1	1.0	0.01029	0.01030	0.01030	0.00168	5.422
			3	62.3	56.3	6.1	10.1	9.1	1.0	0.01028	0.01030	0.01029	0.00168	5.425
			4	62.3	56.2	6.1	10.1	9.1	1.0	0.01032	0.01030	0.01031	0.00168	5.409
			5	62.3	56.2	6.1	10.1	9.1	1.0	0.01033	0.01031	0.01032	0.00168	5.402
	COLUMN AVERAGE			62.3	56.3	6.1	10.1	9.1	1.0	0.01031	0.01030	0.01031	0.00168	5.414
	STANDARD DEV.			0.0	0.0	0.0	0.0	0.0	0.0	0.00002	0.00000	0.00001	0.00000	10

Source:	Kingston	Description:	Ponded Fly Ash (Cell III)	95% Modified Dry Density at Optimum Moisture Content										
SEQUENCE 11	2.0	2.0	1	13.3	11.3	2.1	2.2	1.8	0.3	0.00207	0.00213	0.00210	0.00034	5,330
			2	13.3	11.3	2.1	2.2	1.8	0.3	0.00207	0.00214	0.00210	0.00034	5,314
			3	13.3	11.2	2.1	2.1	1.8	0.3	0.00208	0.00215	0.00211	0.00034	5,255
			4	13.3	11.2	2.1	2.1	1.8	0.3	0.00208	0.00216	0.00212	0.00035	5,236
			5	13.3	11.3	2.1	2.2	1.8	0.3	0.00209	0.00217	0.00213	0.00035	5,250
				13.3	11.2	2.1	2.1	1.8	0.3	0.00208	0.00215	0.00211	0.00034	5,277
				0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00002	0.00001	0.00000	42
SEQUENCE 12	2.0	4.0	1	24.3	22.0	2.3	3.9	3.6	0.4	0.00493	0.00497	0.00495	0.00081	4,407
			2	24.3	22.0	2.3	3.9	3.6	0.4	0.00495	0.00501	0.00498	0.00081	4,377
			3	24.3	22.0	2.3	3.9	3.6	0.4	0.00493	0.00498	0.00495	0.00081	4,401
			4	24.4	22.1	2.3	3.9	3.6	0.4	0.00494	0.00499	0.00496	0.00081	4,409
			5	24.3	22.0	2.3	3.9	3.5	0.4	0.00495	0.00504	0.00499	0.00081	4,363
				24.3	22.0	2.3	3.9	3.6	0.4	0.00494	0.00500	0.00497	0.00081	4,391
				0.0	0.0	0.0	0.0	0.0	0.0	0.00001	0.00003	0.00002	0.00000	21
SEQUENCE 13	2.0	6.0	1	36.4	33.0	3.4	5.9	5.3	0.5	0.00782	0.00784	0.00783	0.00128	4,184
			2	36.7	33.5	3.2	5.9	5.4	0.5	0.00788	0.00791	0.00789	0.00129	4,204
			3	36.8	33.3	3.5	5.9	5.4	0.6	0.00784	0.00785	0.00784	0.00128	4,205
			4	36.8	33.5	3.2	5.9	5.4	0.5	0.00791	0.00792	0.00792	0.00129	4,202
			5	36.7	33.5	3.2	5.9	5.4	0.5	0.00789	0.00789	0.00789	0.00129	4,213
				36.7	33.4	3.3	5.9	5.4	0.5	0.00787	0.00788	0.00787	0.00128	4,201
				0.1	0.2	0.1	0.0	0.0	0.0	0.00004	0.00003	0.00004	0.00001	11

Source: Kingston		Description: Ponded Fly Ash (Cell III)					95% Modified Dry Density at Optimum Moisture Content									
SEQUENCE 14	2.0	8.0	1	49.3	44.8	4.5	8.0	7.2	0.7	0.01017	0.01012	0.01015	0.00165	4,382		
			2	49.3	44.8	4.5	8.0	7.2	0.7	0.01017	0.01013	0.01015	0.00165	4,382		
			3	49.4	44.9	4.5	8.0	7.3	0.7	0.01014	0.01012	0.01013	0.00165	4,397		
			4	49.5	45.0	4.5	8.0	7.3	0.7	0.01015	0.01014	0.01015	0.00165	4,395		
			5	49.4	44.9	4.5	8.0	7.3	0.7	0.01013	0.01009	0.01011	0.00165	4,405		
			49.4	44.9	4.5	8.0	7.3	0.7	0.01015	0.01012	0.01014	0.00165	4,392			
			0.1	0.1	0.0	0.0	0.0	0.0	0.00002	0.00002	0.00002	0.00000	10			
SEQUENCE 15	2.0	10.0	1	62.0	56.0	6.0	10.0	9.0	1.0	0.01182	0.01180	0.01181	0.00192	4,703		
			2	62.0	56.0	6.0	10.0	9.0	1.0	0.01182	0.01178	0.01180	0.00192	4,709		
			3	62.0	56.0	6.0	10.0	9.0	1.0	0.01182	0.01178	0.01180	0.00192	4,705		
			4	62.0	56.0	6.0	10.0	9.0	1.0	0.01182	0.01178	0.01180	0.00192	4,707		
			5	62.0	56.0	6.0	10.0	9.0	1.0	0.01182	0.01178	0.01180	0.00192	4,706		
			62.0	56.0	6.0	10.0	9.0	1.0	0.01182	0.01178	0.01180	0.00192	4,706			
			0.0	0.0	0.0	0.0	0.0	0.0	0.00000	0.00001	0.00001	0.00000	2			

SUBMITTED BY, DATE

RJ Bingham 9/5/95

LABORATORY MANAGER

FIGURE 1 - Logarithmic Plot of Resilient Modulus (M_R) vs Cyclic Stress (S_C)

PROJECT NAME: TVA - Fly Ash, Bottom Ash and Scrubber Gypsum Study
 LAW PROJECT NO.: 5810860101
 1. MATERIAL SOURCE: Kingston
 2. MATERIAL DESCRIPTION: Ponded Fly Ash (Cell III)
 3. REMOLDING TARGETS: 95% Modified Dry Density at Optimum Moisture Content
 4. MATERIAL TYPE: 2
 5. TEST DATE: 07-06-1995

$$M_R = K1 (S_C)^{K2} (1+S_3)^{K5}$$

K1 = 3,254
 K2 = -0.09252
 K5 = 0.43051
 R² = 0.91

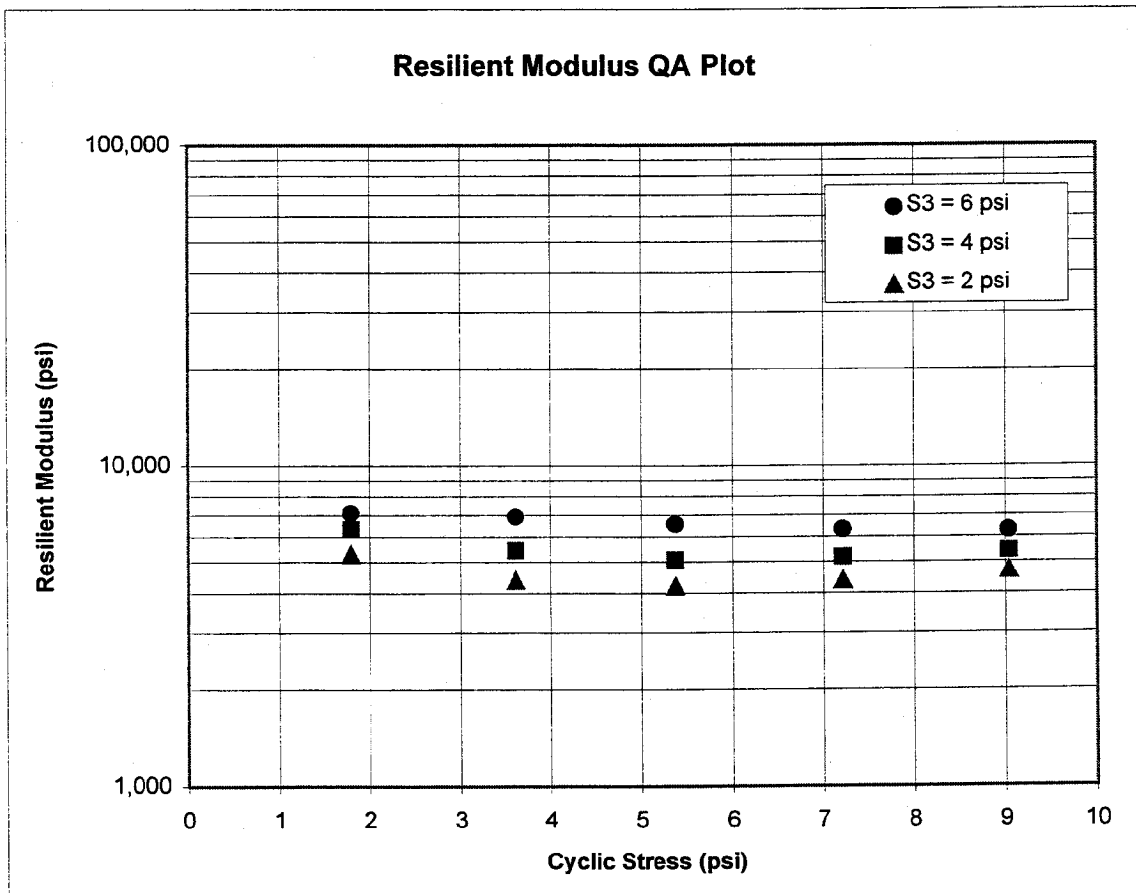


FIGURE 2 - Quick Shear Stress vs Strain

PROJECT NAME: TVA - Fly Ash, Bottom Ash and Scrubber Gypsum Study
LAW PROJECT NO.: 5810860101
1. *MATERIAL SOURCE:* Kingston
2. *MATERIAL DESCRIPTION:* Poned Fly Ash (Cell III)
3. *REMOLDING TARGETS:* 95% Modified Dry Density at Optimum Moisture Content
4. *MATERIAL TYPE* 2
5. *TEST DATE* 07-06-1995

